

Disentangling transient charge order from structural dynamics contributions during coherent atomic motion studied by ultrafast resonant x-ray diffraction

L. Rettig,^{1,2,*} A. Caviezel,¹ S. O. Mariager,¹ G. Ingold,^{1,3} C. Dornes,⁴ S.-W. Huang,^{1,†} J. A. Johnson,^{1,‡} M. Radovic,^{1,3} T. Huber,⁴ T. Kubacka,⁴ A. Ferrer,^{1,4} H. T. Lemke,^{5,§} M. Chollet,⁵ D. Zhu,⁵ J. M. Glownia,⁵ M. Sikorski,⁵ A. Robert,⁵ M. Nakamura,^{6,||} M. Kawasaki,^{7,6} Y. Tokura,^{7,6} S. L. Johnson,⁴ P. Beaud,^{1,3} and U. Staub^{1,¶}

¹Swiss Light Source, Paul Scherrer Institut, 5232 Villigen PSI, Switzerland

²Abteilung Physikalische Chemie, Fritz-Haber-Institut der Max-Planck-Gesellschaft, Faradayweg 4-6, 14195 Berlin, Germany

³SwissFEL, Paul Scherrer Institut, 5232 Villigen PSI, Switzerland

⁴Institute for Quantum Electronics, ETH Zürich, 8093 Zürich, Switzerland

⁵LCLS, SLAC National Accelerator Laboratory, Menlo Park, California 94025, USA

⁶RIKEN Center for Emergent Matter Science, Wako 351-0198, Japan

⁷Department of Applied Physics and Quantum-Phase Electronics Center, University of Tokyo, Hongo, Tokyo 113-8656, Japan



(Received 25 July 2018; published 9 April 2019)

We report on the ultrafast dynamics of charge order and structural response during the photoinduced suppression of charge and orbital order in a mixed-valence manganite. Employing femtosecond time-resolved resonant x-ray diffraction below and at the Mn *K* absorption edge, we present a method to disentangle the transient charge order and structural dynamics in thin films of $\text{Pr}_{0.5}\text{Ca}_{0.5}\text{MnO}_3$. Based on the static resonant scattering spectra, we extract the dispersion correction of charge-ordered Mn^{3+} and Mn^{4+} ions, allowing us to separate the transient contributions of purely charge order from structural contributions to the scattering amplitude after optical excitation. Our finding of a coherent structural mode at around 2.3 THz, which primarily modulates the lattice but does not strongly affect the charge order, supports the picture of the charge order being the driving force of the combined charge, orbital, and structural transition.

DOI: [10.1103/PhysRevB.99.134302](https://doi.org/10.1103/PhysRevB.99.134302)

I. INTRODUCTION

The coupling between the lattice and the electronic structure is of great importance for the physical properties of materials. A particular interest lies in materials which have strong correlation between the electronic, orbital, magnetic, and structural degrees of freedom. These interactions often lead to new ground states of the materials, which are characterized by induced orders in one or more of the subsystems, such as superconducting states, structural phase transitions, and charge-density waves. Often, several orders coexist in a material, and their cooperative or competing character is fundamental for the material properties. In particular, it is of great interest to identify the primary instability that drives the phase transition and a possible parasitic order. One example for such a state is the structural-nematic phase transition in the Fe pnictide parent compounds, where electronic nematic order

is considered to drive a concomitant structural phase transition [1].

To understand these couplings, a promising route is to manipulate, e.g., the crystal structure and investigate the corresponding changes in the other degrees of freedom. A widely used way is to use epitaxial strain to modify the crystal structure or to apply high pressure. Although these approaches are very useful and have led to very interesting observations, they both are rather limited in their applicability and might also change the microstructure of the materials. In addition, strongly coupled phase transitions often show in equilibrium identical behavior as a function of temperature or pressure, and understanding their hierarchy is therefore very challenging.

These limitations can be overcome by studying the material response to an ultrafast stimulus, which is faster than the fundamental interaction timescale between the degrees of freedom. There have been many studies along these lines. Here we are particularly interested using x rays as a probe of either magnetic, electronic, or crystal structure, as x rays are excellent probes for these (see, e.g., Buzzi *et al.* [2]). A very powerful way to study the coupling between electronic and structural order is to excite the structure directly by terahertz or midinfrared radiation and test the ultrafast electronic or magnetic responses to the excitation. This approach has led to very interesting variation of the electronic or magnetic properties of materials in several correlated electron systems [3–9]. Another approach, although less direct, is to electronically excite a material by an optical excitation and determine

*Corresponding author. rettig@fhi-berlin.mpg.de

†Present address: MAX IV Laboratory, Lund University, PO Box 118, SE-22100 Lund, Sweden.

‡Present address: Department of Chemistry and Biochemistry, Brigham Young University, Provo, UT 84602, USA.

§urs.staub@psi.ch

||Present address: SwissFEL, Paul Scherrer Institut, 5232 Villigen PSI, Switzerland.

¶Present address: PRESTO, Japan Science and Technology Agency, Kawaguchi 332-0012, Japan.

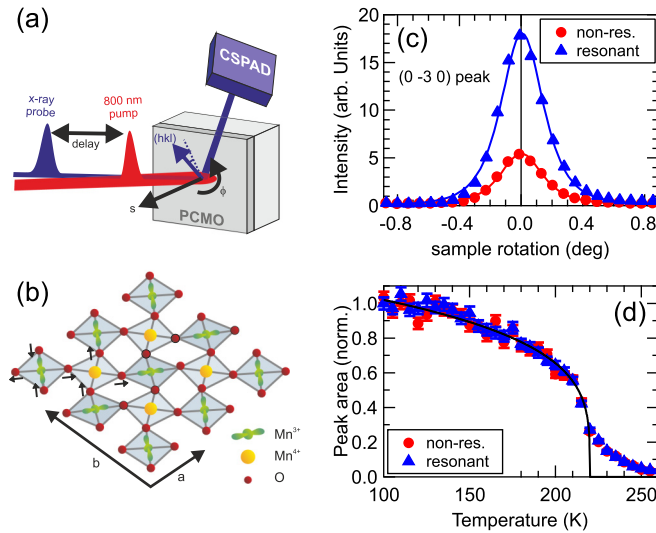


FIG. 1. Experimental scheme and static x-ray diffraction results. (a) Schematic of the time-resolved resonant x-ray diffraction experiment. (b) Sketch of the charge and orbitally ordered phase of alternating Mn^{3+} and Mn^{4+} ions in the a/b plane. (c) Static rocking curves of the $(0\bar{3}0)$ reflection measured by a sample rotation about the surface normal, below (red circles, 6.530 keV) and at resonance (blue triangles, 6.555 keV) with the Mn K absorption edge. (d) Temperature dependence of the normalized integrated on- and off-resonant peak intensities. The solid black line is a power law fit. In good agreement with transport measurements we find $T_{\text{COO}} \approx 220$ K.

the structural and electronic changes in the time domain. As an example, x rays have been used to quantify the structural motion of a coherent phonon and photoemission to determine the changes in the electronic structure in Fe pnictides [10–13]. This allows e.g., determining the mode-dependent electron phonon coupling.

Manganites are another class of interesting materials, in which the correlation between electronic ordering and the associated structural distortions has been intensely studied in the time domain [8, 14–19]. The half-doped simple perovskite $\text{Pr}_{0.5}\text{Ca}_{0.5}\text{MnO}_3$ (PCMO) shows a charge and orbital order (CO/OO) phase transition around 240 K concomitant with a structural distortion, characterized by an alternating pattern of Mn^{3+} and Mn^{4+} ions, as schematically shown in Fig. 1(b). This transition is followed in temperature by an antiferromagnetic order of the Mn^{3+} spins around 150 K [20]. The correlation between the electronic and crystal structures has been studied by ultrafast time-resolved resonant and nonresonant x-ray diffraction [17]. In particular, reflections that are selectively sensitive to electronic order, the orbital order, or the structural distortions have been investigated. The coherent dynamics of all of these reflections and the optically driven phase transition could be well described by an ultrafast quench of the charge order with a time-dependent order parameter that triggers the structural phase transition and launches several coupled coherent phonon modes [17].

However, an important open question remained about whether the coherent modes also couple back onto the charge

order and coherently modulate the charge disproportionation between neighboring Mn sites. Although the mode amplitude for the $(0\bar{3}0)$ reflection, which is primarily sensitive to the electronic ordering, has been found to be much weaker than that of reflections sensitive to the structural distortion alone, a clear separation of electronic and structural components was beyond the scope of our earlier study [17]. To clarify this point and to better understand the hierarchy of coupled phase transitions in $\text{Pr}_{0.5}\text{Ca}_{0.5}\text{MnO}_3$, we address here how the electronic states are modified during the coherent motion of the ions involved in the long-lived low-frequency coherent phonon oscillation. Resonant x-ray diffraction has been used to disentangle electronic and lattice degrees of freedom statically in complex oxides [21–28]. The use of femtosecond x-ray pulses allows us to disentangle these degrees of freedom in a single experiment by simply tuning the x-ray energy on and off resonance. With this intrinsically combined spectroscopic and diffraction approach we can determine the role of this mode in relation to the electronic ordering.

II. EXPERIMENTAL DETAILS

Resonant x-ray diffraction experiments were performed on a thin film of $\text{Pr}_{0.5}\text{Ca}_{0.5}\text{MnO}_3$ of approximately 40 nm thickness grown on an (011) -oriented $(\text{LaAlO}_3)_{0.3}(\text{SrAl}_{0.5}\text{Ta}_{0.5}\text{O}_3)_{0.7}$ (LSAT) substrate using a pulsed laser deposition technique with a laser pulse frequency of 2 Hz at 850 °C in an oxygen pressure of 1.5 mTorr (for details see Ref. [29]).

Static energy-dependent x-ray diffraction experiments were performed at the X04SA beamline at the Swiss Light Source, Paul Scherrer Institute, using the surface science scattering end station [30] equipped with a Pilatus 200k pixel detector [31], and time-resolved on- and off-resonant diffraction experiments were performed at the X-ray Pump-Probe (XPP) instrument [32] at the Linac Coherent Light Source (LCLS) [33] x-ray free electron laser (XFEL) at the SLAC National Accelerator Laboratory. In both experiments, an asymmetric diffraction configuration [34], as sketched in Fig. 1(a), was used, where the horizontally polarized x-ray probe pulses entered the film at 8° grazing incidence. The x-ray energy was tuned in the vicinity of the Mn K edge using a silicon (111) monochromator, with an energy resolution of ≈ 1.1 eV. During energy scans, the sample was held in the diffraction condition (constant \mathbf{q} scans). The sample temperature was controlled between 100 K and the charge ordering temperature of $T_{\text{COO}} \approx 220$ K using a cryogenic nitrogen blower.

For time-resolved x-ray diffraction experiments performed at the LCLS, a weakly focused ($230 \times 230 \mu\text{m}^2$) 55-fs optical pulse with a wavelength of 800 nm excited the sample with a repetition rate of 120 Hz at an incidence angle of 14° (p polarization), synchronized to the ≈ 50 -fs x-ray probe pulses from the LCLS, and diffracted x-ray pulses were detected at the full repetition rate using the Cornell-SLAC Pixel Array Detector (CSPAD) [35]. The timing jitter between pump and probe pulses was measured and corrected shot by shot using the spectral encoding correlation technique [36], with an accuracy of ≈ 15 fs, yielding an overall temporal resolution of ≈ 85 fs.

III. RESULTS AND DISCUSSION

The charge ordering manifests in a lowering of crystal symmetry that is accompanied by a structural distortion and a staggered configuration of the Mn^{3+} orbitals. This results in the occurrence of additional, symmetry-forbidden reflections in the x-ray diffraction signal. The diffraction intensity of some of these reflections becomes strongly modulated in the vicinity of the Mn K absorption edge due to the charge disproportionation of neighboring Mn sites. Figure 1(c) shows x-ray rocking curves of the high-temperature symmetry-forbidden $(0\bar{3}0)$ reflection, measured by rotating the sample about the surface normal, below (red) and at (blue) the Mn K absorption edge. Here the strong resonant enhancement of the intensity by more than three times at resonance arises due to the charge ordering pattern, while the intensity off resonance originates from the accompanying structural distortion. The temperature dependence of the integrated peak intensity of this reflection below and at resonance is shown in Fig. 1(d), which represents the regular behavior of a reflection that follows the order parameter squared. The equivalent temperature dependence of the on- and off-resonant diffraction intensities demonstrates the strong coupling of the structural and charge order transitions in thermal equilibrium in contrast to results found in nickelates [21].

A. Refinement of static resonant x-ray diffraction data

The resonant enhancement of the x-ray diffraction signal of a charge order reflection arises due to the valence charge inequality of neighboring ions, which gives rise to an energy shift of the absorption edge and therefore to a resonant contribution from the x-ray dispersion correction close to an absorption edge. As the film is very thin compared to the x-ray penetration depth, an absorption correction, which typically creates large uncertainties on such data of single crystals, is negligible in our study. In addition, as the peaks are broad due to the finite size of the film, refraction effects can also be ignored when changing the x-ray energy. Note that we consider here only the electronic difference (labeled as charge order/disproportionation) on the Mn sites as seen by the dipole transition at the Mn K edge that probes the Mn $4p$ states. This analysis remains valid independent of the microscopic origin of the resonant behavior, e.g., due to orbital contributions or phenomena such as bond valence order [22–28]. Distinguishing such models would require nontrivial first-principles calculations of the spectral shape of the scattering factors at resonance that go beyond the goal of this study. The charge disproportionation and the respective dispersion corrections in such an electronic ordered system can directly be determined from resonant x-ray diffraction data of selected symmetry-forbidden charge order peaks of type $(0k0)$ with k being odd [21,37,38]. For the case of $\text{Pr}_{0.5}\text{Ca}_{0.5}\text{MnO}_3$, the resonant structure factor near the Mn K edge can be written to first order as

$$F_{(0k0)} = \underbrace{A_{\text{Pr/Ca,O}}(Q, E)}_{\text{structure } \sigma} + \underbrace{4\Delta f_{\text{Mn}}^0(Q) + 4\Delta f'_{\text{Mn}}(E) + 4i\Delta f''_{\text{Mn}}(E)}_{\text{charge order } \eta}. \quad (1)$$

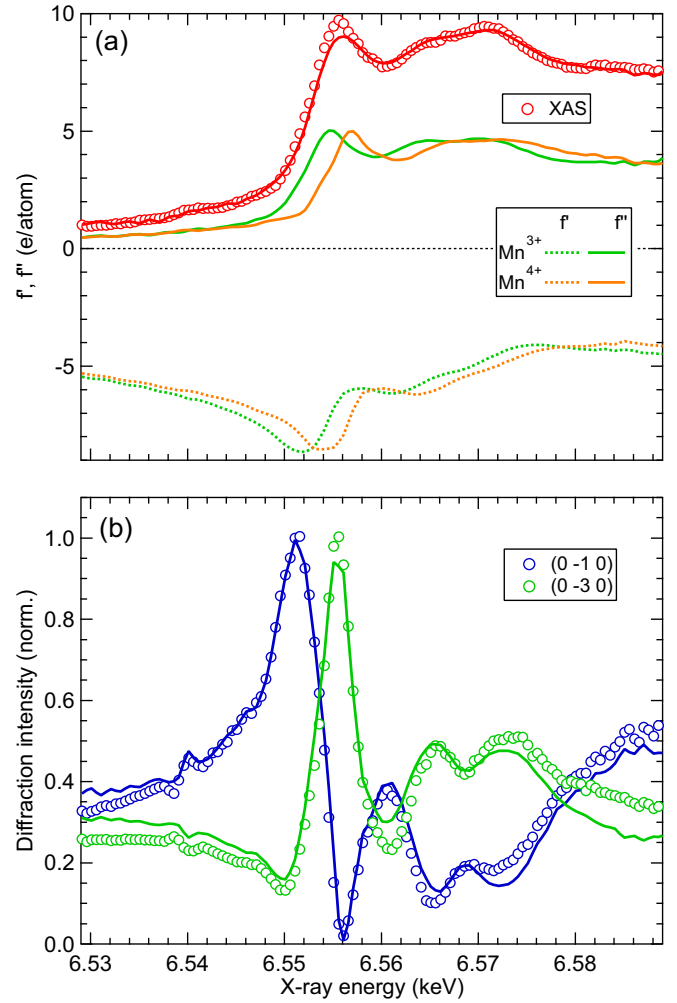


FIG. 2. Energy dependence of resonant x-ray diffraction. (a) X-ray fluorescence signal (red) and (b) resonant diffraction intensity of the $(0\bar{1}0)$ (blue) and $(0\bar{3}0)$ (green) peaks across the Mn K absorption edge. The solid red, blue, and green lines are the results of a refinement of the data (see text). The extracted real (imaginary) part of the anomalous dispersion corrections of Mn^{3+} and Mn^{4+} sites is shown in (a) as green and yellow dashed (solid) lines, respectively.

Here the first term corresponds to the structural contributions from the displacements of Pr, Ca, and O ions. The contribution from the charge disproportionation is determined by the form factor differences $\Delta f_{\text{Mn}} = f_{\text{Mn}^{3+}} - f_{\text{Mn}^{4+}}$ and consists of three parts, which represent the change in Thompson scattering amplitude and the difference in the real and imaginary parts of the dispersion correction between the charge-ordered ions. With knowledge of the low-temperature structure [39] this expression for the structure factor can be used to describe the resonant diffraction intensity $I \propto |F(Q, E)|^2$ and to determine the dispersion corrections $f_{\text{Mn}^{3+}}$ and $f_{\text{Mn}^{4+}}$. Additionally, according to the optical theorem the x-ray absorption spectrum is proportional to the average imaginary part of the dispersion correction $f''_{\text{Mn}^{3+}} + f''_{\text{Mn}^{4+}}$, which is fitted simultaneously.

We adopt the following iterative global fit procedure to determine the dispersion corrections $f_{\text{Mn}^{3+}}$ and $f_{\text{Mn}^{4+}}$ from the x-ray fluorescence spectrum [Fig. 2(a)] and the resonant x-ray diffraction spectra for the $(0\bar{1}0)$ and $(0\bar{3}0)$

reflections [Fig. 2(b)]: In each iteration, the imaginary parts of the dispersion corrections $f''_{\text{Mn}^{3+}} + f''_{\text{Mn}^{4+}}$ are varied, and the real parts $f'_{\text{Mn}^{3+}} + f'_{\text{Mn}^{4+}}$ are determined by Kramers-Kronig transformation, using tabulated atomic scattering factor values outside the experimental region [40]. From these, the resonant diffraction intensities for the two peaks are calculated and together with the absorption spectrum are fitted to the experimental data. Additionally, a regularization term of the form

$$\lambda [f''_{\text{Mn}^{3+}}(E) - f''_{\text{Mn}^{4+}}(E + \delta E)]^2, \quad (2)$$

which favors resemblance of the individual f'' curves shifted by the energy δE , is introduced, where λ controls the importance of this condition.

The results of this iterative fitting procedure are shown as solid lines in Fig. 2 and reproduce all data reasonably well. In particular, the shifted maxima of the resonant diffraction curves are well captured by the model. Additionally, Fig. 2(a) shows the determined real and imaginary parts of the dispersion correction for Mn^{3+} and Mn^{4+} . The fit yields an energy shift of the absorption edge of $\delta E \approx 2.2$ eV, which in comparison to the single-valence compounds LaMnO_3 and CaMnO_3 would correspond to a valence state of $\text{Mn}^{3.2+}$ and $\text{Mn}^{3.8+}$ in the approximation of spherical scattering factors [22]. These extracted dispersion corrections can now be used to disentangle the time dependence of structural and charge order dynamics from measurements taken at two different energies.

B. Time-dependent structural and charge order dynamics

Figure 3(a) shows the time-resolved diffraction intensities of the $(0\bar{3}0)$ reflection at two different x-ray energies below resonance (red) and at the maximum of the resonant intensity (blue), with an incident excitation fluence of $F = 1.8$ mJ/cm². The experimental error bars are determined as the standard errors of the XFEL shot distribution of the diffraction signal, rescaled to the standard deviation of the signal before excitation to account for possible drifts. Both curves show a fast drop within the time resolution of the experiment, followed by a weak recovery on a picosecond timescale, overlaid by weak coherent oscillations. Apart from a slightly larger suppression at resonance, the two curves look very similar.

In order to separate the dynamics of charge order and structural distortion, we rewrite Eq. (1) introducing time-dependent structural and charge order parameters $\sigma(t)$ and $\eta(t)$, respectively:

$$F_{(0\bar{3}0)}^E(t) = \sigma(t)C_1^E + \eta(t)C_2^E, \quad (3)$$

with $C_1^E = A_{\text{Pr/CaO}}(E)$ and $C_2^E = 4\Delta f_{\text{Mn}}^0 + 4\Delta f'_{\text{Mn}}(E) + 4i\Delta f''_{\text{Mn}}(E)$ and $E = 6.530$ keV and 6.555 keV. This expression allows us to investigate the sensitivity of the diffraction intensity to the structural distortion and to the charge ordering. The corresponding diffraction intensities normalized to the value at $\sigma = \eta = 1$ are shown in Figs. 4(a) and 4(b) as a function of the size of the corresponding order parameters for the two investigated energies. Here green curves show the dependence on η , while yellow curves show the dependence on σ , and the respective other order parameter is held at the value indicated by the dashed green and yellow lines.

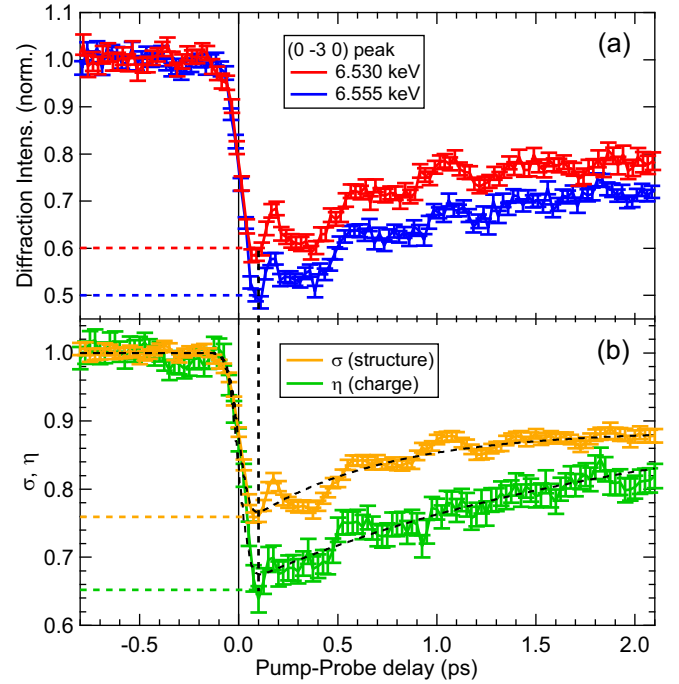


FIG. 3. Time-dependent resonant x-ray diffraction. (a) Normalized time-dependent diffraction intensity of the $(0\bar{3}0)$ peak measured off resonance (red, 6.530 keV) and on resonance (blue, 6.555 keV, same data as shown in Fig. 2(c) of Ref. [17]) with the Mn K absorption edge. Error bars represent standard errors of the XFEL shot distribution, corrected for XFEL drifts (see text). (b) Time-dependent structural (σ , yellow) and charge (η , green) order parameters determined by applying the solution of Eqs. (3) and (4) to the data in (a). Dashed lines are single-exponential fits (see text).

Due to the fact that the charge ordering mostly influences the diffraction signal at resonance, the off-resonant diffraction intensity is, as expected, mostly sensitive to the structural distortion and shows only a weak variation with the charge order parameter η . In contrast, at the resonance energy, both structural and charge order parameters show a similar influence

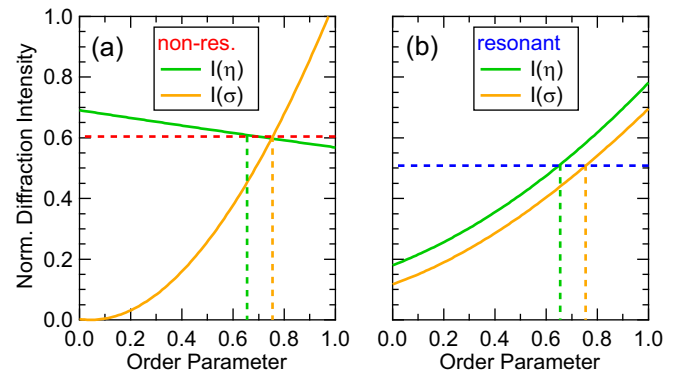


FIG. 4. Determination of the transient order parameters. Dependence of the normalized diffraction intensity on the structural (yellow) and charge order parameters (green) (a) off resonance and (b) on resonance with the Mn K absorption edge. Dashed lines mark the values of the order parameters obtained at the minimum of the diffraction intensity time traces. The respective other order parameter is kept fixed at this value.

on the diffraction intensity, demonstrating the necessity for a proper description of the energy-dependent x-ray intensity to disentangle charge and structural order dynamics.

This is achieved by inverting the expressions for the normalized diffraction intensities

$$\left(\frac{I(t)}{I_0}\right)_{(0\bar{3}0)}^E = \left|\left(\frac{F(t)}{F_0}\right)_{(0\bar{3}0)}^E\right|^2 \quad (4)$$

evaluated at the two measured energies to yield the corresponding structural and charge order parameters $\sigma(t)$ and $\eta(t)$, respectively. The disentangled normalized time-dependent structural and charge order parameters are shown in Fig. 3(b). Both order parameters show a very fast drop within the temporal resolution of ~ 80 fs, followed by a slow recovery on a picosecond timescale. The charge order parameter $\eta(t)$ shows a significantly stronger suppression, with a minimum of ~ 0.65 at 100 fs, than the structural order parameter $\sigma(t)$, which shows a minimum of ~ 0.76 at the same time. As a cross-check, we can calculate the diffraction intensities for the two energies from our diffraction model for this time delay (Fig. 4). The values of ~ 0.6 for the nonresonant normalized diffraction intensity and ~ 0.5 for the resonant normalized diffraction intensity agree well with the observed intensities at $t = 100$ fs; in particular their ratio matches very well, demonstrating the consistency of our evaluation.

The stronger response of the charge order parameter suggests the suppression of charge order as the driving force for the structural dynamics, in agreement with our previous description of the coupled charge, orbital, and structural dynamics by a time-dependent charge order parameter [17]. However, how strongly the structural dynamics could also influence the charge order dynamics on the ultrafast timescale is still an open question. Apart from the strong suppression around t_0 , weak coherent oscillations from coherently excited phonon modes are visible in the raw diffraction data. Interestingly, however, these oscillations predominantly show up in the structural order parameter. For a more quantitative analysis, a smooth exponential background function is subtracted from the curves in Fig. 3(b), and the residual coherent signal is shown in Fig. 5(a) for the two order parameters. Oscillation amplitudes are extracted by fitting a damped sinusoidal function to the data, where the damping time constant is fixed to the value determined in our previous refinement of the structural dynamics [17]. The fit for $\sigma(t)$ yields a reasonable description (adjusted $R^2 = 0.66$) of the data with an initial oscillation amplitude of $4.8\% \pm 0.8\%$ at a frequency of 2.2 ± 0.1 THz (black solid line). A similar fit of $\eta(t)$ with the same (fixed) oscillation frequency yields a significantly worse description of the data (dashed black line, adjusted $R^2 = 0.07$) and a much smaller initial amplitude of $2.5\% \pm 1.7\%$. The much weaker coherent response of η is corroborated by the fast Fourier transform (FFT) of the two order parameters shown in Fig. 5(b). Here $\sigma(t)$ shows a strong spectral peak at ~ 2.3 THz, very close to the dominating coherent phonon frequency of the in-plane motion of the Pr/Ca ions [17]. In contrast, the spectrum of $\eta(t)$ shows a much smaller and broader response in a larger spectral region, which is close to the noise limit. Therefore, we conclude that the coherent phonon mode that governs the structural

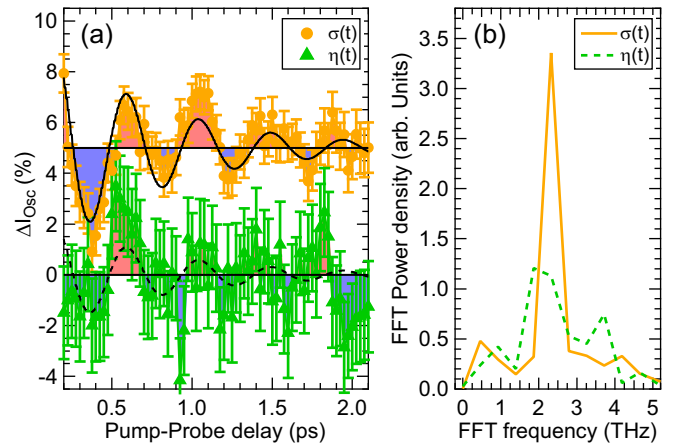


FIG. 5. Coherent oscillations of structural and charge components. (a) Oscillatory component of the structural (yellow) and charge (green) order parameters after subtraction of the single-exponential background shown in Fig. 3. Data are vertically offset, and lines are damped cosine fits (see text). (b) Fast Fourier transform power density of the data shown in (a).

transition does not couple or only weakly couples back on the charge order parameter.

The observed coherent mode around 2.3 THz agrees well with the coherent modes observed in $\text{Pr}_{0.5}\text{Ca}_{0.5}\text{MnO}_3$ and similar manganites [16,17,41–43], which have been identified as coherent oscillations of the Pr and Ca cations coupled to lateral motion of the Mn-O cages [42], driven by the suppression of charge order and Jahn-Teller distortion [17]. This mode does not soften significantly for increasing temperatures when approaching the charge and orbital ordering transition [41], suggesting that this mode is not a true soft mode of the transition and is therefore not relevant for the electronic ordering. The amplitude mode of the charge order is expected to be linked to a change in the volume of the oxygen octahedra as a change in ionic charge impacts the ionic radii of the Mn ions. Consequently, a difference in charge does expand and shrink the size of the octahedra alternately along the ordering wave vector, as has been observed by the structural determination in the ground state [39]. Candidates for the relevant modes for the charge and orbital orders are the asymmetric stretch and Jahn-Teller modes of the distorted octahedra, respectively, which occur at much faster frequencies of around 16 THz [17,18]. The initial dynamics of those oscillations occur within the first ~ 100 fs after excitation and are not accessible with our current temporal resolution. However, due to the strongly coupled nature of the various modes in the system, the slow coherent cation oscillation dominates the dynamics at later times also of those faster modes and leads to a coherent modulation of their coordinates [17]. In an intuitive picture, this can be seen as a harmonic oscillator driven off resonantly which also oscillates with the driving frequency. This implies that the coherent oscillations found in the structural dynamics indeed correspond to a modulation of the octahedra volume along the charge order coordinate. Our observation of the absence of a clear coherent response in the charge order itself thus strongly suggests that those coherent structural modulations of the octahedral volumes do not lead to a transient charge transfer between neighboring Mn sites.

This brings us back to our initial question about the hierarchy of coupled phase transitions in this system. The absence of charge order response to a structural modulation demonstrates that the charge and orbital orders are the driving force of the coupled phase transition, and the structural distortion can be regarded as a secondary order, which stabilizes the electronic order but is not sufficient to drive the transition alone. This behavior is analogous to the coupled structural/nematic transition in the Fe pnictide parent compounds, where strong evidence for an electronically driven phase transition and a secondary structural transition also exists [1,13]. The identification of the hierarchy of coupled phase transitions in complex materials as demonstrated in our experiment not only provides an important benchmark for theory but could also allow identifying the appropriate handle for precise control of phase transitions with competing orders, such as the charge-density wave and stripe order ground state present in superconducting cuprates. Our approach of separating structural and electronic contributions from on- and off-resonant x-ray diffraction data can also be extended to such incommensurate or bond-centered ordered systems, provided that the equilibrium structure is known.

IV. CONCLUSION

In conclusion, we investigated the transient coupling between charge order and structural response in charge and orbitally ordered $\text{Pr}_{0.5}\text{Ca}_{0.5}\text{MnO}_3$. Using time-resolved x-ray diffraction both below and at the Mn K absorption edge, we

were able to separate contributions of purely charge order from structural contributions to the scattering amplitude. We found a coherent structural mode which primarily modulates the lattice but does not strongly affect the charge order. Our findings confirm the charge order is the driving force for the combined charge, orbital, and structural transition, where the structural transition is a secondary effect induced by the electronic order.

ACKNOWLEDGMENTS

This research was carried out on the XPP Instrument at the Linac Coherent Light Source (LCLS) at the SLAC National Accelerator Laboratory. LCLS is an Office of Science User Facility operated for the U.S. Department of Energy Office of Science by Stanford University. Use of LCLS, SLAC National Accelerator Laboratory, is supported by the U.S. Department of Energy, Office of Science, Office of Basic Energy Sciences, under Contract No. DE-AC02-76SF00515. Static resonant x-ray diffraction experiments were performed at the X04SA Material Science beamline at the Swiss Light Source, Paul Scherrer Institut, Villigen, Switzerland. This work was supported by the NCCR Molecular Ultrafast Science and Technology (NCCR MUST), a research instrument of the Swiss National Science Foundation (SNSF), and by the German Research Foundation (DFG) within the Emmy Noether program (Grant No. RE 3977/1-1). A.C. and T.K. acknowledge financial support by SNSF, Grants No. 200021_124496 and 200021_144115, respectively.

-
- [1] R. M. Fernandes, A. V. Chubukov, and J. Schmalian, *Nat. Phys.* **10**, 97 (2014).
- [2] M. Buzzi, M. Foerst, R. Mankowsky, and A. Cavalleri, *Nat. Rev. Mater.* **3**, 299 (2018).
- [3] M. Rini, R. Tobey, N. Dean, J. Itatani, Y. Tomioka, Y. Tokura, R. W. Schoenlein, and A. Cavalleri, *Nature (London)* **449**, 72 (2007).
- [4] M. Forst, C. Manzoni, S. Kaiser, Y. Tomioka, Y. Tokura, R. Merlin, and A. Cavalleri, *Nat. Phys.* **7**, 854 (2011).
- [5] M. Forst, R. Mankowsky, H. Bromberger, D. Fritz, H. Lemke, D. Zhu, M. Chollet, Y. Tomioka, Y. Tokura, R. Merlin, J. Hill, S. Johnson, and A. Cavalleri, *Solid State Commun.* **169**, 24 (2013).
- [6] D. Fausti, R. I. Tobey, N. Dean, S. Kaiser, A. Dienst, M. C. Hoffmann, S. Pyon, T. Takayama, H. Takagi, and A. Cavalleri, *Science* **331**, 189 (2011).
- [7] T. Kubacka, J. A. Johnson, M. C. Hoffmann, C. Vicario, S. de Jong, P. Beaud, S. Grübel, S.-W. Huang, L. Huber, L. Patthey, Y.-D. Chuang, J. J. Turner, G. L. Dakovski, W.-S. Lee, M. P. Minitti, W. Schlotter, R. G. Moore, C. P. Hauri, S. M. Koohpayeh, V. Scagnoli, G. Ingold, S. L. Johnson, and U. Staub, *Science* **343**, 1333 (2014).
- [8] V. Esposito, M. Fechner, R. Mankowsky, H. Lemke, M. Chollet, J. M. Glowia, M. Nakamura, M. Kawasaki, Y. Tokura, U. Staub, P. Beaud, and M. Först, *Phys. Rev. Lett.* **118**, 247601 (2017).
- [9] M. Mitrano, A. Cantaluppi, D. Nicoletti, S. Kaiser, A. Perucchi, S. Lupi, P. Di Pietro, D. Pontiroli, M. Riccò, S. R. Clark, D. Jaksch, and A. Cavalleri, *Nature (London)* **530**, 461 (2016).
- [10] L. Rettig, S. O. Mariager, A. Ferrer, S. Grübel, J. A. Johnson, J. Rittmann, T. Wolf, S. L. Johnson, G. Ingold, P. Beaud, and U. Staub, *Phys. Rev. Lett.* **114**, 067402 (2015).
- [11] S. Gerber, K. W. Kim, Y. Zhang, D. Zhu, N. Plonka, M. Yi, G. L. Dakovski, D. Leuenberger, P. Kirchmann, R. G. Moore, M. Chollet, J. M. Glowia, Y. Feng, J.-S. Lee, A. Mehta, A. F. Kemper, T. Wolf, Y.-D. Chuang, Z. Hussain, C.-C. Kao, B. Moritz, Z.-X. Shen, T. P. Devereaux, and W.-S. Lee, *Nat. Commun.* **6**, 7377 (2015).
- [12] S. Gerber, S.-L. Yang, D. Zhu, H. Soifer, J. A. Sobota, S. Rebec, J. J. Lee, T. Jia, B. Moritz, C. Jia, A. Gauthier, Y. Li, D. Leuenberger, Y. Zhang, L. Chaix, W. Li, H. Jang, J.-S. Lee, M. Yi, G. L. Dakovski, S. Song, J. M. Glowia, S. Nelson, K. W. Kim, Y.-D. Chuang, Z. Hussain, R. G. Moore, T. P. Devereaux, W.-S. Lee, P. S. Kirchmann, and Z.-X. Shen, *Science* **357**, 71 (2017).
- [13] L. Rettig, S. O. Mariager, A. Ferrer, S. Grübel, J. A. Johnson, J. Rittmann, T. Wolf, S. L. Johnson, G. Ingold, P. Beaud, and U. Staub, *Struct. Dyn.* **3**, 023611 (2016).
- [14] T. Ogasawara, T. Kimura, T. Ishikawa, M. Kuwata-Gonokami, and Y. Tokura, *Phys. Rev. B* **63**, 113105 (2001).
- [15] D. Polli, M. Rini, S. Wall, R. W. Schoenlein, Y. Tomioka, Y. Tokura, G. Cerullo, and A. Cavalleri, *Nat. Mater.* **6**, 643 (2007).
- [16] P. Beaud, S. L. Johnson, E. Vorobeva, U. Staub, R. A. De Souza, C. J. Milne, Q. X. Jia, and G. Ingold, *Phys. Rev. Lett.* **103**, 155702 (2009).
- [17] P. Beaud, A. Caviezel, S. O. Mariager, L. Rettig, G. Ingold, C. Dornes, S.-W. Huang, J. A. Johnson, M. Radovic, T. Huber, T.

- Kubacka, A. Ferrer, H. T. Lemke, M. Chollet, D. Zhu, J. M. Glowia, M. Sikorski, A. Robert, H. Wadati, M. Nakamura, M. Kawasaki, Y. Tokura, S. L. Johnson, and U. Staub, *Nat. Mater.* **13**, 923 (2014).
- [18] R. Singla, A. Simoncig, M. Först, D. Prabhakaran, A. L. Cavalieri, and A. Cavalleri, *Phys. Rev. B* **88**, 075107 (2013).
- [19] V. Esposito, L. Rettig, E. Abreu, E. M. Bothschafter, G. Ingold, M. Kawasaki, M. Kubli, G. Lantz, M. Nakamura, J. Rittman, M. Savoini, Y. Tokura, U. Staub, S. L. Johnson, and P. Beaud, *Phys. Rev. B* **97**, 014312 (2018).
- [20] S. Y. Zhou, Y. Zhu, M. C. Langner, Y.-D. Chuang, P. Yu, W. L. Yang, A. G. Cruz Gonzalez, N. Tahir, M. Rini, Y.-H. Chu, R. Ramesh, D.-H. Lee, Y. Tomioka, Y. Tokura, Z. Hussain, and R. W. Schoenlein, *Phys. Rev. Lett.* **106**, 186404 (2011).
- [21] U. Staub, G. I. Meijer, F. Fauth, R. Allenspach, J. G. Bednorz, J. Karpinski, S. M. Kazakov, L. Paolasini, and F. d'Acapito, *Phys. Rev. Lett.* **88**, 126402 (2002).
- [22] J. Garcia, M. C. Sanchez, J. Blasco, G. Subias, and M. G. Proietti, *J. Phys.: Condens. Matter* **13**, 3243 (2001).
- [23] M. v. Zimmermann, C. S. Nelson, Y.-J. Kim, J. P. Hill, D. Gibbs, H. Nakao, Y. Wakabayashi, Y. Murakami, Y. Tokura, Y. Tomioka, T. Arima, C.-C. Kao, D. Casa, C. Venkataraman, and T. Gog, *Phys. Rev. B* **64**, 064411 (2001).
- [24] M. v. Zimmermann, C. S. Nelson, J. P. Hill, D. Gibbs, M. Blume, D. Casa, B. Keimer, Y. Murakami, C.-C. Kao, C. Venkataraman, T. Gog, Y. Tomioka, and Y. Tokura, *Phys. Rev. B* **64**, 195133 (2001).
- [25] J. Garcia and G. Subias, *Phys. Rev. B* **68**, 127101 (2003).
- [26] M. v. Zimmermann, S. Grenier, C. S. Nelson, J. P. Hill, D. Gibbs, M. Blume, D. Casa, B. Keimer, Y. Murakami, C.-C. Kao, C. Venkataraman, T. Gog, Y. Tomioka, and Y. Tokura, *Phys. Rev. B* **68**, 127102 (2003).
- [27] S. Grenier, J. P. Hill, D. Gibbs, K. J. Thomas, M. v. Zimmermann, C. S. Nelson, V. Kiryukhin, Y. Tokura, Y. Tomioka, D. Casa, T. Gog, and C. Venkataraman, *Phys. Rev. B* **69**, 134419 (2004).
- [28] J. Herrero-Martín, J. Garcia, J. Blasco, and G. Subias, *Eur. Phys. J. Spec. Top.* **208**, 107 (2012).
- [29] D. Okuyama, M. Nakamura, Y. Wakabayashi, H. Itoh, R. Kumai, H. Yamada, Y. Taguchi, T. Arima, M. Kawasaki, and Y. Tokura, *Appl. Phys. Lett.* **95**, 152502 (2009).
- [30] P. R. Willmott, D. Meister, S. J. Leake, M. Lange, A. Bergamaschi, M. Böge, M. Calvi, C. Cancellieri, N. Casati, A. Cervellino, Q. Chen, C. David, U. Flechsig, F. Gozzo, B. Henrich, S. Jäggi-Spielmann, B. Jakob, I. Kalichava, P. Karvonen, J. Krempasky, A. Lüdeke, R. Lüscher, S. Maag, C. Quitmann, M. L. Reinle-Schmitt, T. Schmidt, B. Schmitt, A. Streun, I. Vartiainen, M. Vitins, X. Wang, and R. Wulschleger, *J. Synchrotron Radiat.* **20**, 667 (2013).
- [31] C. Broennimann, E. F. Eikenberry, B. Henrich, R. Horisberger, G. Huelsen, E. Pohl, B. Schmitt, C. Schulze-Briese, M. Suzuki, T. Tomizaki, H. Toyokawa, and A. Wagner, *J. Synchrotron Radiat.* **13**, 120 (2006).
- [32] M. Chollet, R. Alonso-Mori, M. Cammarata, D. Damiani, J. Defever, J. T. Delor, Y. Feng, J. M. Glowia, J. B. Langton, S. Nelson, K. Ramsey, A. Robert, M. Sikorski, S. Song, D. Stefanescu, V. Srinivasan, D. Zhu, H. T. Lemke, and D. M. Fritz, *J. Synchrotron Radiat.* **22**, 503 (2015).
- [33] W. E. White, A. Robert, and M. Dunne, *J. Synchrotron Radiat.* **22**, 472 (2015).
- [34] S. L. Johnson, P. Beaud, C. J. Milne, F. S. Krasniqi, E. S. Zijlstra, M. E. Garcia, M. Kaiser, D. Grolimund, R. Abela, and G. Ingold, *Phys. Rev. Lett.* **100**, 155501 (2008).
- [35] S. Herrmann, S. Boutet, B. Duda, D. Fritz, G. Haller, P. Hart, R. Herbst, C. Kenney, H. Lemke, M. Messerschmidt, J. Pines, A. Robert, M. Sikorski, and G. Williams, *Nucl. Instrum. Methods Phys. Res., Sect. A* **718**, 550 (2013).
- [36] M. Harmand, R. Coffee, M. R. Bionta, M. Chollet, D. French, D. Zhu, D. M. Fritz, H. T. Lemke, N. Medvedev, B. Zijsa, S. Toleikis, and M. Cammarata, *Nat. Photon.* **7**, 215 (2013).
- [37] Y. Murakami, H. Kawada, H. Kawata, M. Tanaka, T. Arima, Y. Moritomo, and Y. Tokura, *Phys. Rev. Lett.* **80**, 1932 (1998).
- [38] A. M. Mulders, S. M. Lawrence, U. Staub, M. Garcia-Fernandez, V. Scagnoli, C. Mazzoli, E. Pomjakushina, K. Conder, and Y. Wang, *Phys. Rev. Lett.* **103**, 077602 (2009).
- [39] E. E. Rodriguez, T. Proffen, A. Llobet, J. J. Rhyne, and J. F. Mitchell, *Phys. Rev. B* **71**, 104430 (2005).
- [40] B. Henke, E. Gullikson, and J. Davis, *At. Data Nucl. Data Tables* **54**, 181 (1993).
- [41] A. Caviezel, U. Staub, S. L. Johnson, S. O. Mariager, E. Möhr-Vorobeva, G. Ingold, C. J. Milne, M. Garganourakis, V. Scagnoli, S. W. Huang, Q. X. Jia, S.-W. Cheong, and P. Beaud, *Phys. Rev. B* **86**, 174105 (2012).
- [42] A. Caviezel, S. O. Mariager, S. L. Johnson, E. Möhr-Vorobeva, S. W. Huang, G. Ingold, U. Staub, C. J. Milne, S.-W. Cheong, and P. Beaud, *Phys. Rev. B* **87**, 205104 (2013).
- [43] D. Lim, V. K. Thorsmølle, R. D. Averitt, Q. X. Jia, K. H. Ahn, M. J. Graf, S. A. Trugman, and A. J. Taylor, *Phys. Rev. B* **71**, 134403 (2005).