

Ultrafast lattice dynamics and electron-phonon coupling in platinum extracted with a global fitting approach for time-resolved polycrystalline diffraction data

Daniela Zahn,^{1,*} H el ene Seiler,¹ Yoav William Windsor,¹ and Ralph Ernstorfer^{1,†}
¹*Fritz-Haber-Institut der Max-Planck-Gesellschaft, Faradayweg 4-6, 14195 Berlin, Germany*

Quantitative knowledge of electron-phonon coupling is important for many applications as well as for the fundamental understanding of nonequilibrium relaxation processes. Time-resolved diffraction provides direct access to this knowledge through its sensitivity to laser-induced lattice dynamics. Here, we present an approach for analyzing time-resolved polycrystalline diffraction data. A two-step routine is used to minimize the number of time-dependent fit parameters. The lattice dynamics are extracted reliably by finding the best fit to the full transient diffraction pattern rather than by analyzing transient changes of individual Debye-Scherrer rings. We apply this approach to platinum, an important component of novel photocatalytic and spintronic applications, for which a large variation of literature values exists for the electron-phonon coupling parameter G_{ep} . Based on the extracted evolution of the atomic mean squared displacement (MSD) and using a two-temperature model (TTM), we obtain $G_{\text{ep}} = (3.9 \pm 0.2) \cdot 10^{17} \frac{\text{W}}{\text{m}^3\text{K}}$. We find that at least up to an absorbed energy density of 124 J/cm^3 , G_{ep} is not fluence-dependent. Our results for the lattice dynamics of platinum provide insights into electron-phonon coupling and phonon thermalization and constitute a basis for quantitative descriptions of platinum-based heterostructures in nonequilibrium conditions.

I. INTRODUCTION

Platinum is important to many technological fields, and in particular it is often used as a catalyst. Many chemical reactions require high temperatures and/or pressures, rendering them energy-intensive. A promising approach to reduce this energy cost is to employ photocatalysis. One emerging approach is to employ bimetallic heterostructures that combine a catalytically active material (e.g. platinum or palladium) with a plasmonic material (e.g. silver, gold or aluminum)¹, for example in so-called antenna-reactor nanostructures^{2,3}. Another approach is to combine a catalytically active metal with a semiconductor (semiconductor-metal heterostructure)⁴. It has been demonstrated that such structures can exhibit high photocatalytic activities²⁻⁴. In many photocatalytic reactions, highly excited ("hot") electrons play the decisive role⁵⁻⁷. The time scales on which the electrons remain hot depends on their coupling to other degrees of freedom, in particular the lattice, which is the main heat sink on ultrafast time scales. Therefore, knowledge about the ultrafast lattice dynamics is important for understanding the dynamics of hot-carrier driven chemical reactions.

In addition to its use in catalysis, platinum is also an important material for spintronics due to its large spin-orbit coupling. This leads for example to a large Spin-Hall effect, which is widely employed for spin-to-charge or charge-to-spin conversion⁸⁻¹³, and to a large Rashba effect^{14,15}. The functionality of spintronic heterostructures is determined by the interplay of interfacial couplings and couplings within the individual materials. The relaxation processes within a material can therefore strongly influence charge and spin currents across interfaces. For example, the spin-Seebeck current across a photoexcited yttrium iron garnet/platinum

interface strongly depends on the electronic temperature in platinum¹⁶, whose evolution is dominated by electron-lattice equilibration. Therefore, knowledge of the lattice response of platinum serves as a basis for understanding and controlling the behavior of spintronic devices.

In particular, it is of interest to quantify the coupling of excited carriers to the lattice. However, literature values for the electron-phonon coupling constant G_{ep} of platinum vary significantly^{7,17-20}, from $2.5 \cdot 10^{17} \frac{\text{W}}{\text{m}^3\text{K}}$ to $(10.9 \pm 0.5) \cdot 10^{17} \frac{\text{W}}{\text{m}^3\text{K}}$ ¹⁹. So far, most values for G_{ep} in platinum were deduced using optical methods, for example time-resolved optical reflectivity (TRR) measurements¹⁸⁻²¹. A challenge of TRR measurements is that the reflectivity change depends on both the electron and the phonon temperatures²²⁻²⁴, and separating these contributions is non-trivial. In addition, the dependence of the reflectivity change on these temperatures is not always linear, especially for higher fluences^{25,26} and for transition metals¹⁸. An alternative way to access G_{ep} is by using a ferromagnetic detection layer in combination with time-resolved MOKE measurements¹⁷. However, this approach relies on modeling the nonequilibrium responses of both platinum as well as of the detection layer, which limits the precision of the method. In contrast, time-resolved photoemission spectroscopy provides direct access to transient electron temperatures. Determination of G_{ep} with this surface-sensitive technique remains challenging, however, due to the interplay of electron relaxation and transport. Therefore, time-resolved diffraction is an important complementary technique to optical and photoemission measurements. It is only sensitive to the lattice and can therefore directly measure the lattice response to photoexcitation, thus providing quantitative insights into electron-lattice equilibration from the lattice perspective. However, quantitatively extracting the lattice dynamics from time-resolved diffraction data is

not trivial. This is because laser excitation causes the intensity of the Bragg reflections to decrease due to the Debye-Waller effect, but it simultaneously enhances thermal diffuse scattering, which contributes to the background. Separating these effects is particularly challenging for polycrystalline samples compared to single crystals, because the diffraction signal is weaker and the two effects overlap in the probed momenta. An additional challenge is the limited transverse coherence in time-resolved electron diffraction experiments, which causes an overlap of diffraction rings.

Typically, only the most prominent rings are analyzed and the intensity changes of each ring are extracted separately. The latter can lead to inconsistencies, since different rings often yield different results for the amplitudes of the atomic mean-squared displacement (MSD) change. In addition, fit parameters can strongly correlate when performing a fit with many free parameters to overlapping diffraction rings, reducing reliability. Therefore, an approach which extracts the lattice dynamics based on the full diffraction pattern and minimizes fit parameters is desired.

Here, we present such an approach for the analysis of polycrystalline diffraction patterns, which consists of two steps. We use the term "global" to describe our approach since the full diffraction pattern is taken into account in the analysis and there is only one fit parameter for the MSD change and one fit parameter for the lattice expansion. The latter reduces the number of time-dependent fit parameters compared to conventional analyses, in which the intensity and position of each diffraction ring are time-dependent fit parameters. We apply this global approach to femtosecond electron diffraction data of platinum. Next, we convert the results for the MSD change into lattice temperature, perform a fit to a two-temperature model^{27,28} (TTM) and extract a value for the electron-phonon coupling parameter. We also discuss the role of non-thermal phonons in the lattice dynamics. Our results provide quantitative information about electron-lattice equilibration as well as phonon thermalization, which are integral to the understanding of nonequilibrium dynamics in platinum.

II. EXPERIMENT

We study the lattice dynamics of platinum using the compact femtosecond electron diffractometer described in Ref.²⁹. The sample is a freestanding, polycrystalline film of platinum with a thickness of 15 nm. It was deposited on a NaCl single crystal using electron beam evaporation. Then, the platinum film was transferred to a standard TEM grid using the floating technique³⁰. To excite the sample, we use infrared laser pulses with a photon energy of 0.70 eV and a pulse length of around 80 fs (FWHM). The lattice response to photoexcitation is probed using ultrashort electron pulses with a kinetic energy of 70 keV. The estimated time resolution of the

experiment is around 170 fs. The electrons are diffracted by the sample and diffraction patterns are recorded in transmission. Figure 1(a) shows a schematic illustration of the electron diffraction experiment, including a diffraction image of our platinum sample.

Since our sample is polycrystalline, we observe Debye-Scherrer rings. Therefore, we azimuthally average the diffraction images for further analysis. In addition, the data are normalized by dividing each background-subtracted and flatfield-corrected diffraction image by its average intensity (excluding the zero order beam and regions outside the field of view). We choose this normalization method as opposed to normalization to the lowest order diffraction peak to avoid systematic errors due to multiple scattering.

The resulting radial profile (RP) is displayed in Fig. 1(b). Each radial profile corresponds to the average of 20 scans of the pump-probe delay, except for the lowest excitation density, for which 24 scans were recorded. For every point of a pump-probe scan, 13 diffraction images with an integration time of 5 s each were recorded and averaged, corresponding to $13 \times 5 \times 4000 = 260000$ electron pulses in total.

Our main observable is the intensity of the diffraction rings, which weaken as the atomic MSD increases when additional phonons are created (Debye-Waller effect). The relationship between the intensity decrease and the MSD is given by³¹:

$$\frac{I(t)}{I_0} = \exp\left\{-\frac{1}{3} q^2 \Delta\langle u^2 \rangle(t)\right\} \quad (1)$$

Here, $\Delta\langle u^2 \rangle(t)$ is the MSD change, I_0 is the intensity before laser excitation and q is the scattering vector of the diffraction ring, $q = 4\pi \sin(\theta)/\lambda$. This description can only be applied to intensity changes due to incoherent phonons, for instance generated by electron-phonon scattering. It can be used to describe the effects of both non-thermal and thermal phonon distributions³²⁻³⁴.

III. GLOBAL DIFFRACTION DATA ANALYSIS

To analyze the time-resolved polycrystalline diffraction data, we utilize a fit routine in which the MSD is extracted using the whole RP, instead of specific Debye-Scherrer rings. A major advantage of this approach is that the total number of fit parameters can be reduced significantly, especially for the description of the laser-induced changes in the diffraction pattern. This is possible since some information is encoded in all diffraction rings, namely lattice expansion and MSD increase. Therefore, a global fit can increase the reliability of the results, by avoiding artifacts for example due to strong correlations between fit parameters describing overlapping diffraction rings. Disentangling the dynamics of overlapping rings is particularly important in time-resolved electron diffraction due to the finite coherence of the pulsed electron sources.

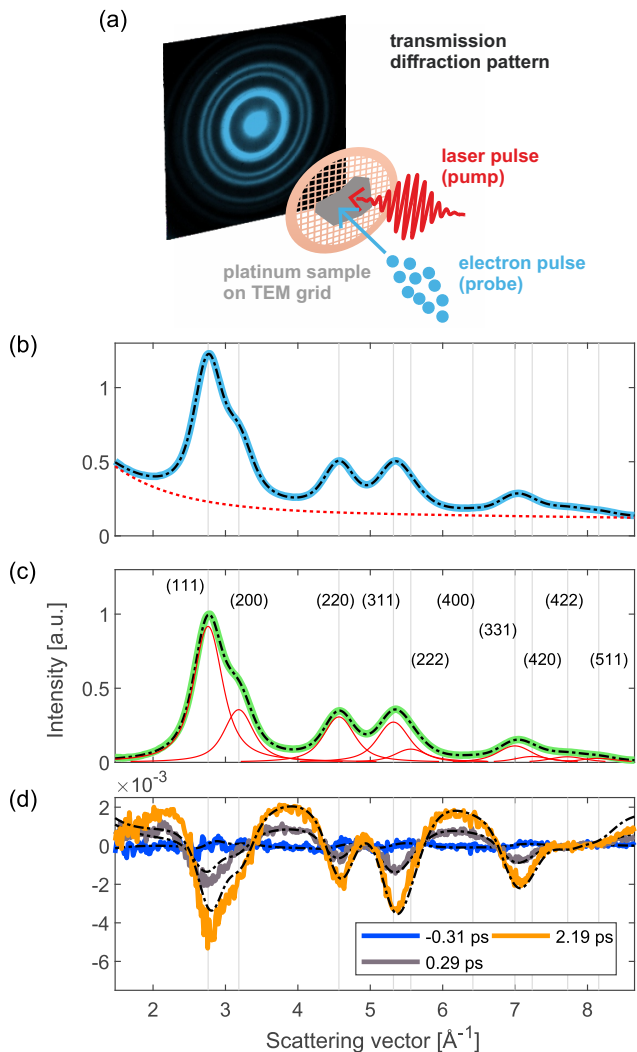


FIG. 1. Experimental setup and diffraction pattern of platinum. (a) Schematic illustration of the electron diffraction experiment. The freestanding thin-film sample is excited with an ultrashort laser pulse and the lattice response is probed with an ultrashort electron pulse. Diffraction patterns for several pump-probe delays are recorded in transmission. (b) Azimuthally averaged diffraction pattern (radial profile, RP) of our platinum sample. The solid blue curve corresponds to the experimental data and the dashed black curve represents the static global fit (see text for details about the fit). The dashed red curve shows the static fit result for the background contribution. (c) RP after subtracting the fit result for the background. The solid green curve shows the experimental data and the dashed black curve shows the static fit result without the background contribution. The contributions of the individual Bragg reflections are displayed in red. (d) Differences between the RPs for selected delays after photoexcitation and the RP prior to photoexcitation. The experimental data are shown as solid curves and the fit results of the dynamic fit are shown as dashed black curves. Note that in Panels (b)-(d), the x-axis was converted from image pixels to scattering vectors using the results of the static fit (for illustration purposes).

In particular, there is a trade-off between coherence, time resolution and signal-to-noise ratio, because a smaller source size increases space-charge effects. In the following, we provide more details about our global fit routine, which consists of two steps: In the first step (static fit), we perform a fit of the RP's before laser excitation. In the second step (dynamic fit), a fit is performed to describe the changes of the RP's following laser excitation. Here, we only include changes due to an increase of the phonon population, hence we do not include any photo-induced rearrangement of atoms within the unit cell, e.g. structural phase transitions. The second step of our fitting routine yields the MSD change, the lattice expansion (i.e., the changes in diffraction ring radii) and the background change as a function of pump-probe delay.

A. Static fit

In the first step of the fitting routine, the goal is to accurately describe the RP's before laser excitation. For this step, first we average all RP's recorded before the arrival of the pump pulse in order to obtain maximum signal-to-noise ratio. For the fit, we use a wide range of reciprocal space that includes the first ten diffraction rings of platinum, from the (111) to the (511) reflection, as shown in Fig. 1(c). Despite the low intensity of the diffraction rings at scattering vectors above 6 \AA^{-1} , including these rings in the analyzed range is beneficial as they feature intensity reductions similar to those of lower order peaks due to a large Debye-Waller effect, as shown in Fig. 1(d).

Our fit function consists of the sum of a background function and peak functions for the azimuthally averaged diffraction rings. The possibility of fitting all diffraction rings and a global background together in the same step is an additional advantage of the global fit, because it yields a reliable background determination. This becomes important in the second step of the fitting routine (dynamic fit), because the background subtraction strongly influences the results for the amplitude of the MSD increase.

The positions of the diffraction peaks in reciprocal space are known. Thus, in order to reduce free parameters in the fit, we don't consider the diffraction ring radii as independent variables. However, in practice, our magnetic lens used to focus the electron beam on the detector can introduce image distortions, which cause a non-linear relationship between scattering vector and pixel number in the RP's (radial distortion). To account for these distortions, we introduce a correction parameter γ as a fit parameter. The radius of the first ring, r_1 , is also a fit parameter and accounts for the conversion of scattering vectors to image pixels. The other ring radii are then given by:

$$r_i = \left(\frac{q_i}{q_1} \right)^\gamma \cdot r_1 \quad (2)$$

Here, q_i are the scattering vectors of the diffraction rings. In our case, the magnetic lens introduces a barrel distortion, and therefore the fit result for γ is a value slightly smaller than one (here: around 0.96). We expect that our distortion correction can also correct pincushion distortions ($\gamma > 1$). Note that only radial distortions can be corrected with γ .

With Eq. 2, the approximate ring radii can be well described. In addition, to refine the ring radii, we introduced individual radius correction factors f_i as fit parameters. These were constrained such that the radii couldn't deviate more than 2% from the values given by Eq. 2. We found that for our experimental data, introducing the individual correction factors f_i in addition to the global distortion correction γ is essential to obtain good agreement to the diffraction pattern before laser excitation, which then also determines the quality of the dynamic fit. However, most of the distortion is corrected by γ , which minimizes erroneous peak positions in the static fit result caused by strong correlations of amplitude and position parameters of overlapping diffraction rings. Note that γ and f_i are parameters related to the measurement system. In the absence of distortions, or if distortions were corrected previously, the correction factors γ and f_i are not necessary and can be set to 1.

The azimuthally averaged diffraction rings are described as Lorentzians with their amplitudes being unconstrained fit parameters. This makes the fitting procedure suitable also for polycrystalline samples with a preferred orientation, which exhibit different relative diffraction ring intensities compared to powder diffraction patterns. The width of the Lorentzians is one fit parameter (w_{reci}), such that the widths of all peaks in reciprocal space are the same. Due to the lens distortions, the widths in pixels, $w_i(w_{\text{reci}}, r)$, are slightly different for the different rings. We don't consider broadening due to finite crystallite sizes according to the Scherrer equation, because the width of the rings is dominated by the finite coherence of the pulsed electron beam. In total, the function describing the diffraction rings is given by:

$$F(r) = \sum_{i=1}^N \frac{A_i}{\left(1 + \left(\frac{(r-r_i) \cdot f_i}{w_i}\right)^2\right)} \quad (3)$$

Here A_i are the amplitudes of the rings (fit parameters) and N is the number of diffraction rings considered. For the background function, we use a phenomenological function, which we choose depending on the experimental conditions. Going beyond a phenomenological description of the diffuse background intensity would require knowledge about the phonon properties of the material. For the measurements presented here, we obtained the best agreement to the experimental data using an exponential function plus a linear relationship:

$$B(r) = a \cdot \exp\{-r/b\} + c + d \cdot r \quad (4)$$

We tested different background functions and found the results for the MSD dynamics to be robust with respect to the choice of background function (less than 8% deviation in MSD amplitude compared to the results presented here).

Finally, the sum $F + B$ is convolved with a Gaussian to account for the finite coherence of the experiment. The convolution width is a fit parameter. In addition, at this point we add another correction related to the measurement system. Since there are also lens distortions which are not radially symmetric and/or due to spherical aberrations, the outer rings are typically slightly broader in the RP. To account for this, we introduce an additional fit parameter δ which distorts the radius axis linearly before the convolution:

$$r' = r \cdot \left(1 - \delta \cdot \frac{r - r_{\text{start}}}{r_{\text{end}} - r_{\text{start}}}\right) \quad (5)$$

r_{start} and r_{end} are the radii of the beginning and the end of the fit range, respectively. Note that the correction factor δ depends on the measurement system, in particular on the amount of not radially symmetric distortions and spherical aberration. If these effects are negligible, this correction factor is not necessary and can be set to zero.

Finally, it should be noted that the width of the Lorentzians and the Gaussian broadening are strongly correlated. The correlation between them is ≈ -0.48 when δ (which influences the average convolution width) is constrained to be zero. Due to this significant correlation, the fit result depends on the starting values. To find the best combination of starting values, the static fit was repeated for all combinations of widths in a reasonable range and with both width parameters fixed. The procedure is similar to a grid search, with the difference being that only the two correlated width parameters form the grid and the other parameters are optimized by the fit. The results are presented in Fig. 2. By this systematic variation of widths, the combination yielding the lowest residual was identified. The static fit was then performed again with this combination of starting parameters. We tested several other starting parameters in the blue region of Fig. 2 and found the same dynamic fit results within error bars, demonstrating the robustness of our approach.

With our fitting procedure, we obtain excellent agreement to the experimentally measured diffraction pattern, as shown in Figure 1(b) and (c). The excellent agreement of the static fit to the experimental data is a very important prerequisite for the second step of the fitting routine, the dynamic fit.

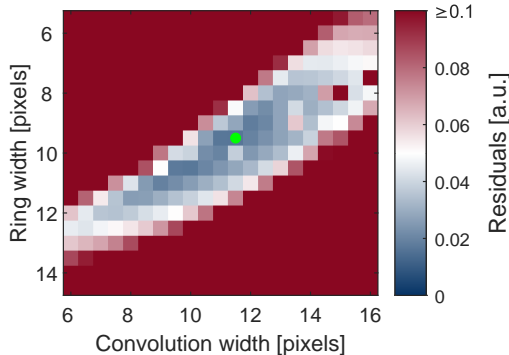


FIG. 2. Visualization of the width optimization procedure. A map of the fit residuals (sum of squared residuals) as a function of diffraction ring width and convolution width is shown. Both of these parameters were kept fixed in the static fits for width optimization. The combination of widths that yields the lowest residual is marked with a green dot.

B. Dynamic fit

In the second step, we analyze changes in the diffraction pattern following laser excitation. In this step, we make use of the results of the static fit, and only allow the following changes to the diffraction pattern compared to the static fit:

- decreases of the diffraction ring intensities corresponding to an MSD increase, according to Debye-Waller theory (see Eq. 1).
- changes of the background parameters. Following laser excitation, the background increases due to an increase in diffuse scattering. This effect is also caused by the phonon population increase, see for example Ref.³³.
- expansion (or contraction) of the sample, leading to a reduction (increase) of the scattering vectors of all rings:

$$q_i(t) = q_{i,0} \cdot \frac{1}{1 + \epsilon(t)} \quad (6)$$

Here, $q_{i,0}$ is the scattering vector before laser excitation. Typically, expansion effects are relatively small compared to MSD changes and whether or not expansion is included has no significant effect on the MSD dynamics.

Note that this description of the photo-induced changes of the diffraction ring intensities is valid for mono-atomic materials with isotropic MSD, for example mono-atomic face-centered cubic (fcc) or body-centered cubic (bcc) metals. Further information on whether MSDs are isotropic can be found in Ref.³⁵. Furthermore, the description can also be applied to many mono-atomic

hexagonal close-packed (hcp) metals, depending on their lattice constant ratio³⁶. The description can be extended to more complex materials, based on the crystal structure and the atomic form factors of the constituent ions.

Especially for low fluences, the noise level of the fit results can be significantly improved by constraining the background parameters, since often the parameters are correlated and local minima are possible. Here we restricted the change in background parameters to no more than 5% from one delay point to the next. Care was taken to ensure that the fit constraints do not alter the results for the lattice dynamics. An overview of all parameters of the fit function in the static and dynamic fit is presented in Table I.

Figure 1(d) presents the differences of the RP's compared to the static RP for several pump-probe delays, as well as the fit results. We obtain good agreement to the experimentally observed changes. The deviations of the ring intensity changes are due to multiple scattering effects beyond the kinematic limit, which are not captured by Eq. 1. Without multiple scattering, we would expect the intensity decreases of Bragg reflections with very low and very high scattering vectors to be better described by the dynamic fit result. Multiple scattering effects are often present in electron diffraction due to the strong interaction of electrons with matter. In platinum, such effects are relatively strong due to its high atomic number and density. For transient MSD changes extracted from changes of individual diffraction rings, this effect leads to ambiguities because different rings yield different results. In contrast, the global fit yields only one value for the MSD increase from all rings combined. Multiple scattering redistributes intensity between different Bragg reflections and is thus expected to increase the pump-probe differences in the low- q range while at the same time decreasing the pump-probe differences in the high- q range. Therefore, we expect the global fit to yield relatively accurate results for the MSD even in the presence of multiple scattering. Note that in addition, multiple scattering also leads to intensity redistribution between Bragg reflections and the zero order beam, which cannot be accounted for in either of the two fitting methods. On the experimental side, multiple scattering could be reduced by higher electron energies or thinner samples. In general, less multiple scattering effects are expected for materials with lower atomic number and/or lower density.

In addition to the deviations between experiment and fit result caused by multiple scattering, there are deviations at both ends of the reciprocal space range considered for the analysis, which we attribute to the limitations of the phenomenological background function (see Eq. 4). However, for most of the range considered, both the background and the diffraction rings are well described by the result of the global fit.

In summary, compared to conventional analysis methods of polycrystalline diffraction patterns, the global fitting approach has two main advantages.

Parameter	Meaning	Static fit	Dynamic fit
A_i	diffraction ring amplitudes	free parameters	changes only according to Eq. 1
r_1	radius of the ring with the lowest scattering vector	free parameter	changes only according to Eq. 6
r_i (except $i = 1$)	radii of the other rings	determined by their scattering vectors q_i , r_1 , and γ	changes only according to Eq. 6
f_i	radius correction factors	free parameters, but constrained to a few % around 1	fixed
w_{reci}	width of all peaks in reciprocal space (one parameter)	free parameter	fixed
w_i	width of the individual peaks in the radial profile	determined by w_{reci} , r_i , and γ	fixed
γ	correction parameter for radial distortions	free parameter	fixed
convolution width	FWHM of the Gaussian that the calculated pattern is convolved with	free parameter	fixed
δ	correction parameter for broadening of higher-order peaks	free parameter	fixed
$\Delta\langle u^2 \rangle$	MSD change	–	free parameter, determines changes of all A_i simultaneously via Eq. 1
ϵ	expansion or contraction	–	free parameter, determines changes of the lattice constant, i.e. of all q_i simultaneously, via Eq. 6
background parameters	depends on the background function	free parameters	free parameters (with dynamic constraints).

TABLE I. Overview of parameters in the static and dynamic fit.

First, the background and the diffraction rings are fitted together, which allows a reliable background determination. Second, the result for the MSD dynamics is based on the full diffraction pattern instead of individual diffraction rings only. In Fig. 3, the global fitting approach is compared to two different analysis methods. Fig. 3(a) highlights the first advantage of the global fitting routine by comparing it to the result of a background subtraction and a *subsequent* fit of the diffraction rings. For the latter, in the first step, the background is subtracted by fitting the background function (see Eq. 4) to certain regions in between the diffraction rings, shown as light blue areas. The resulting background-subtracted experimental data is shown as a solid yellow line. In the second step, a fit of the diffraction rings is performed. Here, we use the same fit function as in the global fitting routine, but without any background. The fit result is shown as a dashed black line. The residuals are significantly higher compared to a *simultaneous* fit of background and rings, as shown in Fig. 3(b). The finite coherence leads to contributions from the diffraction rings also in the "background" regions, and therefore to an overestimation of the background. An additional disadvantage of this method is that the fit result for the background depends on the choice of "background" regions.

The second advantage of the global fitting routine is visualized in Fig. 3(c)-(e), which show the result if no global MSD change is assumed, but the MSD change is a separate fit parameter for each ring. For this "local

fit" of the MSDs we use the same fit function as for the global fit to enable a direct comparison between the two methods. Due to the significant overlap of the individual rings, expansion is not considered here and the MSD of each ring is constrained to be non-negative. The fit was performed analogously to the global fit, hence a fit to the full diffraction pattern was performed (all rings simultaneously, each ring intensity being a separate fit parameter). As shown in Fig. 3(c), different diffraction rings yield different results for the MSD change, in particular also significantly different amplitudes of the MSD rise. Regarding the timescale of the MSD rise, no differences are observed within the experimental accuracy. The MSD amplitude differences are illustrated in Fig. 3(d), which compares between the result from the global fit and the result from the local fit of individual rings. In conventional analyses, often only a subset of the diffraction rings is analyzed^{37,38}. Figure 3(d) demonstrates that if only one or few rings are considered, the uncertainty in MSD amplitude is high and the result depends on which rings are used. In contrast, the global fit uses the full diffraction pattern to extract MSD dynamics (i.e. *all* rings in the observed range of reciprocal space), so we expect its results to be more reliable. In addition, it removes ambiguities which can arise due to the subjective choice of a subset of diffraction rings for the analysis. Note the systematic dependence on the scattering vector in Figure 3(d) suggests that the differences in MSD amplitude are partially caused by multiple scattering, and we expect smaller discrepancies

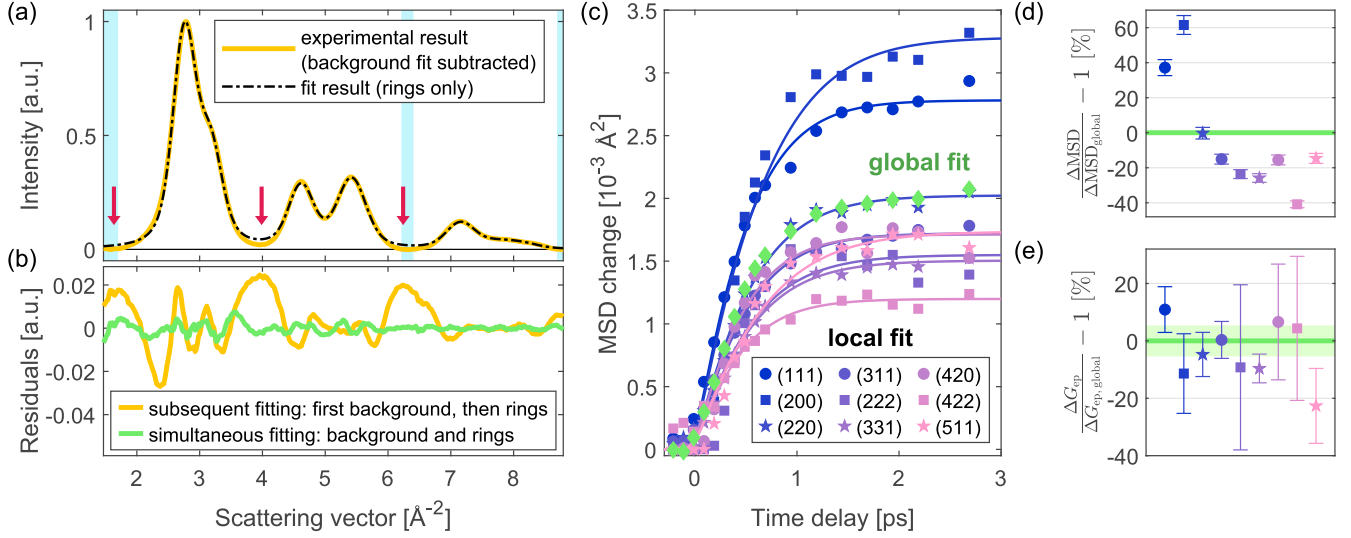


FIG. 3. Comparison of the global fitting routine with two other analysis methods. (a) Result of a background subtraction before fitting the diffraction rings. The experimental data (yellow) corresponds to the average of all RP’s before the arrival of the laser pulse, as used also in the first step of the global fit. The background is subtracted by fitting the background function (see Eq. 4) in regions with low intensity from the diffraction rings (shown as light blue areas). This analysis method leads to an overestimation of the background due to residual intensity from the diffraction rings also in the “background” regions. Particularly problematic regions are indicated with red arrows. (b) Comparison of the residuals of this subsequent fitting of background and diffraction rings (yellow line) to the global fitting procedure, in which both are fitted simultaneously (green line). The simultaneous fitting of background and rings yields much lower residuals: the root-mean-square deviation (RMSD) of the global fit is only 0.0021, compared to 0.0109 for the subsequent fitting of background and rings. The RMSD units are the same as shown in (a), where the first ring is normalized to 1. (c) Result of a local fit of the MSD: The intensity (and thus the MSD change) of each diffraction ring is now a separate fit parameter in the dynamic fit. Results from several diffraction rings are presented, demonstrating that different rings yield different MSD dynamics, particularly in amplitude. The result of the global fit is overplotted. Solid lines are two-temperature model (TTM) fit results. In all the TTM analyses shown here, the pump laser’s arrival time is the same as in the TTM analyses of Section IV. The absorbed energy density of this measurement was 124 J/cm^3 . (d) MSD amplitudes of the individual peaks relative to the global MSD amplitude, calculated from the TTM results at 3 ps. The displayed error bars were calculated based on the standard errors from the TTM fits and assuming that the MSD change is proportional to the fluence. The global MSD amplitude (0% deviation) is shown as a green line. Its error lies within the line width. (e) Results for the electron-phonon coupling G_{ep} from the TTM fits shown in Panel (c) relative to G_{ep} from the global fit. The error bars correspond to the standard errors of the TTM fits. The result of the global analysis is shown as a green line, with the corresponding standard error as shaded area.

in the absence thereof. In addition to the advantage of avoiding a subjective choice of peaks, we expect the minimized number of time-dependent fit parameters and the wide range of reciprocal space considered in the global analysis to be beneficial for the quality of the fit result.

Fig. 3(e) presents G_{ep} values extracted from the local fit results using a TTM. It demonstrates that the ambiguity due to the local fit also translates into an ambiguity in G_{ep} (see Section IV for details on the TTM analysis). Here, the deviations from the global fit result are different compared to Fig. 3(d) because the result for G_{ep} depends on both the amplitude and the timescale of the MSD rise. In contrast to the local fit, the global fit yields one result for the MSD change and thus also one result for G_{ep} , based on the full diffraction pattern.

IV. RESULTS AND DISCUSSION

The MSD evolution of platinum as a function of pump-probe delay extracted with the global fitting routine is presented in Fig. 4. We observe a two-step behavior: A fast component with a time constant of around 600 fs and slower, few-picosecond component with a much smaller amplitude. We attribute the fast component to electron-phonon equilibration and the slow component to phonon redistribution processes. Since the second component is a further MSD increase, these phonon redistribution processes correspond to energy transfer from higher to lower phonon frequencies, since lower-frequency modes exhibit higher displacements per phonon³¹. In addition, higher-frequency phonons decay into several low-frequency phonons due to their higher energy. Hence, we attribute the slow component of

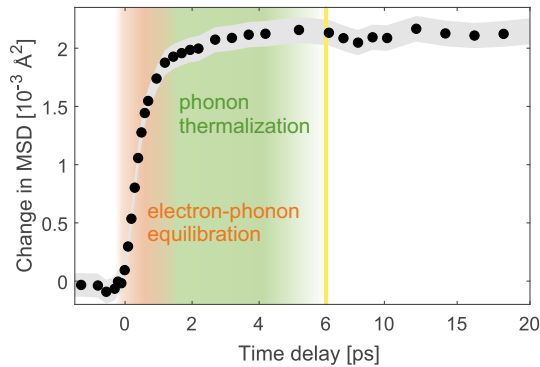


FIG. 4. Change of atomic mean squared displacement (MSD) as a function of pump-probe delay. The grey shaded area represents the error estimates of the data points, which correspond to the standard deviation obtained from the fitting routine. The yellow line indicates a change of scaling of the time axis. The absorbed energy density of this measurement was 124 J/cm^3 .

the lattice dynamics to a population increase of low-frequency phonon modes that couple relatively weakly to the electrons and to other phonon modes. Nevertheless, in platinum, the amplitude of the second MSD rise is small compared to the initial MSD rise, which indicates that after the initial rise, most phonon modes have already thermalized with the electrons, except for a small subset of phonons.

In the following, in order to study electron-phonon coupling quantitatively, we focus on the initial, fast rise of the MSD, i.e. the time scale from -1 to 3 ps. We convert the MSD rise to lattice temperature using the temperature-dependent Debye-Waller factor provided by Ref.³¹. Based on the results for the lattice temperature, we employ a TTM to model the lattice heating and extract the electron-phonon coupling parameter G_{ep} . A schematic illustration of the TTM is displayed in Figure 5(a).

In the TTM, the material is described as consisting of two heat baths, electrons and phonons, which are always in internal thermal equilibrium. The evolution of the system is described by two coupled differential equations and is governed by the magnitude of G_{ep} as well as by the electronic and lattice heat capacities.

Here, we use the electronic heat capacity calculated by Lin et al.³⁹. Since platinum is a transition metal, the relationship between electronic heat capacity and temperature is not linear, especially for high electronic temperatures. For electronic temperatures smaller than ca. 700 K, the heat capacity calculated by Lin et al. roughly corresponds to $c_e = \gamma \cdot T$ with $\gamma \approx 400 \text{ J}/(\text{m}^3\text{K}^2)$. This value is in agreement with experimental results for the heat capacity of platinum at room temperature, as

discussed in Ref.¹⁷. Here, we don't assume a linear relationship for c_e and directly use the results provided by Lin et al.. For the lattice heat capacity, we use the high-temperature limit derived from equipartition, $24.943 \frac{\text{J}}{\text{molK}}$ (corresponding to $2.744 \cdot 10^6 \frac{\text{J}}{\text{m}^3\text{K}}$)^{40,41}. This is a valid approximation since the Debye temperature of platinum, 240 K⁴⁰, is well below room temperature.

In the TTM, the laser pulse is assumed to be of Gaussian shape with a FWHM of 80 fs. The absorbed energy density and the electron-phonon coupling parameter G_{ep} are obtained by finding the best fit of the experimentally measured lattice temperature to the lattice temperature predicted by the TTM. For this fit, the lattice temperature predicted by the TTM is convolved with a Gaussian with a FWHM of 150 fs to account for the estimated duration of the electron pulses. Different electron pulse durations (100 fs and 250 fs) were also tested and found to have no significant influence on the result for G_{ep} (less than 5% deviation). The arrival time of the laser pulse is the same for all fluences, because all measurements presented here were part of the same data acquisition. To obtain the most accurate value for the arrival time, we first performed TTM fits of the individual measurements with the arrival time as a fit parameter. Then, we calculated the weighted average of the resulting arrival times and repeated the TTM fits with the arrival time fixed at this value.

The evolution of the lattice and electronic temperatures resulting from the TTM fit are displayed in Figure 5(b)-(f) for different fluences, together with the experimental results. The TTM fit results yield an excellent description of the experimental data.

The TTM fit result values for G_{ep} are shown in Fig. 5(g). We don't observe any fluence dependence of G_{ep} . In principle, based on theoretical calculations, G_{ep} is expected to depend on the electronic temperature³⁹. However, for our range of fluences, a constant G_{ep} is a good approximation, since the maximum electronic temperature in our experiments is only around 800 K and G_{ep} varies only little in that temperature range.

We therefore calculate the weighted average of the G_{ep} results for different fluences. The result is $(3.9 \pm 0.2) \cdot 10^{17} \frac{\text{W}}{\text{m}^3\text{K}}$. Figure 5(g) shows this value as a horizontal dashed line. The error, which corresponds to the standard error of the weighted mean, represents the statistical error only. Additional systematic contributions could arise, e.g. due to uncertainties in the electronic heat capacity and in the electron pulse duration. Table II compares our result for G_{ep} to existing literature values. Our result is within the range of previously measured values. However, note that most literature values for G_{ep} were extracted with the electron heat capacity coefficient from low-temperature measurements ($\gamma \approx 750 \frac{\text{W}}{\text{m}^3\text{K}^2}$). In contrast, the electron heat capacity we use considers changes of the chemical potential with temperature, which we expect to be more precise at room temperature since the electronic density of states of platinum varies strongly around the Fermi

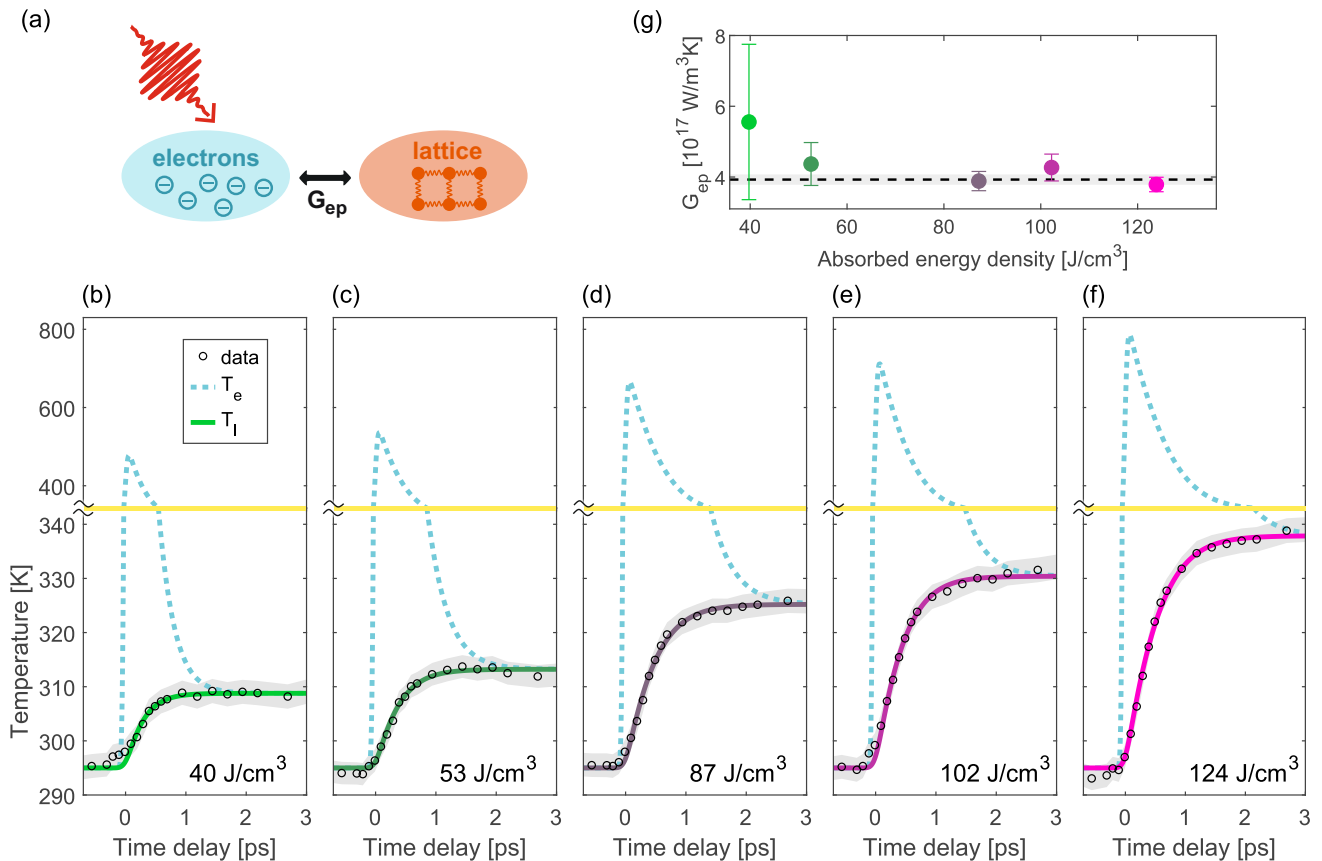


FIG. 5. Quantitative determination of the electron-phonon coupling constant in platinum using a two-temperature model (TTM). (a) Schematic illustration of the TTM. (b)-(f) Experimental data together with temperature evolution according to the TTM fit result for different absorbed energy densities. The dashed blue lines correspond to the evolution of the electronic temperatures (T_e) and the green to pink lines display the evolution of the lattice temperatures (T_l). The TTM result for the lattice temperature was convolved with a Gaussian (FWHM 150 fs) to account for the electron pulse duration (the pump pulse duration is included in the model itself). The yellow line indicates a change of scale in the temperature axis. The experimental results for the lattice temperatures are displayed as black circles and were calculated from the MSD dynamics using the Debye-Waller factor from Ref.³¹. The errors of the experimental data points are displayed as grey shaded areas and correspond to the standard error obtained from the fit of the RP's. (g) TTM fit result for the G_{ep} values for the absorbed energy densities of Panels (b-f). The error bars for the G_{ep} values correspond to the standard error, which was calculated based on the confidence intervals obtained from the TTM fit. The dashed black line corresponds to the weighted average of the G_{ep} values for different absorbed energy densities, and the grey shaded area represents the error of the weighted average.

level³⁹. Since the time evolution of the temperatures in the TTM depends not only on the electron-phonon coupling, but also on the heat capacities, values for G_{ep} extracted with different γ -values are not directly comparable.

The large spread of literature values for G_{ep} (in particular also for similar γ -values) demonstrates that it is non-trivial to extract G_{ep} from time-resolved experimental data. Compared to measurements on heterostructures, our experiments have the advantage that the sample is much less complex and no transport effects between different layers occur. In addition, our sample is freestanding, hence there is no carrier and heat transport to a substrate either. Finally, our films are very thin and we probe in transmission,

hence transport effects within the platinum layer can also be neglected. Therefore, the lattice response we measure reflects only the intrinsic, microscopic relaxation processes in platinum, which reduces the complexity of extracting G_{ep} from the data.

The extraction of G_{ep} with the TTM is based on the assumption that the two heat baths, electrons and phonons, are always in internal thermal equilibrium. For the electrons, particularly in metals, this is usually a good approximation, since electron-electron scattering is typically more efficient than electron-phonon coupling. For the phonons, a thermal distribution is not always a good approximation on short time scales after excitation^{32-34,42-46}. Indeed, also for platinum, we observed signatures of phonon redistribution processes,

Authors	G_{ep} [10^{17} W/(m^3K)]	Method	γ [J/(m^3K^2)]
Hohlfeld ¹⁸	2.5	TRR	740
Kimling et al. ²¹	2.9 ± 0.4	TRR (het.)	721
this work	3.9 ± 0.2	tr-diffraction	c_e from Lin et al. ³⁹ ($\gamma \approx 400$)
Choi et al. ²⁰	4.2	TRR (het.)	721
Jang et al. ¹⁷	6 ± 1	tr-MOKE (het.)	400
Lei et al. ⁷	6.76	tr-photoemission	748
Caffrey et al. ¹⁹	10.9 ± 0.5	TRR	750

TABLE II. Comparison of literature values for the electron-phonon coupling parameter G_{ep} of platinum. The third column lists the experimental method that was applied to obtain G_{ep} . Here, TRR stands for time-resolved reflectivity measurements, "tr" stands for time-resolved, MOKE corresponds to the magneto-optical Kerr effect and "(het.)" indicates that the data was recorded on a heterostructure. The last column lists the value for the electron heat capacity coefficient γ that was used to extract G_{ep} .

indicated by the presence of a second, slow MSD rise, as discussed above. However, compared to the initial fast rise of the MSD, the amplitude of the second rise associated with phonon redistribution processes is rather small. For crystals with a trivial basis such as platinum, the MSD caused by a phonon is inversely proportional to its frequency³¹. Due to this strong dependence of the MSD on the phonon frequency, the amount of frequency redistribution corresponding to the second rise is small. Therefore, after the initial electron-phonon equilibration, the phonon frequencies already resemble a Bose-Einstein distribution. In addition, there could however be temperature differences between different phonon modes of the same frequency, which would not necessarily leave signatures in the MSD dynamics. However, if after the initial electron-phonon equilibration there was still a large amount of (weakly coupled) phonon modes with lower temperatures, this would be noticeable as a two-step behavior in the electron dynamics on timescales larger than around 1.5 ps. Such a two-step behavior is not observed for thin films of platinum^{16,19}. For these reasons, we conclude that for the purpose of describing energy flow from the electrons to the lattice, a TTM is a reasonable approximation.

V. SUMMARY AND CONCLUSIONS

In this work, we provide a direct measurement of the lattice dynamics of laser-excited platinum using femtosecond electron diffraction. We employ a global fitting routine to extract the changes of atomic mean squared displacement (MSD) reliably from the polycrystalline diffraction patterns, which we describe in detail. The approach can be applied to all mono-atomic materials with isotropic MSD, and could also be further extended to describe more complex materials or heterostructures. We extract the MSD evolution of platinum following laser excitation, which exhibits two time scales: a sub-picosecond MSD rise, which we attribute to electron-phonon equilibration, and a further,

much smaller MSD rise on a few-picosecond time scale, which we attribute to phonon-phonon redistribution processes. Based on the dominant, fast MSD rise and using a two-temperature model (TTM), we extract a value of $(3.9 \pm 0.2) \cdot 10^{17} \frac{\text{W}}{\text{m}^3\text{K}}$ for the electron-phonon coupling parameter G_{ep} . Within the range of fluences applied in our experiment, we don't observe any fluence dependence of G_{ep} . Compared to previous reports of G_{ep} , our approach has the advantage that our sample is a freestanding thin film, hence transport effects don't play a role in the dynamics. Furthermore, in contrast to optical spectroscopy, our technique is sensitive only to one subsystem, the lattice. We expect that a precise knowledge of the electron-phonon coupling in platinum will benefit the modeling and understanding of heterostructures containing this material, for example spintronic devices and photocatalytic structures.

DATA AVAILABILITY STATEMENT

The data that support the findings of this study are available from the corresponding author upon reasonable request.

ACKNOWLEDGEMENT

We thank Thomas Vasileiadis and Reza Rouzgar for helpful discussions and Sven Kubala for sample growth. This work was funded by the Deutsche Forschungsgemeinschaft (DFG) through SFB/TRR 227 "Ultrafast Spin Dynamics" (Project B07) and through the Emmy Noether program under Grant No. RE 3977/1, by the European Research Council (ERC) under the European Union's Horizon 2020 research and innovation program (Grant Agreement Number ERC-2015-CoG-682843), and by the Max Planck Society. H.S. acknowledges support by the Swiss National Science Foundation under Grant No. P2SKP2_184100.

- * zahn@fhi-berlin.mpg.de
† ernstorfer@fhi-berlin.mpg.de
- ¹ K. Sytwu, M. Vadai, and J. A. Dionne, *Adv. Phys. X* **4**, 1619480 (2019).
 - ² H. Robotjazi, J. L. Bao, M. Zhang, L. Zhou, P. Christopher, E. A. Carter, P. Nordlander, and N. J. Halas, *Nat. Catal.* **3**, 564 (2020).
 - ³ C. Zhang, H. Zhao, L. Zhou, A. E. Schlather, L. Dong, M. J. McClain, D. F. Swearer, P. Nordlander, and N. J. Halas, *Nano Lett.* **16**, 6677 (2016).
 - ⁴ L. Bai, X. Wang, S. Tang, Y. Kang, J. Wang, Y. Yu, Z.-K. Zhou, C. Ma, X. Zhang, J. Jiang, P. K. Chu, and X.-F. Yu, *Adv. Mater.* **30**, 1803641 (2018).
 - ⁵ Y. Zhang, S. He, W. Guo, Y. Hu, J. Huang, J. R. Mulcahy, and W. D. Wei, *Chem. Rev.* **118**, 2927 (2018).
 - ⁶ L. Zhou, D. F. Swearer, C. Zhang, H. Robotjazi, H. Zhao, L. Henderson, L. Dong, P. Christopher, E. A. Carter, P. Nordlander, and N. J. Halas, *Science* **362**, 69 (2018).
 - ⁷ C. Lei, M. Bauer, K. Read, R. Tobey, Y. Liu, T. Popmintchev, M. M. Murnane, and H. C. Kapteyn, *Phys. Rev. B* **66**, 245420 (2002).
 - ⁸ K. Uchida, S. Takahashi, K. Harii, J. Ieda, W. Koshibae, K. Ando, S. Maekawa, and E. Saitoh, *Nature* **455**, 778 (2008).
 - ⁹ A. Kehlberger, U. Ritzmann, D. Hinzke, E.-J. Guo, J. Cramer, G. Jakob, M. C. Onbasli, D. H. Kim, C. A. Ross, M. B. Jungfleisch, B. Hillebrands, U. Nowak, and M. Kläui, *Phys. Rev. Lett.* **115**, 096602 (2015).
 - ¹⁰ V. E. Demidov, S. Urazhdin, H. Ulrichs, V. Tiberkevich, A. Slavin, D. Baither, G. Schmitz, and S. O. Demokritov, *Nat. Mater.* **11**, 1028 (2012).
 - ¹¹ T. Seifert, S. Jaiswal, U. Martens, J. Hannegan, L. Braun, P. Maldonado, F. Freimuth, A. Kronenberg, J. Henrizi, I. Radu, E. Beaupaire, Y. Mokrousov, P. M. Oppeneer, M. Jourdan, G. Jakob, D. Turchinovich, L. M. Hayden, M. Wolf, M. Münzenberg, M. Kläui, and T. Kampfrath, *Nat. Photon.* **10**, 483 (2016).
 - ¹² W. Yan, E. Sagasta, M. Ribeiro, Y. Niimi, L. E. Hueso, and F. Casanova, *Nat. Commun.* **8**, 661 (2017).
 - ¹³ T. Jungwirth, J. Wunderlich, and K. Olejník, *Nat. Mater.* **11**, 382 (2012).
 - ¹⁴ I. M. Miron, K. Garello, G. Gaudin, P.-J. Zermatten, M. V. Costache, S. Auffret, S. Bandiera, B. Rodmacq, A. Schuhl, and P. Gambardella, *Nature* **476**, 189 (2011).
 - ¹⁵ I. M. Miron, G. Gaudin, S. Auffret, B. Rodmacq, A. Schuhl, S. Pizzini, J. Vogel, and P. Gambardella, *Nat. Mater.* **9**, 230 (2010).
 - ¹⁶ T. S. Seifert, S. Jaiswal, J. Barker, S. T. Weber, I. Razdolski, J. Cramer, O. Gueckstock, S. F. Maehrlein, L. Nadvornik, S. Watanabe, C. Ciccarelli, A. Melnikov, G. Jakob, M. Münzenberg, S. T. B. Goennenwein, G. Woltersdorf, B. Rethfeld, P. W. Brouwer, M. Wolf, M. Kläui, and T. Kampfrath, *Nat. Commun.* **9**, 2899 (2018).
 - ¹⁷ H. Jang, J. Kimling, and D. G. Cahill, *Phys. Rev. B* **101**, 064304 (2020).
 - ¹⁸ J. Hohlfeld, S.-S. Wellershoff, J. Gädde, U. Conrad, V. Jähnke, and E. Matthias, *Chem. Phys.* **251**, 237 (2000).
 - ¹⁹ A. P. Caffrey, P. E. Hopkins, J. M. Klopff, and P. M. Norris, *Microscale Thermophys. Eng.* **9**, 365 (2005).
 - ²⁰ G.-M. Choi, C.-H. Moon, B.-C. Min, K.-J. Lee, and D. G. Cahill, *Nat. Phys.* **11**, 576 (2015).
 - ²¹ J. Kimling and D. G. Cahill, *Phys. Rev. B* **95**, 014402 (2017).
 - ²² R. Rosei and D. W. Lynch, *Phys. Rev. B* **5**, 3883 (1972).
 - ²³ S. D. Brorson, A. Kazeroonian, J. S. Moodera, D. W. Face, T. K. Cheng, E. P. Ippen, M. S. Dresselhaus, and G. Dresselhaus, *Phys. Rev. Lett.* **64**, 2172 (1990).
 - ²⁴ E. Carpena, E. Mancini, C. Dallera, M. Brenna, E. Puppini, and S. De Silvestri, *Phys. Rev. B* **78**, 174422 (2008).
 - ²⁵ P. M. Norris, A. P. Caffrey, R. J. Stevens, J. M. Klopff, J. T. McLeskey, and A. N. Smith, *Rev. Sci. Instrum.* **74**, 400 (2003).
 - ²⁶ A. N. Smith and P. M. Norris, *Appl. Phys. Lett.* **78**, 1240 (2001).
 - ²⁷ S. I. Anisimov, B. L. Kapeliovich, and T. L. Perelman, *J. Exp. Theor. Phys.* **66**, 776 (1974).
 - ²⁸ P. B. Allen, *Phys. Rev. Lett.* **59**, 1460 (1987).
 - ²⁹ L. Waldecker, R. Bertoni, and R. Ernstorfer, *J. Appl. Phys.* **117**, 044903 (2015).
 - ³⁰ J. R. Dwyer, R. E. Jordan, C. T. Hebeisen, M. Harb, R. Ernstorfer, T. Dartigalongue, and R. J. D. Miller, *J. Mod. Opt.* **54**, 923 (2007).
 - ³¹ L. Peng, S. Dudarev, and M. Whelan, *High Energy Electron Diffraction and Microscopy* (Oxford Science Publications, 2011).
 - ³² R. P. Chatelain, V. R. Morrison, B. L. M. Klarenaar, and B. J. Siwick, *Phys. Rev. Lett.* **113**, 235502 (2014).
 - ³³ L. Waldecker, R. Bertoni, H. Hübener, T. Brumme, T. Vasileiadis, D. Zahn, A. Rubio, and R. Ernstorfer, *Phys. Rev. Lett.* **119**, 036803 (2017).
 - ³⁴ D. Zahn, P.-N. Hildebrandt, T. Vasileiadis, Y. W. Windsor, Y. Qi, H. Seiler, and R. Ernstorfer, *Nano Lett.* **20**, 3728 (2020).
 - ³⁵ B. T. M. Willis and A. W. Pryor, *Thermal Vibrations in Crystallography* (Cambridge University Press, 1975).
 - ³⁶ Y. Watanabe, H. Iwasaki, and S. Ogawa, *Jpn. J. Appl. Phys.* **10**, 786 (1971).
 - ³⁷ S. Nie, X. Wang, H. Park, R. Clinite, and J. Cao, *Phys. Rev. Lett.* **96**, 025901 (2006).
 - ³⁸ A. Nakamura, T. Shimojima, M. Nakano, Y. Iwasa, and K. Ishizaka, *Struct. Dyn.* **3**, 064501 (2016).
 - ³⁹ Z. Lin, L. V. Zhigilei, and V. Celli, *Phys. Rev. B* **77**, 075133 (2008).
 - ⁴⁰ C. Kittel, *Introduction to Solid State Physics*, 8th ed. (Wiley, 2004).
 - ⁴¹ C. N. Singman, *J. Chem. Educ.* **61**, 137 (1984).
 - ⁴² L. Waldecker, R. Bertoni, R. Ernstorfer, and J. Vorberger, *Phys. Rev. X* **6**, 021003 (2016).
 - ⁴³ M. Trigo, J. Chen, V. H. Vishwanath, Y. M. Sheu, T. Graber, R. Henning, and D. A. Reis, *Phys. Rev. B* **82**, 235205 (2010).
 - ⁴⁴ M. J. Stern, L. P. René de Cotret, M. R. Otto, R. P. Chatelain, J.-P. Boisvert, M. Sutton, and B. J. Siwick, *Phys. Rev. B* **97**, 165416 (2018).
 - ⁴⁵ U. Ritzmann, P. M. Oppeneer, and P. Maldonado, *Phys. Rev. B* **102**, 214305 (2020).
 - ⁴⁶ H. Seiler, D. Zahn, M. Zacharias, P.-N. Hildebrandt, T. Vasileiadis, Y. W. Windsor, Y. Qi, C. Carbogno, C. Draxl, R. Ernstorfer, and F. Caruso, *Nano Lett.* **21**, 6171 (2021).