

Phonon transport in the gigahertz to terahertz range: Confinement, topology, and second sound

Cite as: J. Appl. Phys. **131**, 180901 (2022); <https://doi.org/10.1063/5.0073508>

Submitted: 30 September 2021 • Accepted: 19 April 2022 • Published Online: 09 May 2022

 Thomas Vasileiadis,  Juan Sebastian Reparaz and  Bartłomiej Graczykowski

COLLECTIONS

Paper published as part of the special topic on [Engineering and Understanding of Thermal Conduction in Materials](#)

 This paper was selected as an Editor's Pick



View Online



Export Citation



CrossMark

ARTICLES YOU MAY BE INTERESTED IN

[Mechanical properties of \$\text{Li}_2\text{MoO}_4\$ single crystals](#)

Journal of Applied Physics **131**, 175102 (2022); <https://doi.org/10.1063/5.0085260>

[Vector optical field manipulation via structural functional materials: Tutorial](#)

Journal of Applied Physics **131**, 181101 (2022); <https://doi.org/10.1063/5.0089859>

[Observation of an anisotropic ultrafast spin relaxation process in large-area \$\text{WTe}_2\$ films](#)

Journal of Applied Physics **131**, 163903 (2022); <https://doi.org/10.1063/5.0090935>

Journal of Applied Physics **Special Topics** Open for Submissions [Learn More](#)

Phonon transport in the gigahertz to terahertz range: Confinement, topology, and second sound

Cite as: J. Appl. Phys. **131**, 180901 (2022); doi: [10.1063/5.0073508](https://doi.org/10.1063/5.0073508)

Submitted: 30 September 2021 · Accepted: 19 April 2022 ·

Published Online: 9 May 2022



View Online



Export Citation



CrossMark

Thomas Vasileiadis,^{1,a)}  Juan Sebastian Reparaz,²  and Bartłomiej Graczykowski^{1,a),b)} 

AFFILIATIONS

¹Faculty of Physics, Adam Mickiewicz University, Uniwersytetu Poznańskiego 2, 61-614 Poznań, Poland

²Institut de Ciència de Materials de Barcelona, ICMAB-CSIC, Campus UAB, 08193 Bellaterra, Spain

Note: This paper is part of the Special Topic on Engineering and Understanding of Thermal Conduction in Materials.

^{a)}**Also at:** Max Planck Institute for Polymer Research, Ackermannweg 10, D-55128 Mainz, Germany.

^{b)}**Author to whom correspondence should be addressed:** bartlomiej.graczykowski@amu.edu.pl

ABSTRACT

Transport of heat and hypersound with gigahertz (GHz) to terahertz (THz) phonons is crucial for heat management in electronics, mediating signal processing with microwave radiation, thermoelectrics, and various types of sensors based on nanomechanical resonators. Efficient control of heat and sound transport requires new materials, novel experimental techniques, and a detailed knowledge of the interaction of phonons with other elementary excitations. Wave-like heat transport, also known as second sound, has recently attracted renewed attention since it provides several opportunities for overcoming some of the limitations imposed by diffusive transport (Fourier's regime). The frequency-domain detection of GHz-to-THz phonons can be carried out in a remote, non-destructive, and all-optical manner. The ongoing development of nanodevices and metamaterials made of low-dimensional nanostructures will require spatially resolved, time-resolved, and anisotropic measurements of phonon-related properties. These tasks can be accomplished with Brillouin light scattering (BLS) and various newly developed variants of this method, such as pumped-BLS. In the near future, pumped-BLS is expected to become useful for characterizing GHz topological nanophononics. Finally, second-sound phenomena can be observed with all-optical methods like frequency-domain thermoreflectance.

Published under an exclusive license by AIP Publishing. <https://doi.org/10.1063/5.0073508>

I. INTRODUCTION

Nowadays, material science and solid-state physics aim to provide devices with: (i) low energy consumption and efficient thermal management, (ii) mechanical robustness, and (iii) closed-loop lifecycle management. The efficient control of heat is particularly challenging as the device components approach nanoscale dimensions.^{1,2} In addition, energy efficiency in signal processing can require transforming one type of signal into another, e.g., the transformation of microwaves into acoustic phonons with piezoelectric elements.³ Mechanical robustness is necessary for wireless devices,³ sensors,^{4,5} and actuators,⁶ especially when they operate in harsh environmental conditions. On the other hand, closed-loop lifecycle management often requires trade-offs between devices' performance, durability, and environmental impact of their components.

The mechanical and thermal properties of materials are strongly connected with the physics of acoustic phonon transport in the gigahertz (GHz) to terahertz (THz) regime. This creates a growing demand for the so-called nanophononics, meaning nano- and meta-materials that enable control over phonons. In general, nanophononics offers heat management, efficient heat removal, energy harvesting, vibrational attenuation, sensors based on nanomechanical resonators, and optomechanics for mediating signal processing with microwaves.⁷⁻⁹ It goes without saying that the progress in this field requires the development of new sensitive probes of phonons that can be harnessed for contactless, non-destructive, mechanical, and thermal evaluation of functional materials. The generation, transport, and attenuation of GHz-THz phonons can be efficiently studied with various all-optical, inelastic light

scattering techniques. In combination with optical microscopy, light-based techniques provide adequate spatial resolution for most practical designs of GHz phononic metamaterials.^{8–11} The detection of acoustic phonons with light is a manifestation of optomechanical (OM) coupling. The OM coupling can be sufficiently strong for mechanical evaluation of single nanostructures.^{12–15} Light-based techniques can be categorized into frequency (GHz–THz) and time-domain (ns–ps) methods. Frequency-domain methods include Raman thermometry,^{16,17} Brillouin light scattering (BLS),¹⁸ and frequency-domain thermoreflectance (FD-TR).^{19,20} Time-domain methods include transient grating techniques,^{21–23} time-resolved thermoreflectance (TD-TR),^{24,25} time-domain BLS,²⁶ and the method of asynchronous optical sampling (ASOPS).^{27,28} In this work, we emphasize experimental works and particularly the techniques of BLS, FD-TR, and TD-TR. We discuss how the recently developed pumped-BLS approach can be used to study acoustic Anderson localization, one-way transport in acoustic diodes, and topological acoustics. In the discussion of BLS, we omit its use on the biomedical sector^{29–32} and on spintronics (magnonics).^{33–36} Finally, we turn our attention to thermal waves, otherwise known as Second Sound. In the hydrodynamic regime, the temperature field is partially transported by thermal waves, as given by the hyperbolic heat equation. We provide a historical overview of the field, emphasizing the recent developments in experiments, theoretical aspects, and numerical experiments.

II. SPONTANEOUS BRILLOUIN LIGHT SCATTERING FROM THERMAL PHONONS

The development of BLS started in 1922 with the work of Léon Brillouin³⁷ and continued with early contributions by Mandelstam in 1926³⁸ and with the discovery of stimulated BLS in 1964.³⁹ Initially, BLS was mainly applied to study bulk materials such as transparent glasses, polymers, and liquids that give a strong signal of inelastically scattered light. However, the development of high-quality single-mode lasers and multipass tandem Fabry-Perot interferometers⁴⁰ paved the way for more demanding BLS measurements of opaque, semiconducting, and spatially confined systems. Spontaneous BLS is a versatile, heavily used, frequency-domain probe of thermally populated GHz phonons,¹⁸ while stimulated BLS plays an important role in fiber optics.⁴¹ Spontaneous BLS combined with optical microscopy, termed micro-BLS (μ -BLS), offers a spatial resolution of hundreds of nanometers to a few micrometers that can be used to study sub-micrometer thick membranes and phononic metamaterials.¹¹ Nowadays, BLS is used for the characterization of inorganic bulk and nanoscale materials, fiber optics, soft matter, and biological systems and for studying spin waves (magnons). On the one hand, BLS can be used to reveal the elastic properties of nanomaterials like nanospheres^{42–45} (OD), nanowires¹² or nanopillars^{46,47} (1D), and nanosheets^{15,48} (2D). On the other hand, BLS can be used to study thermal transport.

A. Optomechanical coupling in low-dimensional materials

The OM-coupling driving BLS stems from two phenomena: the photoelastic coupling (PE) and the moving interface (MI) or surface ripple mechanism.^{53,54} The PE coupling can be understood

as the (bulk) inelastic diffraction of light from acoustic waves. The MI mechanism is inelastic light scattering by surface (interface) motions. Interestingly, the PE and MI effects can give inelastically scattered light of opposite phase leading to self-cancellation of BLS.^{43,55}

The OM coupling and BLS signal of nanomaterials can be enhanced through the plasmonic near fields of metallic nanostructures.^{13,14,56–58} However, we believe that the enhancement factor for BLS cannot reach that of surface-enhanced Raman scattering (SERS), in which the signal of molecular vibrations is enhanced by over 10^8 times with plasmons.⁵⁹ On the one hand, the strong enhancement observed in SERS is currently attributed to atomic-scale lightning rod effects close to the so-called picocavities.⁶⁰ Such phenomena are relevant for molecules but cannot be exploited for the confined acoustic modes of entire nanostructures. On the other hand, the BLS signal comes from volume (PE) and surface (MI) integrals that take into account the entire distribution of atomic displacements and their overlap with the electromagnetic fields.⁵⁸ This means that if there is a considerable spatial separation between the maximum atomic displacement and the maximum electromagnetic field, then the OM coupling and the BLS enhancement will be limited. The experimental efforts for plasmon-enhanced BLS are facilitated by the development of electromagnetic perturbation theories for dissipative systems.⁶¹

Nevertheless, the recent study of Babacic *et al.*¹⁵ on few-nanometer thick free-standing MoSe₂ membranes [Fig. 1(a)] shows that the intrinsic PE coupling of some low-dimensional materials can be exceptionally strong. MoSe₂ is a van der Waals (vdW) layered material and a prototypical member of the transition metal dichalcogenides (TMDCs) family. In MoSe₂, the OM coupling enables the detection of confined acoustic (Lamb) waves [Fig. 1(b)]. As the membranes' thickness decreases, the bulk acoustic phonons transform into symmetric (S) and anti-symmetric (A) Lamb waves and shear-horizontal (SH) waves. All these waves can be probed with μ -BLS for selected polarization of the incident and scattered light (p-p for A and S, p-s or s-p for SH). Due to momentum conservation during light scattering, the acoustic wavevector q of all these waves is parallel to the surface with magnitude $q = 4\pi \sin \theta / \lambda$, where θ is the angle of incidence and λ is the wavelength of light. The measured dispersion relationships are sensitively dependent on the elastic properties, the membrane thickness, and the residual stress. Thus, μ -BLS is a new contactless method for elastic evaluation and measurements of thickness and stress of 2D nanomaterials. Interestingly, BLS is capable of detecting SH waves [Fig. 1(b)] due to PE coupling despite the minimal scattering volume governed by membrane thicknesses down to three molecular layers. This observation calls for further investigations of light-matter interactions and OM coupling in ultrathin TMDCs.

Regarding bulk homogenous semiconductors, μ -BLS can probe under certain conditions all types of acoustic phonons: longitudinal (L) and transverse (T) bulk acoustic waves (BAWs), Rayleigh surface waves (RSWs), pseudo-RSWs, and the so-called high-frequency pseudo-surface waves (HFPSAWs). The surface-confined RSWs contribute to BLS through the surface-ripple mechanism (MI coupling). The probed RSWs have acoustic wavevector q parallel to the surface, identical to that of Lamb waves. The

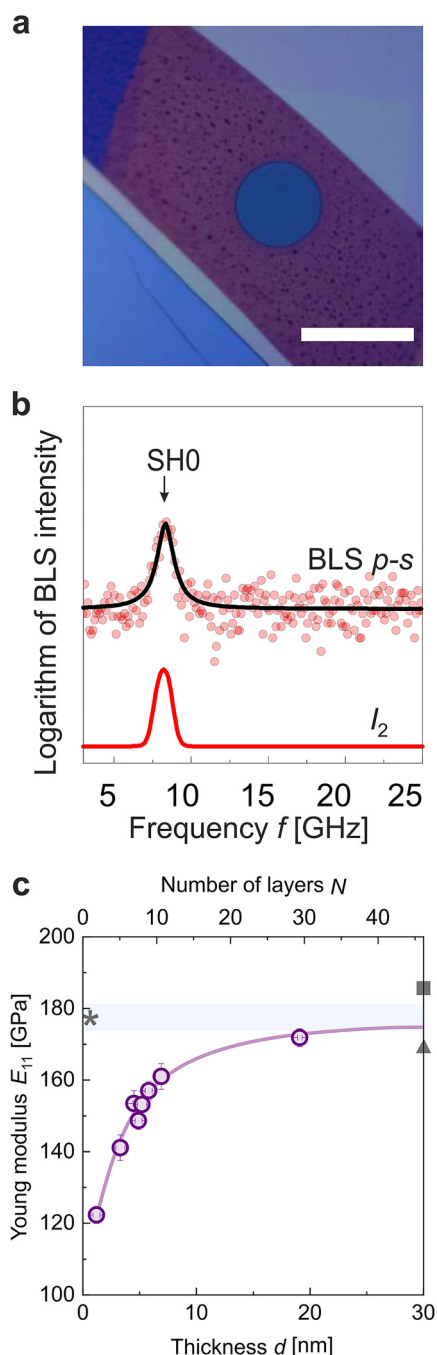


FIG. 1. Optomechanical coupling and elastic size effect in MoSe₂. (a) Optical microscopy of free-standing ultrathin MoSe₂ membranes suspended over circular holes on a Si₃N₄ substrate. (b) Evidence of ultra-strong OM coupling in MoSe₂: experimental and calculated BLS spectra of shear-horizontal (SH) acoustic waves in a 6.9 nm-thick membrane. (c) The thickness dependent Young modulus of MoSe₂ showing significant elastic softening. (a)–(c) obtained from Babacic *et al.*, *Adv. Mater.* **33**, 2008614 (2021). Copyright 2021 Author(s), licensed under a Creative Commons Attribution (CC BY) license.

acoustic wavevector of HFPSAWs obeys the same relationship for highly opaque materials like TMDCs. In this case, the signal comes from sub-surface PE coupling. The back-scattering BLS from usual bulk phonons is suppressed due to the anisotropic optical properties of TMDCs and particularly the very short penetration depth at optical wavelengths. Sub-surface PE coupling also enables the detection of transverse (SH) bulk waves propagating in the close vicinity of the free surface. In conclusion, the optical properties of TMDCs facilitate momentum-resolved μ -BLS detection of all types of acoustic waves using the simple back-scattering geometry. These non-destructive measurements reveal the complete anisotropic elasticity of low-dimensional materials (elastic constants), which are inaccessible to semi-empirical techniques like atomic force microscopy nano-indentation.

B. Elastic size effect in 2D materials

As all fields of nanotechnology, research in nanophononics was strongly affected by the discovery of graphene. It has even been suggested that the most successful applications of graphene could stem from its phononic rather than electronic properties and that practical applications will be based on few-layer structures rather than pure single layers.⁶² Graphene remains at the forefront of research in phononics, including exotic phonon-hydrodynamics phenomena⁶² and second sound (Sec. IV). However, the study of phonon transport in two dimensions can become particularly challenging for 2D materials beyond graphene, termed van der Waals materials, which can have complicated compound structures and strong in-plane anisotropies.

Van der Waals materials and particular TMDCs and nanomaterials are expected to be the game-changer for flexible and miniaturized devices due to their unique electronic, optical, optoelectronic, and thermal properties with respect to bulk—see Refs. 15 and 48 and references therein. All real-world applications of TMDCs require mechanical and thermal durability, as well as accurate knowledge of their size-dependent anisotropic mechanical properties. In addition, a long-debated topic on TMDCs has been the effect of thickness on their elastic properties. These questions cannot receive a definite answer with techniques that give a spatial average of the elastic response (e.g., nano-indentation or buckling-based metrology). Instead, it is possible to combine BLS, Raman, and pump-probe measurements to find all the independent components of the elasticity tensor.

Following this approach, it has been shown that the elastic parameters of MoSe₂ are decreasing as the thickness gets smaller—see, for instance, the thickness-dependence of the in-plane Young modulus in Fig. 1(c). The observed elastic size effect has two profound implications. First, it affects the performance of nanomechanical devices, such as nanomechanical resonators for sensors. Second, it is expected to affect the thermal transport with GHz–THz acoustic phonons in nanodevices. Thus, these measurements are also valuable for achieving good thermal management in nanodevices. Equipped with the knowledge on prototypical TMDCs like MoS₂ and MoSe₂, it is now possible to apply BLS on more complicated materials, such as 2D metamaterials based on TMDCs⁶³ and 2D materials with strongly anisotropic structures such as black phosphorus^{64,65} and orpiment⁶⁶ (As₂S₃).

III. BRILLOUIN LIGHT SCATTERING FROM NON-THERMAL PHONONS

BLS of semi-opaque, light-absorbing, and ultrasmall semiconductors is characterized by a poor signal-to-noise ratio and requires exceptionally long exposure times. This obstacle can be overcome with the recently developed technique called pumped-BLS.⁶⁹ This all-optical technique combines femtosecond laser excitation of non-thermal, coherent acoustic waves with continuous wave (CW) lasers for frequency-domain detection. Using this technique, the BLS signal of photoexcited gigahertz phonons in semiconducting nanomembranes displays a hundredfold enhancement as compared with thermal equilibrium, without the need of prescribed metallic transducers. Recently, Rolle *et al.*⁷⁰ have used a similar approach to inject coherent phonons in opaque phononic crystals and study them with BLS.

Pumped-BLS can also be used in a time-resolved manner using appropriate electronics. Such time-resolved measurements are useful for studying phase transitions, for instance, glass transitions.⁷¹ Beyond pulsed lasers, time-resolved BLS can be combined with other external stimuli, such as magnetic fields for studying spin waves.⁷² An interesting task for time-resolved BLS will be to examine the elastic properties of 2D materials with interesting topological properties and photoinduced phase transitions like MoSe₂,⁷³ MoTe₂,⁷⁴ and WTe₂.⁷⁵

A. Topological nanophononics

The functionalities of phononic devices cannot be entirely explained by their vibrational density of states (VDOS) and a single experimental spectrum. For instance, topological phononics own their properties on reciprocal-space characteristics, e.g., double Dirac cones^{76–78} and band-inversion.^{79,80} Such features in momentum-space can be revealed through angle-resolved (momentum-resolved) BLS measurements. Moreover, it is not straightforward to conceive the reciprocal-space characteristics of topological phononics from their real-space morphology. Various factors, such as unavoidable structural imperfections, can lead to disorder and incoherent phonon transport.²⁸ In this aspect, BLS is again a useful tool for the characterization of topological phononics.

Studies of topological acoustics in the sub-GHz range employ loudspeakers to launch acoustic waves and microphones for detection. A similar approach can be adopted for the recently developed field of high frequency (GHz) topological nanophononics^{79,81} with pumped-BLS [Fig. 2(a)]. In this case, the “loudspeaker” and the “microphone” will be femtosecond laser pulses and μ -BLS, respectively. The μ -BLS measurements can provide the VDOS or the band structure with a broad or narrow collection angle, respectively [Fig. 2(a), right]. The various phononic bands have a BLS cross section that varies according to symmetry considerations. Thus, to extract as many bands as possible, it is necessary to employ various scattering geometries and polarizations. Despite being tedious, such measurements reveal the character (symmetry) of the various vibrational modes, which is an important factor for topological phase transitions such as band inversion at interfaces.^{80,82}

A particularly interesting class of topological systems are the so-called higher-order topological crystals.^{82–84} A 2D second-order topological crystal will host 2D bulk-states, 1D edge-states, and 0D

corner-states. Owing to their spatial resolution, μ -BLS and pumped-BLS can be used to map the VDOS and to reveal states with 1D and 0D confinement [Fig. 2(b)]. Spatially resolved pumped-BLS can also be useful for studying acoustic Anderson localization.⁸⁵ Moreover, BLS can be used to prove one-way transport on 1D edge-states [Fig. 2(c)]. The relative intensities of Stokes and anti-Stokes scattering is a direct manifestation of directional transport of acoustic waves.⁶⁹ The scenario depicted in Fig. 2(c) will lead to an asymmetric BLS spectrum as the one sketched in Fig. 2(d) (the same approach can be followed for acoustic diodes^{86–88}). Additionally, topological edge-states show robustness to disorder and immunity against back-scattering. These aspects can be examined using pumped-BLS as in Fig. 2(e).

In view of applications, a highly desired characteristic of topological phononics is tunability.^{80,89} Li *et al.*⁶⁷ have synthesized tunable sub-GHz topological phononics by creating a heterostructure of immobile hard PnCs and mobile soft PnCs [Fig. 2(f)]. Such functional combinations of hard and soft matter have also been explored in the field of GHz nanophononics. For instance, Wang *et al.*⁹⁰ have demonstrated thermally tunable anisotropic thermoelastic properties in hybrid Bragg stacks of mica-type nanosheets and polymer layers. We consider hard-soft heterostructures as a promising class of materials for tunable nanophononics and for the emerging field of topological phononics in the GHz range.⁹¹ Within the spirit of pumped-BLS, the external stimulus for mobilizing the soft part can be focused laser light. The conversion of light into motion is a separate challenge that can be addressed with various types of soft-matter photoactuators.⁶ Some of the authors have already worked in this direction. Recently, we demonstrated fast light-driven motion of bioinspired nanomembranes, while simultaneously probing their mechanical and thermal properties with BLS.⁹² The combination of softness and flexibility with photo-thermal and photoactuating properties was made possible using ultrathin polydopamine with a layered lamellar-like microscopic structure.^{68,92} In the case of membrane-like systems, the additional merit of BLS is the ability to extract the strain from the dispersion relationship of flexural acoustic waves^{15,48,68} [Fig. 2(g)].

IV. THERMAL WAVES OR “SECOND SOUND”

The study of wave-like heat transport became a subject of mainstream research after the discovery of thermal waves in liquid He. At that time, superconductivity was also a flourishing research field, which triggered many studies to explain the origin of such waves. In fact, the physical similarities between superfluidity and superconductivity led, in some cases, to the development of similar theoretical models, e.g., the popular “two-fluid model.” Wave-like heat transport was also later rediscovered in solid He,⁹³ which encouraged numerous researchers to search for the existence of thermal waves in other solid materials.

The theoretical foundations of second sound were set already in the 1960s by Guyer and Krumhansl,⁹⁵ Chester,⁹⁶ Hardy,⁹⁷ Enz,^{98,99} and co-workers, who predicted the existence of different types of wave-like heat transport. Thermal waves of the “drifting” type were first predicted, originating from dominant normal phonon–phonon scattering events. In addition, the existence of a “driftless” or “high-frequency” type, as well as “other types” of

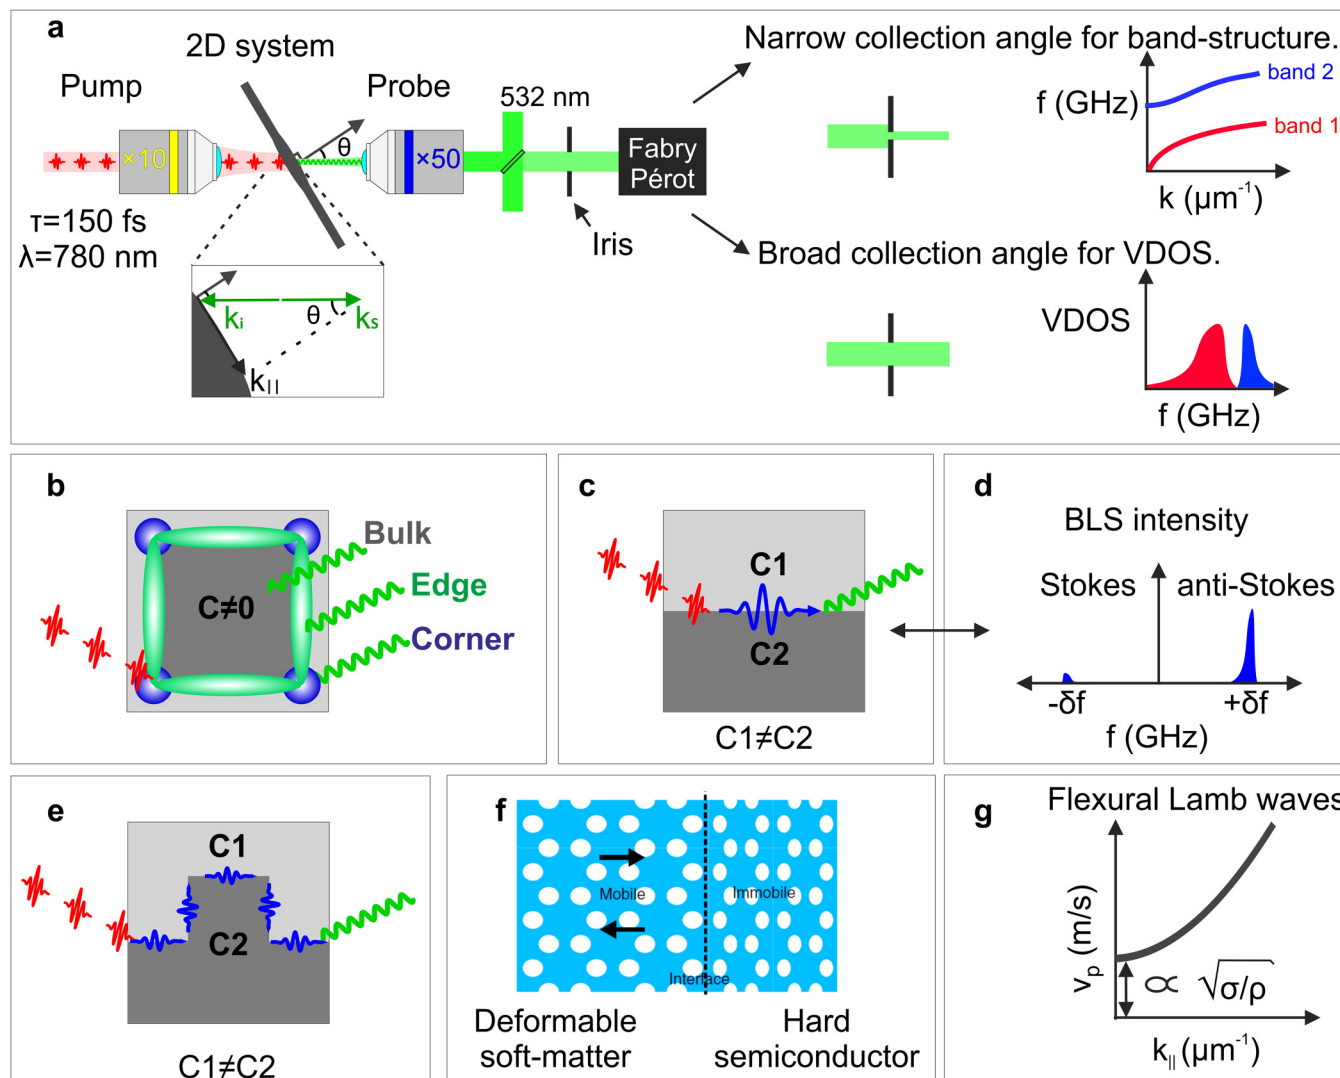


FIG. 2. Pumped Brillouin light scattering and its potential uses in topological phononics. (a) Schematic illustration of the pumped-BLS setup. (b) Pumped-BLS measurements of second-order topological phononic crystals. (c) and (d) Excitation and detection of one-way edge states, and the resulting asymmetric Stokes and anti-Stokes intensities, respectively. (e) Potential experiment for verifying topological robustness to disorder and immunity to back-scattering with pumped-BLS. (f) Tunable topological phononics based on heterostructures of deformable and immobile phononic crystals as in the work of Li *et al.*⁶⁷ Reproduced with permission from Li *et al.*, Nat. Commun. 9, 3045 (2018). Copyright 2018 Springer Nature. (g) Scheme for extracting the residual strain of nanomembranes from measurements of the dispersion of flexural acoustic waves (see Refs. 15, 48, and 68).

thermal waves, was also envisioned, as predicted by different solutions to the linearized Boltzmann transport equation (BTE). Interestingly, for the case of driftless or high-frequency thermal waves, it was theoretically found that the dominance of normal scattering events is not a necessary condition. However, the key requirement is instead the slow decay of the energy flux. Figures 3(a) and 3(b) display a simplified schematic representation of the different types of thermal waves as observed in the time or frequency domain.

The first theoretical framework was recently re-interpreted in terms of hydrodynamic thermal transport through thermal collective excitations named after “relaxons,” i.e., the thermal quasiparticles responsible for relaxing a thermal perturbation. In two recent publications,^{100,101} Simoncelli, Ceppellotti, and Marzari further developed the hydrodynamic formalism based on the framework initially proposed by Guyer and Krumhansl⁹⁵ and Hardy,⁹⁷ i.e., redefining the problem in terms of relaxons and solving *ab initio* the linearized BTE. They have provided a valuable platform to

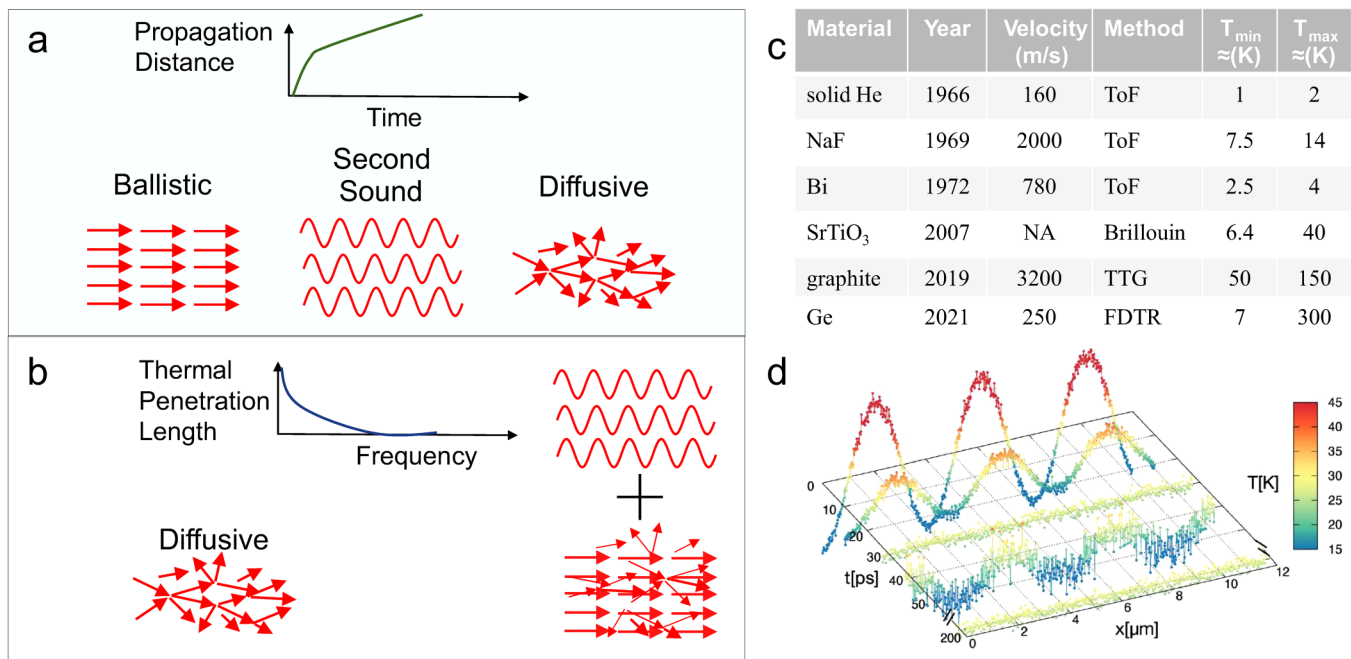


FIG. 3. Illustration of the different heat propagation regimes as observed in the time and frequency domain, on a hypothetical material, which supports wave-like heat transport (second sound). (a) Time evolution of an instantaneously excited heat pulse. The propagation speed of the initially excited heat wavepacket decreases as time elapses due to the transition between different thermal regimes. After a certain amount of time, normal phonon scattering events (conserving energy and momentum) trigger wave-like heat transport. (b) Frequency response to a broadband thermal harmonic waveform. The thermal penetration depth drastically decreases for the higher frequencies. Wave-like transport is observed in the higher frequency range over a diffusive background. (c) Properties of thermal waves as experimentally observed in different materials, including the year when they were detected, their propagation velocity and detection method, as well as the temperature window where the thermal waves are observed (ToF: time of flight, TTG: thermal transient grating, FDTR: frequency-domain thermoreflectance). (d) Extracted from Melis *et al.*, Phys. Chem. Chem. Phys., **23**, 15275 (2021). Copyright 2021 Author(s), licensed under a Creative Commons Attribution (CC BY) license. Numerical experiments using NEMD simulation the temporal response of Cumulene under a spatially harmonic-shaped thermal excitation resembling experiments done using TTG.

study second sound by setting the solution of the BTE in terms of thermal quasiparticles, a linear combination of individual phonons, which describe heat propagation more realistically than through the individual phonon picture. In particular, they have shown that it is possible to derive the damped wave equation (hyperbolic heat equation) for the case of drifting second sound, namely, when normal scattering processes are the leading phonon-phonon scattering mechanism. The more complex case of driftless second sound or high-frequency second sound, i.e., when the slow decay of the heat flux is the key requirement, was recently theoretically studied by Beardo *et al.*¹⁰² (see S6) from a macroscopic perspective. The authors proposed an *ansatz* for the solution of the linearized BTE, which takes into account the presence of a rapidly varying heat flux. Hence, they were able to derive an expression for the relaxation time of high-frequency thermal waves depending only on individual phonon properties, which can be obtained using well-established *ab initio* methods.

The experimental observation of second sound in solid materials is limited to a very small number of materials and experimental methods to date. Few techniques have been proven useful to detect the existence of thermal waves, among which are (i) impulse

experiments (time of flight), (ii) Brillouin scattering, (iii) thermal transient grating (TTG), and (iv) frequency-domain thermoreflectance. From the materials perspective, after thermal waves were experimentally demonstrated in solid He, substantial research efforts were invested to detect them in other solid materials. Disappointingly, the observation of thermal waves was only initially possible for solid He, NaF, and Bi. After a gap of almost 40 years (1972–2007) with no new experiments on second sound, in 2007 Koreeda *et al.* suggested the observation of thermal waves in SrTiO₃. Their work was based on Brillouin scattering experiments, which exhibited a singular broad band for temperatures below ≈ 50 K. The origin of this band was suggested to be of wave-like character based on a rather complex lineshape analysis of the Brillouin spectra, hence providing an indirect demonstration of the existence of second sound in SrTiO₃. More recently, second sound was observed almost up to 150 K in highly oriented pyrolytic graphite by Huberman *et al.*¹⁰³ The authors have used thermal transient grating experiments to study the temporal evolution of sinusoidal temperature distribution on the surface of the samples. Interestingly, these observations were also theoretically confirmed using *ab initio* calculations by Simoncelli *et al.*¹⁰¹ Interestingly,

second sound has been recently suggested as a possible explanation for the exceptionally high thermal conductivity of graphene and few-layer graphene.^{62,104}

High-frequency wave-like heat transport (so-called high-frequency second sound) was only recently experimentally demonstrated in Ge by Beardo *et al.*¹⁰² The authors have shown that it is possible to unlock the propagation of thermal waves in natural bulk Ge by driving the system out of equilibrium with a rapidly varying harmonic temperature field. As the frequency of the thermal excitation increased toward the hundreds of MHz range, the observation of thermal waves gradually developed. It was shown that this approach is robust enough to expose wave-like heat transport independently, to a certain extent, on the phonon scattering rates of the studied material (normal or resistive), as well as on temperature. Figure 3(c) displays a summary of the materials where second sound was claimed to be observed to date, including the experimental method used for its detection, as well as some of its fundamental properties (velocity and temperature window for its observation).

Several recent numerical experiments have also provided valuable results to address the existence of second sound in conditions that cannot be currently experimentally reproduced. To name a few, in a pioneer work Tsai and MacDonald¹⁰⁵ have shown the existence of thermal waves under a strong shock-wave using molecular dynamics (MD) in extreme pressure and temperature conditions. More recently, second sound was studied in low dimensional materials^{106,107} and carbon nanotubes.¹⁰⁸ In particular, Melis *et al.*⁹⁴ addressed the existence of second sound in cumulene using non-equilibrium molecular dynamics. The authors have simulated a TTG experiment, showing how an initially excited harmonic temperature distribution exhibits a phase shift of π as time elapses. Figure 3(d) displays the spatiotemporal evolution of the temperature field in a similar fashion as it would be obtained in a TTG experiment. A phase shift of π is observed after ≈ 50 ps, where damping of the thermal wave is evidenced by the significant signal decrease. Note that a phase shift of π in the temperature field can only be explained through the presence of thermal waves. In the case of a purely diffusive response, a monotonous decay of the initially excited harmonic thermal field toward steady-state equilibrium is expected. Finally, Zhang *et al.*¹⁰⁹ have recently extended the study of second sound to organic materials numerically showing its existence in polyacene ($-C_4H_2-$)_n, polyacetylene ($-C_2H_2-$)_n, and polyethylene ($-C_2H_4-$)_n bulk crystals.

V. CONCLUDING REMARKS

The mechanics and thermodynamics of materials are ultimately connected to their elastic properties. Basic solid-state physics and the advent of nanotechnology show that these elastic properties are generally anisotropic and size-dependent. All-optical techniques, particularly Brillouin light scattering, can be used to extract the components of the elasticity tensor and their size-dependent evolution in a remote, non-destructive way. Thus, BLS can be used to monitor the engineering of the acoustic properties of materials, for instance, with chemical doping.¹¹⁰ Acoustically engineered materials can then be tailored for various functionalities. As an example, lattice softening can be used to reduce the thermal conductivity and improve thermoelectric performance.¹¹¹

Recently, the BLS experimental setup has gained the capability to operate at any wavelength of the visible spectrum so that it can be easily adapted for a large variety of semiconducting and plasmonic nanomaterials. The underlying physics of optomechanical coupling is a separate fertile field with far-reaching implications for light-matter interactions. In addition to a spontaneous scattering of light from thermal waves, it is possible to combine Brillouin light scattering with femtosecond lasers to increase the population of phonons and, thus, their signal. The femtosecond laser pulses can also be used to prepare phononic wavepackets for testing novel concepts in nanophononics, e.g., one-way transport in topological edge states and acoustic Anderson localization.

Finally, the various activities (theory, experiments, and numerical experiments) on the detection of thermal waves in solid materials have gained substantial momentum in recent years. It is yet to be expected that through novel experimental concepts targeting small length scales, short time scales, or high frequencies, the existence of a second sound will probably be demonstrated in other materials. The question remains to which extent can we profit from this heat transport regime to better control heat propagation as an alternative to the diffusive regime described by Fourier's law.

ACKNOWLEDGMENTS

This project has received funding from the European Union's Horizon 2020 Research and Innovation Programme (No. 101003436) and the Polish National Science Centre (No. UMO-2018/31/D/ST3/03882). J.S.R. acknowledges financial support from the Spanish Ministerio de Economía, Industria y Competitividad for its support through Grant No. CEX2019-000917-S (FUNFUTURE) in the framework of the Spanish Severo Ochoa Centre of Excellence program and Grant No. PID2020-119777GB-I0016 (THERM2MAIN). The authors thank Jeena Varghese for her assistance with preparing the figures.

AUTHOR DECLARATIONS

Conflict of Interest

The authors have no conflicts to disclose.

DATA AVAILABILITY

Data sharing is not applicable to this article as no new data were created or analyzed in this study.

REFERENCES

- ¹G. Tan, L.-D. Zhao, and M. G. Kanatzidis, "Rationally designing high-performance bulk thermoelectric materials," *Chem. Rev.* **116**, 12123–12149 (2016).
- ²D. G. Cahill, P. V. Braun, G. Chen, D. R. Clarke, S. Fan, K. E. Goodson, P. Keblinski, W. P. King, G. D. Mahan, A. Majumdar, H. J. Maris, S. R. Phillpot, E. Pop, and L. Shi, "Nanoscale thermal transport. II. 2003–2012," *Appl. Phys. Rev.* **1**, 011305 (2014).
- ³S. Benchabane and A. Reinhardt, "Elastic metamaterials for radiofrequency applications," in *Fundamentals and Applications of Acoustic Metamaterials* (John Wiley & Sons, Ltd., 2019), Chap. 8, pp. 207–262.
- ⁴N. Morell, A. Reserbat-Plantey, I. Tsioutsios, K. G. Schädlér, F. Dubin, F. H. L. Koppens, and A. Bachtold, "High quality factor mechanical resonators based on WSe₂ monolayers," *Nano Lett.* **16**, 5102–5108 (2016).

- ⁵N. Morell, S. Tepsic, A. Reserbat-Plantey, A. Cepellotti, M. Manca, I. Epstein, A. Isacsson, X. Marie, F. Mauri, and A. Bachtold, "Optomechanical measurement of thermal transport in two-dimensional MoSe₂ lattices," *Nano Lett.* **19**, 3143–3150 (2019).
- ⁶H. Kim, S. kyun Ahn, D. M. Mackie, J. Kwon, S. H. Kim, C. Choi, Y. H. Moon, H. B. Lee, and S. H. Ko, "Shape morphing smart 3D actuator materials for micro soft robot," *Mater. Today* **41**, 243–269 (2020).
- ⁷S. Volz, J. Ordonez-Miranda, A. Shchepetov, M. Prunnila, J. Ahopelto, T. Pezeril, G. Vaudel, V. Gusev, P. Ruello, and E. M. Weig *et al.*, "Nanophononics: State of the art and perspectives," *Eur. Phys. J. B* **89**, 147 (2016).
- ⁸T. Vasileiadis, J. Varghese, V. Babacic, J. Gomis-Bresco, D. Navarro Urrios, and B. Graczykowski, "Progress and perspectives on phononic crystals," *J. Appl. Phys.* **129**, 160901 (2021).
- ⁹Y. Cang, Y. Jin, B. Djafari-Rouhani, and G. Fytas, "Fundamentals, progress and perspectives on high-frequency phononic crystals," *J. Phys. D: Appl. Phys.* **55**, 193002 (2022).
- ¹⁰M. Sledzinska, B. Graczykowski, F. Alzina, J. Santiso Lopez, and C. Sotomayor Torres, "Fabrication of phononic crystals on free-standing silicon membranes," *Microelectron. Eng.* **149**, 41–45 (2016).
- ¹¹M. Sledzinska, B. Graczykowski, J. Maire, E. Chavez-Angel, C. M. Sotomayor-Torres, and F. Alzina, "2D phononic crystals: Progress and prospects in hypersound and thermal transport engineering," *Adv. Funct. Mater.* **30**, 1904434 (2020).
- ¹²F. Kargar, B. Debnath, J.-P. Kakko, A. Säynätjoki, H. Lipsanen, D. L. Nika, R. K. Lake, and A. A. Balandin, "Direct observation of confined acoustic phonon polarization branches in free-standing semiconductor nanowires," *Nat. Commun.* **7**, 3261 (2016).
- ¹³A. Girard, H. Gehan, A. Crut, A. Mermet, L. Saviot, and J. Margueritat, "Mechanical coupling in gold nanoparticles supermolecules revealed by plasmon-enhanced ultralow frequency Raman spectroscopy," *Nano Lett.* **16**, 3843–3849 (2016).
- ¹⁴A. Girard, H. Gehan, A. Mermet, C. Bonnet, J. Lermé, A. Berthelot, E. Cottancin, A. Crut, and J. Margueritat, "Acoustic mode hybridization in a single dimer of gold nanoparticles," *Nano Lett.* **18**, 3800–3806 (2018).
- ¹⁵V. Babacic, D. Saleta Reig, S. Varghese, T. Vasileiadis, E. Coy, K.-J. Tielrooij, and B. Graczykowski, "Thickness-dependent elastic softening of few-layer free-standing MoSe₂," *Adv. Mater.* **33**, 2008614 (2021).
- ¹⁶E. Chávez-Angel, J. S. Reparaz, J. Gomis-Bresco, M. R. Wagner, J. Cuffe, B. Graczykowski, A. Shchepetov, H. Jiang, M. Prunnila, J. Ahopelto, F. Alzina, and C. M. Sotomayor Torres, "Reduction of the thermal conductivity in free-standing silicon nano-membranes investigated by non-invasive Raman thermometry," *APL Mater.* **2**, 012113 (2014).
- ¹⁷J. S. Reparaz, E. Chavez-Angel, M. R. Wagner, B. Graczykowski, J. Gomis-Bresco, F. Alzina, and C. M. Sotomayor Torres, "A novel contactless technique for thermal field mapping and thermal conductivity determination: Two-laser Raman thermometry," *Rev. Sci. Instrum.* **85**, 034901 (2014).
- ¹⁸F. Kargar and A. A. Balandin, "Advances in Brillouin-Mandelstam light-scattering spectroscopy," *Nat. Photonics* **15**, 720 (2021).
- ¹⁹A. J. Schmidt, R. Cheaito, and M. Chiesa, "A frequency-domain thermoreflectance method for the characterization of thermal properties," *Rev. Sci. Instrum.* **80**, 094901 (2009).
- ²⁰K. T. Regner, D. P. Sellan, Z. Su, C. H. Amon, A. J. McGaughey, and J. A. Malen, "Broadband phonon mean free path contributions to thermal conductivity measured using frequency domain thermoreflectance," *Nat. Commun.* **4**, 095901 (2013).
- ²¹J. A. Rogers, L. Dhar, and K. A. Nelson, "Noncontact determination of transverse isotropic elastic moduli in polyimide thin films using a laser based ultrasonic method," *Appl. Phys. Lett.* **65**, 312–314 (1994).
- ²²F. Bencivenga, R. Mincigrucci, F. Capotondi, L. Foglia, D. Naumenko, A. A. Maznev, E. Pedersoli, A. Simoncini, F. Caporaletti, V. Chiloyan, R. Cucini, F. Dallari, R. A. Duncan, T. D. Frazer, G. Gao, A. Gessini, L. Giannessi, S. Huberman, H. Kapteyn, J. Knobloch, G. Kurdi, N. Mahne, M. Manfreda, A. Martinelli, M. Murnane, E. Principi, L. Raimondi, S. Spampinati, C. Spezzani, M. Trovò, M. Zangrando, G. Chen, G. Monaco, K. A. Nelson, and C. Masciovecchio, "Nanoscale transient gratings excited and probed by extreme ultraviolet femtosecond pulses," *Sci. Adv.* **5**, eaaw5805 (2019).
- ²³A. A. Maznev, R. Mincigrucci, F. Bencivenga, V. Unnikandanunni, F. Capotondi, G. Chen, Z. Ding, R. A. Duncan, L. Foglia, M. G. Izzo, C. Masciovecchio, A. Martinelli, G. Monaco, E. Pedersoli, S. Bonetti, and K. A. Nelson, "Generation and detection of 50 GHz surface acoustic waves by extreme ultraviolet pulses," *Appl. Phys. Lett.* **119**, 044102 (2021).
- ²⁴D. G. Cahill, "Analysis of heat flow in layered structures for time-domain thermoreflectance," *Rev. Sci. Instrum.* **75**, 5119–5122 (2004).
- ²⁵P. E. Hopkins, C. M. Reinke, M. F. Su, R. H. Olsson, E. A. Shaner, Z. C. Leseman, J. R. Serrano, L. M. Phinney, and I. El-Kady, "Reduction in the thermal conductivity of single crystalline silicon by phononic crystal patterning," *Nano Lett.* **11**, 107–112 (2011).
- ²⁶P. Ruello and V. E. Gusev, "Physical mechanisms of coherent acoustic phonons generation by ultrafast laser action," *Ultrasonics* **56**, 21–35 (2015).
- ²⁷J. Cuffe, O. Ristow, E. Chávez, A. Shchepetov, P.-O. Chapuis, F. Alzina, M. Hettich, M. Prunnila, J. Ahopelto, T. Dekorsy, and C. M. Sotomayor Torres, "Lifetimes of confined acoustic phonons in ultrathin silicon membranes," *Phys. Rev. Lett.* **110**, 277 (2013).
- ²⁸M. R. Wagner, B. Graczykowski, J. S. Reparaz, A. El Sachat, M. Sledzinska, F. Alzina, and C. M. Sotomayor Torres, "Two-dimensional phononic crystals: Disorder matters," *Nano Lett.* **16**, 5661–5668 (2016).
- ²⁹F. Palombo and D. Fioretto, "Brillouin light scattering: Applications in biomedical sciences," *Chem. Rev.* **119**, 7833–7847 (2019).
- ³⁰J. Margueritat, A. Virgone-Carlotta, S. Monnier, H. Delanoë-Ayari, H. C. Mertani, A. Berthelot, Q. Martinet, X. Dagany, C. Rivière, J.-P. Rieu, and T. Dehoux, "High-frequency mechanical properties of tumors measured by Brillouin light scattering," *Phys. Rev. Lett.* **122**, 149 (2019).
- ³¹M. Bailey, M. Alunni-Cardinali, N. Correa, S. Caponi, T. Holsgrove, H. Barr, N. Stone, C. P. Winlove, D. Fioretto, and F. Palombo, "Viscoelastic properties of biopolymer hydrogels determined by Brillouin spectroscopy: A probe of tissue micromechanics," *Sci. Adv.* **6**, eabc1937 (2020).
- ³²C. Poon, J. Chou, M. Cortie, and I. Kabakova, "Brillouin imaging for studies of micromechanics in biology and biomedicine: From current state-of-the-art to future clinical translation," *J. Phys.: Photonics* **3**, 012002 (2021).
- ³³T. Sebastian, K. Schultheiss, B. Obry, B. Hillebrands, and H. Schultheiss, "Micro-focused Brillouin light scattering: Imaging spin waves at the nanoscale," *Front. Phys.* **3**, 1589 (2015).
- ³⁴A. Osada, A. Gloppe, R. Hisatomi, A. Noguchi, R. Yamazaki, M. Nomura, Y. Nakamura, and K. Usami, "Brillouin light scattering by magnetic quasivortices in cavity optomagnonics," *Phys. Rev. Lett.* **120**, 133602 (2018).
- ³⁵R. Hisatomi, A. Noguchi, R. Yamazaki, Y. Nakata, A. Gloppe, Y. Nakamura, and K. Usami, "Helicity-changing Brillouin light scattering by magnons in a ferromagnetic crystal," *Phys. Rev. Lett.* **123**, 207401 (2019).
- ³⁶R. Freeman, R. Lemasters, T. Kalejaiye, F. Wang, G. Chen, J. Ding, M. Wu, V. E. Demidov, S. O. Demokritov, H. Harutyunyan, and S. Urazhdin, "Brillouin light scattering of spin waves inaccessible with free-space light," *Phys. Rev. Res.* **2**, 033427 (2020).
- ³⁷L. Brillouin, "Diffusion de la lumière et des rayons X par un corps transparent homogène," *Ann. Phys.* **9**, 88–122 (1922).
- ³⁸E. L. Feinberg, "The forefather (about Leonid Ilsaakovich Mandelstam)," *Phys.-Usp.* **45**, 81–100 (2002).
- ³⁹R. Y. Chiao, C. H. Townes, and B. P. Stoicheff, "Stimulated Brillouin scattering and coherent generation of intense hypersonic waves," *Phys. Rev. Lett.* **12**, 592–595 (1964).
- ⁴⁰R. Mock, B. Hillebrands, and R. Sandercock, "Construction and performance of a Brillouin scattering set-up using a triple-pass tandem Fabry-Perot interferometer," *J. Phys. E: Sci. Instrum.* **20**, 656–659 (1987).
- ⁴¹J.-C. Beugnot, S. Lebrun, G. Pauliat, H. Maillotte, V. Laude, and T. Sylvestre, "Brillouin light scattering from surface acoustic waves in a subwavelength-diameter optical fibre," *Nat. Commun.* **5**, 5242 (2014).

- ⁴²H. Kim, Y. Cang, E. Kang, B. Graczykowski, M. Secchi, M. Montagna, R. D. Priestley, E. M. Furst, and G. Fytas, "Direct observation of polymer surface mobility via nanoparticle vibrations," *Nat. Commun.* **9**, 1 (2018).
- ⁴³B. Graczykowski, A. Gueddida, B. Djafari-Rouhani, H.-J. Butt, and G. Fytas, "Brillouin light scattering under one-dimensional confinement: Symmetry and interference self-canceling," *Phys. Rev. B* **99**, 165431 (2019).
- ⁴⁴V. Babacic, J. Varghese, E. Coy, E. Kang, M. Pochylski, J. Gapinski, G. Fytas, and B. Graczykowski, "Mechanical reinforcement of polymer colloidal crystals by supercritical fluids," *J. Colloid Interface Sci.* **579**, 786–793 (2020).
- ⁴⁵B. Graczykowski, N. Vogel, K. Bley, H.-J. Butt, and G. Fytas, "Multiband hypersound filtering in two-dimensional colloidal crystals: Adhesion, resonances, and periodicity," *Nano Lett.* **20**, 1883–1889 (2020).
- ⁴⁶B. Graczykowski, S. Mielcarek, A. Trzaskowska, J. Sarkar, P. Hakonen, and B. Mroz, "Tuning of a hypersonic surface phononic band gap using a nanoscale two-dimensional lattice of pillars," *Phys. Rev. B* **86**, 085426 (2012).
- ⁴⁷X. Huang, D. Otori, R. Yanagisawa, R. Anufriev, S. Samukawa, and M. Nomura, "Coherent and incoherent impacts of nanopillars on the thermal conductivity in silicon nanomembranes," *ACS Appl. Mater. Interfaces* **12**, 25478–25483 (2020).
- ⁴⁸B. Graczykowski, M. Sledzinska, M. Placidi, D. Saleta Reig, M. Kasprzak, F. Alzina, and C. M. Sotomayor Torres, "Elastic properties of few nanometers thick polycrystalline MoS₂ membranes: A nondestructive study," *Nano Lett.* **17**, 7647–7651 (2017).
- ⁴⁹T. Sonehara, E. Tatsu, S. Saikan, and S. Ohno, "Temperature dependence of the Brillouin frequency shift in crystals," *J. Appl. Phys.* **101**, 103507 (2007).
- ⁵⁰D. R. Birt, K. An, A. Weathers, L. Shi, M. Tsoi, and X. Li, "Brillouin light scattering spectra as local temperature sensors for thermal magnons and acoustic phonons," *Appl. Phys. Lett.* **102**, 082401 (2013).
- ⁵¹K. S. Olsson, N. Klimovich, K. An, S. Sullivan, A. Weathers, L. Shi, and X. Li, "Temperature dependence of Brillouin light scattering spectra of acoustic phonons in silicon," *Appl. Phys. Lett.* **106**, 051906 (2015).
- ⁵²K. S. Olsson, K. An, and X. Li, "Magnon and phonon thermometry with inelastic light scattering," *J. Phys. D: Appl. Phys.* **51**, 133001 (2018).
- ⁵³S. G. Johnson, M. Ibanescu, M. A. Skorobogatiy, O. Weisberg, J. D. Joannopoulos, and Y. Fink, "Perturbation theory for Maxwell's equations with shifting material boundaries," *Phys. Rev. E* **65**, 066611 (2002).
- ⁵⁴A. Every, B. Mathe, and J. Comins, "The study of guided waves in surfaces and thin supported films using surface Brillouin scattering and acoustic microscopy," *Ultrasonics* **44**, e929–e934 (2006).
- ⁵⁵O. Florez, P. F. Jarschel, Y. A. V. Espinel, C. M. B. Cordeiro, T. P. Mayer Alegre, G. S. Wiederhecker, and P. Dainese, "Brillouin scattering self-cancellation," *Nat. Commun.* **7**, 1172 (2016).
- ⁵⁶Z. N. Utegulov, J. M. Shaw, B. T. Draine, S. A. Kim, and W. L. Johnson, *Proc. SPIE* **6641**, 178–187 (2007).
- ⁵⁷Z. Meng, V. V. Yakovlev, and Z. Utegulov, *Proc. SPIE* **9340**, 125–132 (2015).
- ⁵⁸A. Noulal, E. Kang, T. Maji, M. Gkikas, B. Djafari-Rouhani, and G. Fytas, "Optomechanical coupling in Ag polymer nanocomposite films," *J. Phys. Chem. C* **125**, 14854–14864 (2021).
- ⁵⁹J. Langer, D. Jimenez de Aberasturi, J. Aizpurua, R. A. Alvarez-Puebla, B. Auguie, J. J. Baumberg, G. C. Bazan, S. E. J. Bell, A. Boisen, A. G. Brolo, J. Choo, D. Cialla-May, V. Deckert, L. Fabris, K. Faulds, F. J. Garcia de Abajo, R. Goodacre, D. Graham, A. J. Haes, C. L. Haynes, C. Huck, T. Itoh, M. Käll, J. Kneipp, N. A. Kotov, H. Kuang, E. C. Le Ru, H. K. Lee, J.-F. Li, X. Y. Ling, S. A. Maier, T. Mayerhöfer, M. Moskovits, K. Murakoshi, J.-M. Nam, S. Nie, Y. Ozaki, I. Pastoriza-Santos, J. Perez-Juste, J. Popp, A. Pucci, S. Reich, B. Ren, G. C. Schatz, T. Shegai, S. Schlucker, L.-L. Tay, K. G. Thomas, Z.-Q. Tian, R. P. Van Duyne, T. Vo-Dinh, Y. Wang, K. A. Willets, C. Xu, H. Xu, Y. Xu, Y. S. Yamamoto, B. Zhao, and L. M. Liz-Marzán, "Present and future of surface-enhanced Raman scattering," *ACS Nano* **14**, 28–117 (2020).
- ⁶⁰M. Urbietta, M. Barbry, Y. Zhang, P. Koval, D. Sánchez-Portal, N. Zabala, and J. Aizpurua, "Atomic-scale lightning rod effect in plasmonic picocavities: A classical view to a quantum effect," *ACS Nano* **12**, 585–595 (2018).
- ⁶¹A. G. Primo, N. C. Carvalho, C. M. Kersul, N. C. Frateschi, G. S. Wiederhecker, and T. P. M. Alegre, "Quasinormal-mode perturbation theory for dissipative and dispersive optomechanics," *Phys. Rev. Lett.* **125**, 233601 (2020).
- ⁶²A. A. Balandin, "Phononics of graphene and related materials," *ACS Nano* **14**, 5170–5178 (2020).
- ⁶³B. Munkhbat, A. B. Yankovich, D. G. Baranov, R. Verre, E. Olsson, and T. O. Shegai, "Transition metal dichalcogenide metamaterials with atomic precision," *Nat. Commun.* **11**, 1271 (2020).
- ⁶⁴D. Zahn, P.-N. Hildebrandt, T. Vasileiadis, Y. W. Windsor, Y. Qi, H. Seiler, and R. Ernstorfer, "Anisotropic nonequilibrium lattice dynamics of black phosphorus," *Nano Lett.* **20**, 3728–3733 (2020).
- ⁶⁵H. Seiler, D. Zahn, M. Zacharias, P.-N. Hildebrandt, T. Vasileiadis, Y. W. Windsor, Y. Qi, C. Carbone, C. Draxl, R. Ernstorfer, and F. Caruso, "Accessing the anisotropic nonthermal phonon populations in black phosphorus," *Nano Lett.* **21**, 6171–6178 (2021).
- ⁶⁶M. Šiškins, M. Lee, F. Alijani, M. R. van Blankenstein, D. Davidovikj, H. S. J. van der Zant, and P. G. Steeneken, "Highly anisotropic mechanical and optical properties of 2D layered As₂S₃ membranes," *ACS Nano* **13**, 10845–10851 (2019).
- ⁶⁷S. Li, D. Zhao, H. Niu, X. Zhu, and J. Zang, "Observation of elastic topological states in soft materials," *Nat. Commun.* **9**, 3045 (2018).
- ⁶⁸T. Marchesi D'Alvise, S. Harvey, L. Hueske, J. Szelwicka, L. Veith, T. P. J. Knowles, D. Kubiczek, C. Flaig, F. Port, K.-E. Gottschalk, F. Rosenau, B. Graczykowski, G. Fytas, F. S. Ruggeri, K. Wunderlich, and T. Weil, "Ulathin polydopamine films with phospholipid nanodiscs containing a glycoprotein A domain," *Adv. Funct. Mater.* **30**, 2000378 (2020).
- ⁶⁹T. Vasileiadis, H. Zhang, H. Wang, M. Bonn, G. Fytas, and B. Graczykowski, "Frequency-domain study of nonthermal gigahertz phonons reveals fano coupling to charge carriers," *Sci. Adv.* **6**, eabd4540 (2020).
- ⁷⁰K. Rolle, D. Yaremkevich, A. V. Scherbakov, M. Bayer, and G. Fytas, "Lifting restrictions on coherence loss when characterizing non-transparent hypersonic phononic crystals," *Sci. Rep.* **11**, 2004732 (2021).
- ⁷¹K. Rolle, H.-J. Butt, and G. Fytas, "Flash Brillouin scattering: A confocal technique for measuring glass transitions at high scan rates," *ACS Photonics* **8**, 531–539 (2021).
- ⁷²K. Schultheiss, N. Sato, P. Matthies, L. Körber, K. Wagner, T. Hula, O. Gladii, J. E. Pearson, A. Hoffmann, M. Helm, J. Fassbender, and H. Schultheiss, "Time refraction of spin waves," *Phys. Rev. Lett.* **126**, 137201 (2021).
- ⁷³M.-F. Lin, V. Kochat, A. Krishnamoorthy, L. Bassman, C. Weninger, Q. Zheng, X. Zhang, A. Apte, C. S. Tiwary, X. Shen, R. Li, R. Kalia, P. Ajayan, A. Nakano, P. Vashishta, F. Shimojo, X. Wang, D. M. Fritz, and U. Bergmann, "Ultrafast non-radiative dynamics of atomically thin MoSe₂," *Nat. Commun.* **8**, 1745 (2017).
- ⁷⁴B. Peng, H. Zhang, W. Chen, B. Hou, Z.-J. Qiu, H. Shao, H. Zhu, B. Monserrat, D. Fu, H. Weng, and C. M. Soukoulis, "Sub-picosecond photo-induced displacive phase transition in two-dimensional MoTe₂," *npj 2D Mater. Appl.* **4**, 15089 (2020).
- ⁷⁵E. J. Sie, C. M. Nyby, C. D. Pemmaraju, S. J. Park, X. Shen, J. Yang, M. C. Hoffmann, B. K. Ofori-Okai, R. Li, A. H. Reid, S. Weathersby, E. Mannebach, N. Finney, D. Rhodes, D. Chenet, A. Antony, L. Balicas, J. Hone, T. P. Devereaux, T. F. Heinz, X. Wang, and A. M. Lindenberg, "An ultrafast symmetry switch in a Weyl semimetal," *Nature* **565**, 61–66 (2019).
- ⁷⁶Y. Deng, H. Ge, Y. Tian, M. Lu, and Y. Jing, "Observation of zone folding induced acoustic topological insulators and the role of spin-mixing defects," *Phys. Rev. B* **96**, 184305 (2017).
- ⁷⁷H. Dai, M. Qian, J. Jiao, B. Xia, and D. Yu, "Subwavelength acoustic topological edge states realized by zone folding and the role of boundaries selection," *J. Appl. Phys.* **124**, 175107 (2018).
- ⁷⁸Q. Zhang, Y. Chen, K. Zhang, and G. Hu, "Dirac degeneracy and elastic topological valley modes induced by local resonant states," *Phys. Rev. B* **101**, 014101 (2020).
- ⁷⁹M. Esmann, F. R. Lamberti, P. Senellart, I. Favero, O. Krebs, L. Lanco, C. Gomez Carbonell, A. Lemaître, and N. D. Lanzillotti-Kimura, "Topological nanophononic states by band inversion," *Phys. Rev. B* **97**, 155422 (2018).

- ⁸⁰Z. Zhang, Y. Tian, Y. Cheng, Q. Wei, X. Liu, and J. Christensen, "Topological acoustic delay line," *Phys. Rev. Appl.* **9**, 034032 (2018).
- ⁸¹G. Arregui, O. Ortiz, M. Esmann, C. M. Sotomayor-Torres, C. Gomez-Carbonell, O. Mauguin, B. Perrin, A. Lemaître, P. D. García, and N. D. Lanzillotti-Kimura, "Coherent generation and detection of acoustic phonons in topological nanocavities," *APL Photonics* **4**, 030805 (2019).
- ⁸²Z. Zhang, H. Long, C. Liu, C. Shao, Y. Cheng, X. Liu, and J. Christensen, "Deep-subwavelength holey acoustic second-order topological insulators," *Adv. Mater.* **31**, 1904682 (2019).
- ⁸³H. Xue, Y. Yang, F. Gao, Y. Chong, and B. Zhang, "Acoustic higher-order topological insulator on a kagome lattice," *Nat. Mater.* **18**, 108–112 (2019).
- ⁸⁴H. Xue, Y. Yang, G. Liu, F. Gao, Y. Chong, and B. Zhang, "Realization of an acoustic third-order topological insulator," *Phys. Rev. Lett.* **122**, 244301 (2019).
- ⁸⁵H. Hu, A. Strybulevych, J. H. Page, S. E. Skipetrov, and B. A. van Tiggelen, "Localization of ultrasound in a three-dimensional elastic network," *Nat. Phys.* **4**, 945–948 (2008).
- ⁸⁶A. Maznev, A. Every, and O. Wright, "Reciprocity in reflection and transmission: What is a 'phonon diode'?", *Wave Motion* **50**, 776–784 (2013).
- ⁸⁷T. Devaux, A. Cebrecos, O. Richoux, V. Pagneux, and V. Tournat, "Acoustic radiation pressure for nonreciprocal transmission and switch effects," *Nat. Commun.* **10**, 579 (2019).
- ⁸⁸M. Kasprzak, M. Sledzinska, K. Zaleski, I. Iatsunskyi, F. Alzina, S. Volz, C. M. Sotomayor Torres, and B. Graczykowski, "High-temperature silicon thermal diode and switch," *Nano Energy* **78**, 105261 (2020).
- ⁸⁹J.-P. Xia, D. Jia, H.-X. Sun, S.-Q. Yuan, Y. Ge, Q.-R. Si, and X.-J. Liu, "Programmable coding acoustic topological insulator," *Adv. Mater.* **30**, 1805002 (2018).
- ⁹⁰Z. Wang, K. Rolle, T. Schilling, P. Hummel, A. Philipp, B. A. F. Kopera, A. M. Lechner, M. Retsch, J. Breu, and G. Fytas, "Tunable thermoelastic anisotropy in hybrid Bragg stacks with extreme polymer confinement," *Angew. Chem. Int. Ed.* **59**, 1286–1294 (2020).
- ⁹¹Q. Zhang, D. Lee, L. Zheng, X. Ma, S. I. Meyer, L. He, H. Ye, Z. Gong, B. Zhen, K. Lai, and A. T. C. Johnson, "Gigahertz topological valley Hall effect in nanoelectromechanical phononic crystals," *Nat. Electron.* **5**, 157–163 (2022).
- ⁹²T. Vasileiadis, T. Marchesi D'Alvise, C.-M. Saak, M. Pochylski, S. Harvey, C. V. Synatschke, J. Gapinski, G. Fytas, E. H. G. Backus, T. Weil, and B. Graczykowski, "Fast light-driven motion of polydopamine nanomembranes," *Nano Lett.* **22**, 578–585 (2022).
- ⁹³C. C. Ackerman, B. Bertman, H. A. Fairbank, and R. A. Guyer, "Second sound in solid helium," *Phys. Rev. Lett.* **16**, 789–791 (1966).
- ⁹⁴C. Melis, G. Fugallo, and L. Colombo, "Room temperature second sound in cumulene," *Phys. Chem. Chem. Phys.* **23**, 15275–15281 (2021).
- ⁹⁵R. A. Guyer and J. A. Krumhansl, "Solution of the linearized phonon Boltzmann equation," *Phys. Rev.* **148**, 766–778 (1966).
- ⁹⁶M. Chester, "Second sound in solids," *Phys. Rev.* **131**, 2013–2015 (1963).
- ⁹⁷R. J. Hardy, "Phonon Boltzmann equation and second sound in solids," *Phys. Rev. B* **2**, 1193–1207 (1970).
- ⁹⁸C. P. Enz, "Microscopic theory of thermal excitations in dielectric crystals and the analogy between first and second sound," *Phys. Lett.* **20**, 442–444 (1966).
- ⁹⁹C. P. Enz, "One-particle densities, thermal propagation, and second sound in dielectric crystals," *Ann. Phys.* **46**, 114–173 (1968).
- ¹⁰⁰A. Cepellotti and N. Marzari, "Thermal transport in crystals as a kinetic theory of relaxons," *Phys. Rev. X* **6**, 041013 (2016).
- ¹⁰¹M. Simoncelli, N. Marzari, and A. Cepellotti, "Generalization of Fourier's law into viscous heat equations," *Phys. Rev. X* **10**, 011019 (2020).
- ¹⁰²A. Beardo, M. López-Suárez, L. A. Pérez, L. Sendra, M. I. Alonso, C. Melis, J. Bafaluy, J. Camacho, L. Colombo, R. Rurali, F. X. Alvarez, and J. S. Reparaz, "Observation of second sound in a rapidly varying temperature field in Ge," *Sci. Adv.* **7**, eabg4677 (2021).
- ¹⁰³S. Huberman, R. A. Duncan, K. Chen, B. Song, V. Chiloyan, Z. Ding, A. A. Maznev, G. Chen, and K. A. Nelson, "Observation of second sound in graphite at temperatures above 100 K," [arXiv:1901.09160](https://arxiv.org/abs/1901.09160) (2019).
- ¹⁰⁴Y. Machida, N. Matsumoto, T. Isono, and K. Behnia, "Phonon hydrodynamics and ultrahigh-room-temperature thermal conductivity in thin graphite," *Science* **367**, 309–312 (2020).
- ¹⁰⁵D. H. Tsai and R. A. MacDonald, "Molecular-dynamical study of second sound in a solid excited by a strong heat pulse," Technical Report No. 10, 1976.
- ¹⁰⁶A. Cepellotti, G. Fugallo, L. Paulatto, M. Lazzeri, F. Mauri, and N. Marzari, "Phonon hydrodynamics in two-dimensional materials," *Nat. Commun.* **6**, 569 (2015).
- ¹⁰⁷S. Lee, D. Broido, K. Esfarjani, and G. Chen, "Hydrodynamic phonon transport in suspended graphene," *Nat. Commun.* **6**, 6290 (2015).
- ¹⁰⁸S. Lee and L. Lindsay, "Hydrodynamic phonon drift and second sound in a (20, 20) single-wall carbon nanotube," *Phys. Rev. B* **95**, 184304 (2017).
- ¹⁰⁹Z. Zhang, Y. Ouyang, Y. Guo, T. Nakayama, M. Nomura, S. Volz, and J. Chen, "Hydrodynamic phonon transport in bulk crystalline polymers," *Phys. Rev. B* **102**, 195302 (2020).
- ¹¹⁰F. Kargar, E. H. Penilla, E. Aytan, J. S. Lewis, J. E. Garay, and A. A. Balandin, "Acoustic phonon spectrum engineering in bulk crystals via incorporation of dopant atoms," *Appl. Phys. Lett.* **112**, 191902 (2018).
- ¹¹¹R. Hanus, M. T. Agne, A. J. E. Rettie, Z. Chen, G. Tan, D. Y. Chung, M. G. Kanatzidis, Y. Pei, P. W. Voorhees, and G. J. Snyder, "Lattice softening significantly reduces thermal conductivity and leads to high thermoelectric efficiency," *Adv. Mater.* **31**, 1900108 (2019).