


Faraday Discussions

Accepted Manuscript



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

This article can be cited before page numbers have been issued, to do this please use: J. Valenzuela Reina, F. Civaia, A. F. Harper, C. Scheurer and S. Köcher, *Faraday Discuss.*, 2024, DOI: 10.1039/D4FD00075G.

Cite this: DOI: 00.0000/xxxxxxxxxx

The EFG Rosetta Stone: Translating between DFT calculations and solid state NMR experiments

Javier Valenzuela Reina,^{*} Federico Civaia^{*}, Angela F. Harper^{*}, Christoph Scheurer^{*} and Simone S. Köcher^{†*}Received Date
Accepted Date

DOI: 00.0000/xxxxxxxxxx

We present a comprehensive study on the best practices for integrating first principles simulations in experimental quadrupolar solid-state nuclear magnetic resonance (SS-NMR), exploiting the synergies between theory and experiment for achieving the optimal interpretation of both. Most high performance materials (HPM), such as battery electrodes, exhibit complex SS-NMR spectra due to dynamic effects or amorphous phases. NMR crystallography for such challenging materials requires reliable, accurate, efficient computational methods for calculating NMR observables from first principles for the transfer between theoretical material structure models and the interpretation of their experimental SS-NMR spectra.

NMR-active nuclei within HPMs are routinely probed by their chemical shielding anisotropy (CSA). However, several nuclear isotopes of interest, e.g. ⁷Li and ²⁷Al, have a nuclear quadrupole and experience additional interactions with the surrounding electric field gradient (EFG). The quadrupolar interaction is a valuable source of information about atomistic structure, and in particular, local symmetry, complementing the CSA. As such, there is a range of different methods and codes to choose from for calculating EFGs, from all-electron to plane wave methods¹⁻³. We benchmark the accuracy of different simulation strategies for computing the EFG tensor of quadrupolar nuclei with plane wave density functional theory (DFT) and study the impact of the material structure as well as the details of the simulation strategy. Especially for small nuclei with few electrons, such as ⁷Li, we show that the choice of physical approximations and simulation parameters has a large effect on the transferability of the simulation results⁴. To the best of our knowledge, we present the first comprehensive reference scale and literature survey for ⁷Li quadrupolar couplings. The results allow us to establish practical guidelines for developing the best simulation strategy for correlating DFT to experimental data extracting the maximum benefit and information from both, thereby advancing further research into HPMs.

1 Introduction

Properties, functionality, and longevity of solid state high performance materials (HPMs) depend critically on their atomistic structure. In order to improve and tailor a material's properties, an understanding of its underlying structure is therefore essential. Solid-state nuclear magnetic resonance (SS-NMR) spectroscopy stands as a pivotal analytical tool in the study of inorganic, organic, and hybrid materials, irrespective of their crystalline or amorphous nature.⁵ The technique's inherent sensitivity to local atomic environments, coupled with its non-destructive approach, renders it indispensable for probing the intricate structural details of various materials.⁶ Advanced SS-NMR experiments also

probe atom dynamics and even allow for *in situ* and *in operando* studies⁷.

However, most HPMs, such as battery electrodes or catalysts, exhibit complex, ambiguous SS-NMR spectra due to dynamic effects or amorphous phases. NMR crystallography for such challenging materials requires reliable, accurate, efficient computational methods for calculating NMR observables from first principles for the transfer between theoretical models of a material and the unambiguous interpretation and analysis of its experimental SS-NMR spectra⁸⁻¹⁰. Furthermore, as the field turns towards predicting NMR spectra using machine learning and surrogate models which take training data from computed NMR quantities, the accuracy of the underlying first-principles computed observables is often considered as a baseline for extrapolation. Therefore, it is critical to provide a reference to the actual experimental values, to avoid compounding errors during the training process¹¹.

^{*} Fritz-Haber Institute of the Max Planck Society, Berlin (DE)

[†] Institut für Energie und Klimaforschung (IEK-9), Forschungszentrum Jülich GmbH, Jülich, (DE)



Table 1 Spin I and nuclear electric quadrupole moment Q of the ${}^7\text{Li}$ and ${}^{27}\text{Al}$ isotopes discussed in this paper.⁴⁵

Isotope	I	Q / fm^2
${}^7\text{Li}$	3/2	-4.01
${}^{27}\text{Al}$	5/2	14.66

The local atomistic structure of HPMs is often studied by probing the chemical shielding anisotropy (CSA) of their NMR-active nuclei^{8–10,12–14}. The interpretation of the chemical shifts of diamagnetic compounds in SS-NMR experiments with first-principles calculations of the CSA tensors is already well established^{10,12,15,16}. However, several nuclear isotopes of interest, e.g. ${}^7\text{Li}$, and ${}^{27}\text{Al}$, also have a nuclear quadrupole and therefore experience additional interactions with the surrounding electric field gradient (EFG), which are another valuable source of information complementing the CSA¹⁷. While the isotropic chemical shielding is an indirect probe for the ability of the local electron density to shield the nucleus in an applied magnetic field^{18–20}, the quadrupolar coupling is exceptionally sensitive to the symmetry of the electron density distribution and hence a powerful probe for local atomistic environments, structural motifs, and distortions^{21,22}. The calculation of quadrupolar coupling also requires less computational effort, since it is based on the ground state electronic structure and does not rely on response theory²³. But quadrupolar coupling manifests as complex features in experimental NMR spectra, such as broadened lines or satellite peaks, hence making theoretical simulations indispensable for reliable interpretation and analysis^{2,21,24}. There are several examples in the literature which show that experimental quadrupolar parameters, in combination with density functional theory (DFT) simulations can be leveraged to perform structure refinement^{25,26}, force-field validation^{27,28} as well as dynamic²⁹ and structural investigation^{30,31} in complex materials.

In the present work, we study the ${}^7\text{Li}$ and ${}^{27}\text{Al}$ nuclei in detail, since both nuclei play a critical role in high performance energy storage materials, such as solid state electrolytes, state-of-the-art electrodes, and stabilizing coatings^{32–34}. We apply pseudopotential (PP) plane wave DFT codes to calculate the quadrupolar observables in a series of diamagnetic, ionic Li and Al crystalline compounds and include an extensive literature survey of experimentally determined quadrupolar properties. We chose to limit our study to diamagnetic compounds, as paramagnetic systems require spin-polarized DFT calculations and often yield less accurate experimental results due to fast relaxation and pronounced broadening³⁵. The comparison of our simulations with experimental values from literature provides a reference scale and a comprehensive benchmark of the accuracy of the simulation and its dependence on various parameters we tested. Furthermore, we assess the implications of various approximations applied during the computational process.

2 Methods

2.1 The EFG Tensor

For NMR-active nuclei with a nuclear spin $I > 1/2$, the nuclear electric quadrupole moment Q interacts with the local EFG tensor, \mathbf{V} , which leads to an additional splitting of energy levels in an external magnetic field beyond the Zeeman effect^{36–39}. The second-rank, traceless, symmetric EFG tensor describes the gradient of the electric field at the nucleus depending on the surrounding charge distribution as the spatial second derivative of

the electrostatic potential $V(\mathbf{x})$ ⁴⁰

$$\mathbf{V} = \frac{\partial^2 V(\mathbf{x})}{\partial x_i \partial x_j}. \quad (1)$$

The eigendecomposition of the EFG tensor \mathbf{V} provides its eigenvalues and eigenvectors. The latter are a crucial quantity for comparing the calculated tensor with its experimental equivalent, the direction cosines^{41–43}, and define the local principal axes system (PAS) of the EFG relative to the crystalline coordinate system. The direction cosines represent the projection of each EFG eigenvector V_i on each lattice vector μ_j of the studied material.

More commonly studied quadrupolar coupling observables are determined by the three eigenvalues V_{ii} of the EFG tensor, which are ordered according to⁴⁴

$$|V_{zz}| > |V_{yy}| > |V_{xx}|. \quad (2)$$

The observables are the quadrupolar coupling constant C_Q , which is defined by the magnitude of the coupling, and the asymmetry $\eta \in [0, 1]$, which is a measure of the shape of the tensor

$$C_Q = \frac{eQ V_{zz}}{h}, \quad (3)$$

$$\eta = \frac{V_{xx} - V_{yy}}{V_{zz}}, \quad (4)$$

where e is the elementary charge and h Planck's constant. Nuclear properties of the studied nuclei ${}^7\text{Li}$ and ${}^{27}\text{Al}$ are reported in Table 1.

2.2 Calculation of EFG Tensors

First approaches to correlate experimental NMR observables with specific structural information or motifs already started shortly after the invention of NMR spectroscopy. The first correlation and increment schemes were empirical in nature and targeted indirect spin-spin coupling^{46,47} and chemical shielding^{48–52} mostly restricted to organic molecules. The first *ab initio* calculations of tensorial NMR properties based on the electronic structure near the nucleus relied on local basis sets and were hence technically challenging for the simulation of extended solids^{19,20,53,54}. Crystalline and semi-crystalline (e.g. defected, disordered) solid materials are most commonly described in periodic boundary conditions (PBC) utilizing Bloch plane waves⁵⁵ to take advantage of the translational symmetry^{56,57}. PPs approximate the electron density in the nuclear region by an effective core potential and thereby increase the efficiency of plane wave calculations significantly. However, the concept of PPs approximating the core region is diametrically opposed to simulating NMR observables, which capture interactions of the nuclear spin or quadrupolar



moment with the local electron density near the nucleus. Only the introduction of the projected augmented wave (PAW)⁵⁸ and the gauge-including projector augmented-wave (GIPAW)⁵⁹ methods finally allowed for the simulation of NMR properties of solids in the computationally efficient PP-PBC picture. The PAW formalism reconstructs the electron density in the core region from the optimized pseudo-electron density, while GIPAW adds translational invariance of the magnetic field gauge¹⁷.

Since NMR parameters are highly sensitive to the electronic structure, any simulation parameter that influences the converged electron density near the nucleus has an impact on the accuracy of the NMR parameter prediction. In particular, small nuclei with a small number of electrons such as Li, where the distinction between core region and valence electrons becomes vague, are expected to be susceptible to modifications in the electronic structure calculations.

One of the factors which is known to affect the resulting NMR parameter predictions is the atomistic geometry^{60,61}. Depending on the material and the method (X-ray diffraction (XRD), neutron scattering), the experimentally determined structure might not be accurate. Hence, first-principles geometry relaxations are sometimes recommended^{9,60}.

In this work, we test several simulation parameters and their impact on the accuracy of the resulting quadrupolar coupling. In order to study the effects of geometry, we compare EFG simulations with the unmodified empirical experimental input structures (**empir.**), optimized structures with fixed experimental lattice vectors and relaxed atomic positions (**fixed cell**), and fully optimized structures with both relaxed atomic positions and lattice vectors (**opt.**). While **empir.** structures determined by XRD usually fail to give reliable positions for light atoms such as hydrogen, a full DFT structure relaxation yields equilibrium structures at 0 K. **Fixed cell** structures maintain the room temperature lattice constants adopted from **empir.** structures, while optimizing atomic positions and in particular equilibrating the coordinates of light atoms.

In addition, we test the influence of exchange-correlation (xc) functionals^{4,62–64} (LDA⁶⁵, PBE⁶⁶, PBEsol⁶⁷, PW91⁶⁸, RSCAN⁶⁹), PPs, as well as cell size on the accuracy of the quadrupolar coupling computation and establish a reference scale correlating the results with experimental values from literature.

A similar study was previously conducted for CSA of ⁷Li¹⁵, however for ⁷Li quadrupolar C_Q and η parameters, available literature information is significantly sparser. In order to describe the amount of information available for all of the data in our survey, we have classified the ⁷Li and ²⁷Al compounds into two groups according to the extent of information available.

Group 1: Crystal structure and experimental values for C_Q and/or η are available, but not necessarily from the same reference.

Group 2: Crystal structure and the full EFG tensor (direction cosines) are available.

As has been previously reported, the accuracy of the nuclear electric quadrupole moment Q is also critical for comparing experi-

mental and computational C_Q values^{70,71}. But since the Q values for ²⁷Al and ⁷Li (c.f. Table 1) have not changed by more than 1% since 2008^{72,73}, we neglect this discussion here.

2.3 Computational Details

The structures of the Li and Al compounds were extracted from the Materials Project database⁷⁴, the Cambridge Structural Database (CSD)⁷⁵ or from the cited references^{21,41–43,76–98}.

The EFG calculations and geometry optimizations with CASTEP v23.1^{99,100} are converged with respect to the basis set cut-off energy and the Monkhorst k-point grid. The convergence threshold is set to a variation of less than 5% for C_Q as well as η . For the geometry optimizations, an energy tolerance of 2.0×10^{-5} eV/atom, a maximum force of 0.05 eV/Å, and a stress tolerance of 0.1 GPa/atom are employed. Cut-off energy and k-point grid are adopted from the EFG calculations. The same procedure is followed for the calculations with Quantum ESPRESSO 7.2¹⁰¹ (QE), using the same convergence criteria. Further computational details are presented in the Supplementary Information.

3 Results

3.1 ²⁷Al NMR

²⁷Al is one of the best-known and most widely studied quadrupolar nuclei in SS-NMR, both theoretically and experimentally. There is extensive experimental data available in literature for its quadrupolar observables, both C_Q and even η ¹⁰². However, to the best of our knowledge, experimental data on its full EFG tensors is rather sparse. Here, we discuss a set of 13 Al compounds of **Group 1** and two of **Group 2**.

Since Al is rather oxophilic, it is preferentially coordinated by oxygen in octahedral AlO₆ environments, which suggests a small to negligible quadrupolar coupling due to the high local symmetry. But the large nuclear electric quadrupole moment Q amplifies even a small V_{zz} , which might arise from small distortions or a less symmetric crystal space group, to a sizable C_Q ¹⁰³.

Testing the impact of the xc-functional on the calculated C_Q and η with CASTEP shows that the highly ionic Al compounds studied here are well described by both LDA⁶⁵, GGA (PBE⁶⁶, PBEsol⁶⁷, PW91⁶⁸), and meta-GGA (RSCAN⁶⁹) functionals. The standard deviation of C_Q and η with respect to the applied xc-functional is on the order of 3% and 9%, respectively. The impact of the xc-functional is thus deemed negligible and further calculations are all conducted with PBE⁶⁶.

Similarly, simulations based on the different crystal geometries **empir.**, **fixed cell**, and **opt.** derived with CASTEP only yield standard deviations on the order of 6% and 15% for C_Q and η , respectively. Overall, the **fixed cell** structures provide the best agreement with experimental reference values. The **opt.** structures yield the least reliable predictions, since PBE⁶⁶ is well known to overestimate interatomic bond lengths¹⁰⁴ and hence allows the cell volume to extend and distort. Lattice parameters



of crystalline materials determined experimentally with high confidence are regularly available in literature or databases, discouraging the use of the **opt.** structures in this case¹⁰⁵. Since the effect of DFT relaxation, either **fixed cell** or **opt.**, is minimal, all further calculations are performed with **fixed cell** structures.

The power of PBC is that they represent an infinitely large defect-free model of a crystalline solid by exploiting the translational symmetry of the Bloch plane waves⁵⁵. Calculations in PBC are usually conducted on the smallest possible unit cell (primitive cell) and expected to yield the same results as a supercell. However, previous studies have shown, that cell symmetry and supercell effects can cause numerical errors depending on the implementation of the PBC, grids, and the charge augmentation^{15,106}. Hence, the CASTEP EFG calculations were repeated with $2 \times 2 \times 2$ supercells producing identical results and ruling out any supercell effects in the case of Al.

Al is a third period element with three valence electrons in the 3s and 3p orbitals. The ten electrons of the first and second period orbitals can be considered core orbitals. Correspondingly, the default CASTEP PP (C19) includes those electrons in the effective core potential and only treats the three valence electrons explicitly. The same discrimination is made in the Quantum ESPRESSO PP utilized in this work. Tests using a CASTEP hard PP with eleven electrons being treated explicitly yield a minor decline in agreement with experiment by 0.17 MHz for C_Q , whereas η remains unaffected. Details can be found in the Supplementary Information Tab. S3.

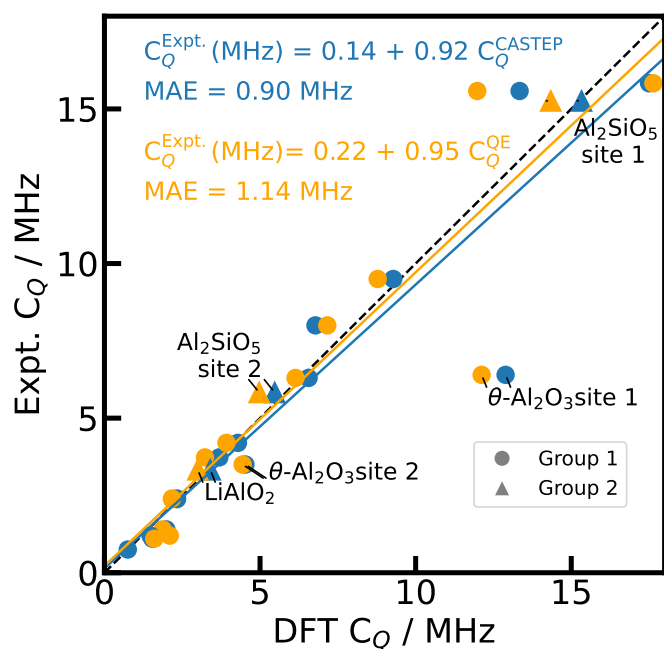


Fig. 1 Reference scale for $^{27}\text{Al } C_Q$. The $^{27}\text{Al } C_Q$ values for 15 Al-containing compounds are simulated with PBE, fixed cell geometries, default PP, and unit cells using CASTEP (blue) and Quantum ESPRESSO (orange). The experimental values from literature can be found in Supplementary Information Tab. S3. $\kappa\text{-Al}_2\text{O}_3$ and AlVO_4 are omitted (see text). The dashed diagonal line indicates the limit of ideal correlation.

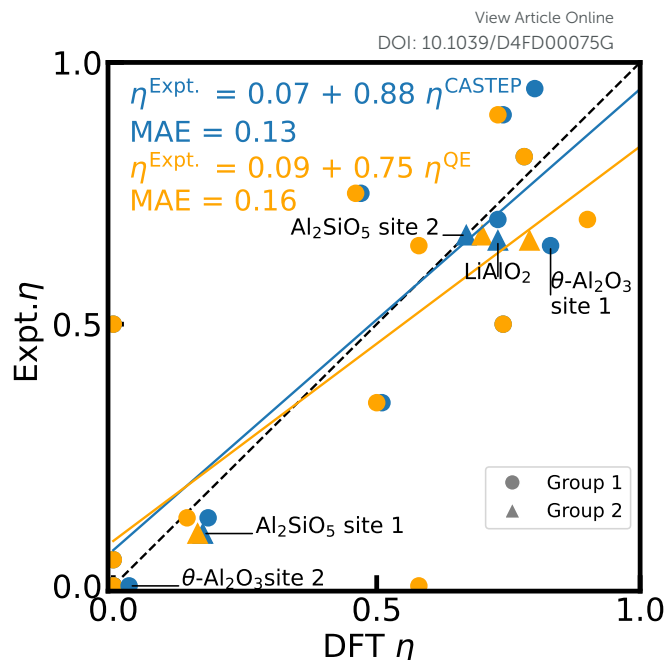


Fig. 2 Reference scale for $^{27}\text{Al } \eta$. The $^{27}\text{Al } \eta$ values for 15 Al-containing compounds are simulated with PBE, fixed cell geometries, default PP, and unit cells using CASTEP (blue) and Quantum ESPRESSO (orange). The experimental values from literature can be found in Supplementary Information Tab. S3. $\kappa\text{-Al}_2\text{O}_3$ and AlVO_4 are omitted (see text). The dashed diagonal line indicates the limit of ideal correlation.

In general, the simulations with PBE⁶⁶, **fixed cell** geometry, and default PP yield a good agreement with experimental $^{27}\text{Al } C_Q$ values both for CASTEP and Quantum ESPRESSO calculations as shown in Fig. 1 with a mean absolute error of the linear fit (MAE) of 0.90 MHz (18%) and 1.14 MHz (24%), respectively. Distinct outliers are found for $\theta\text{-Al}_2\text{O}_3$ ⁹⁸, $\kappa\text{-Al}_2\text{O}_3$ ⁷⁸ and AlVO_4 ⁷⁹ (c.f. Supplementary Information), which feature Al on multiple inequivalent crystallographic positions. For $\kappa\text{-Al}_2\text{O}_3$ and AlVO_4 , comparison of the literature references^{78,79,81,107} with the structural data derived from CSD⁷⁵ does not allow for an unambiguous assignment of the different crystallographic positions or reveals inconsistencies between different references. Therefore, we neglect $\kappa\text{-Al}_2\text{O}_3$ and AlVO_4 here.

In comparison to the reference scale for $^{27}\text{Al } C_Q$, the correlation between DFT and experimental values of $^{27}\text{Al } \eta$ is considerably less accurate, especially for the mentioned outliers (c.f. Supplementary Information), with a MAE of 0.13 and 0.16 (c.f. Fig. 2) for CASTEP and Quantum ESPRESSO, respectively. The asymmetry η is even more sensitive to the local charge distribution and its symmetry than C_Q as a result of its dependence on all the three components of the EFG tensor (Equ. 4), leading to a more pronounced error propagation of inaccuracies in the electron density. When correlating the individual principal components of the EFG tensor with values derived from experimental C_Q and η values (Supplementary Information Fig. S3), the larger deviation of η is reflected in the larger errors of V_{yy} , in particular for the outlier $\theta\text{-Al}_2\text{O}_3$.

For ^{27}Al , we found full experimental EFG tensors for both Al_2SiO_5 and $\gamma\text{-LiAlO}_2$ in literature^{43,108} (**Group 2**), which pro-



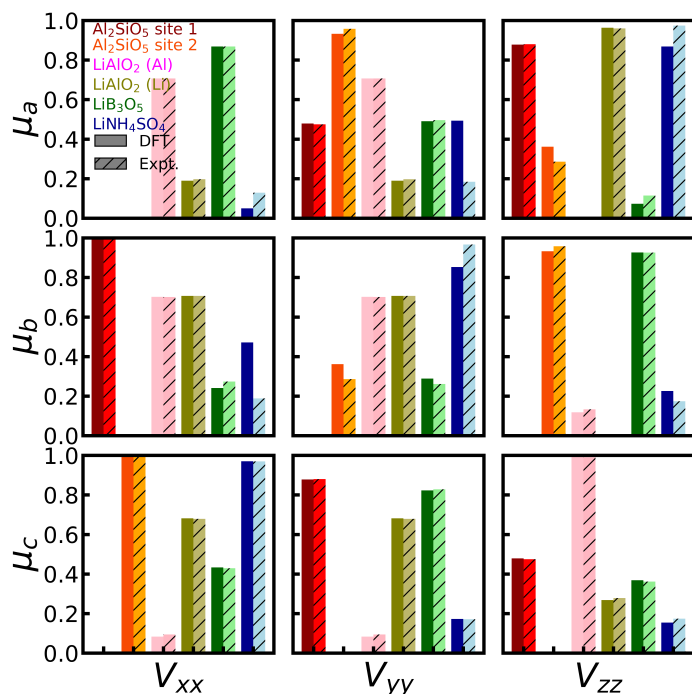


Fig. 3 Orientation of EFG tensors for ${}^7\text{Li}$ and ${}^{27}\text{Al}$. The experimentally determined direction cosines of LiB_3O_5 ⁴¹, LiNH_4SO_4 ⁴², Al_2SiO_5 ⁴³ and $\gamma\text{-LiAlO}_2$ ⁹⁷ are compared with full EFG tensors calculated with CASTEP, PBE, fixed cell geometry, default PP, and supercells (for ${}^7\text{Li}$) and unit cell (for ${}^{27}\text{Al}$). The direction cosines give the projection of each EFG eigenvector V_i on each lattice vector μ_j of the studied material.

vide us with the unique opportunity to not only evaluate the accuracy of the calculated magnitude C_Q and shape η of the EFG tensor, but also its orientation with respect to the crystal lattice. The experimental references provide the so-called direction cosines of the EFG tensor for each magnetically inequivalent ${}^{27}\text{Al}$ site, which can be correlated to the eigenvectors of the EFG tensor. Fig. 3 depicts the comparison of experimental and theoretical direction cosines (red and orange for Al_2SiO_5 and pink for $\gamma\text{-LiAlO}_2$). The DFT simulations can reproduce the experimental values with an average error of 5%, and show especially good agreement for $\gamma\text{-LiAlO}_2$, which actually outperforms the previous DFT results^{97,109}, hence predicting the orientation of the EFG tensor with excellent accuracy.

The reliable prediction of quadrupolar observables for ${}^{27}\text{Al}$ with good accuracy independent of xc-functional, geometry relaxation, PP, and supercell effect verifies the plane wave, PP method with GIPAW as robust and useful approach for calculating solid state EFGs. The quantitatively close agreement between CASTEP and Quantum ESPRESSO results proves the reliability of the method independent of the implementation, for ${}^{27}\text{Al}$.

3.2 ${}^7\text{Li}$ NMR

Although ${}^7\text{Li}$ and its quadrupolar couplings are not as well studied as ${}^{27}\text{Al}$, quadrupolar ${}^7\text{Li}$ SS-NMR plays a crucial role in materials research for Li ion batteries, where Li is the charge carrier³⁴. A multitude of different NMR experiments is available that probe the local atomistic structure of ${}^7\text{Li}$ as well as its dynamics by ad-

ressing either CSA or quadrupolar interactions⁹¹. *In operando* experiments even allow for tracking charge transport through batteries while cycling¹¹⁰.

In contrast to ${}^{27}\text{Al}$, the nuclear electric quadrupole moment, Q for ${}^7\text{Li}$ is an order of magnitude smaller, and Li has only three electrons. A small number of electrons presents a challenge when using a Li PP, which divides the electrons into core and valence electrons as well as the electron density in a core and an interstitial region. For the three electrons of Li, this distinction becomes ambiguous. Furthermore, the number of experimental ${}^7\text{Li}$ C_Q , and in particular η and explicit EFG tensors components for crystalline, ionic, diamagnetic Li compounds available in literature is limited. In the following, we discuss a set of 24 Li compounds, of which 20 belong to **Group 1**, and three to **Group 2**. However, the availability of data for η is extremely sparse.

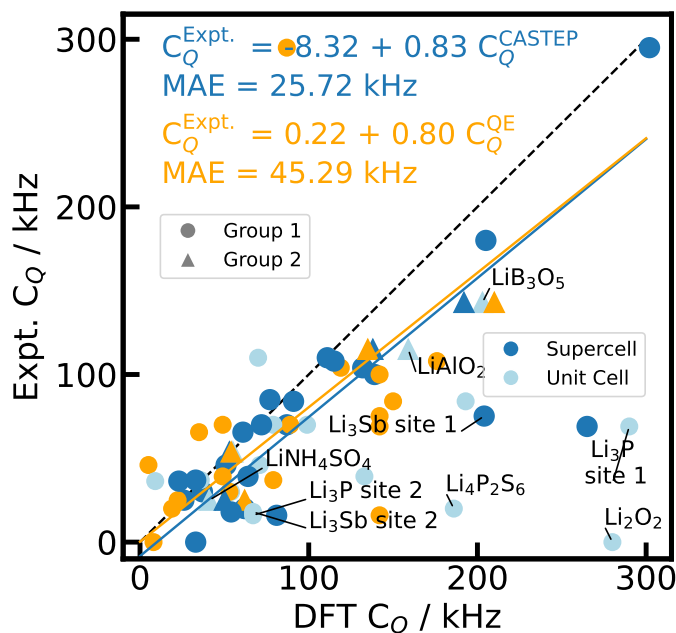


Fig. 4 Reference scale for ${}^7\text{Li}$ C_Q . The ${}^7\text{Li}$ C_Q values for 23 Li-containing compounds are calculated with PBE, fixed cell geometries, using CASTEP for unit cells (light blue), $2\times 2\times 2$ supercells (blue), and Quantum Espresso (orange) with the default PP in each case. The experimental values from literature can be found in Supplementary Information Tab. S4. The dashed diagonal line indicates the limit of ideal correlation. Outliers including Li_3P and Li_3Sb are labelled and described further in the text. The data point for Li_3N [site 1] ($C_Q = 582$ kHz, Supplementary Information Tab. S4) is beyond the depicted range, but included in the regression analysis.

As already observed for ${}^{27}\text{Al}$, the impact of the xc-functional is negligible for these ionic compounds with standard deviations of 1% and 3% for CASTEP-based C_Q and η , respectively. PBE⁶⁶ is chosen as default xc-functional for all further analyses (c.f. Fig. 4).

Similarly, the details of geometry relaxation are largely irrelevant with a standard deviation of 3% (C_Q) and 10% (η) for **empir.**, **fixed cell**, and **opt.** geometries simulated with CASTEP. However, there is one significant exception, LiNH_4SO_4 ⁴². With the experimental crystal structure adopted from CSD⁷⁵, the



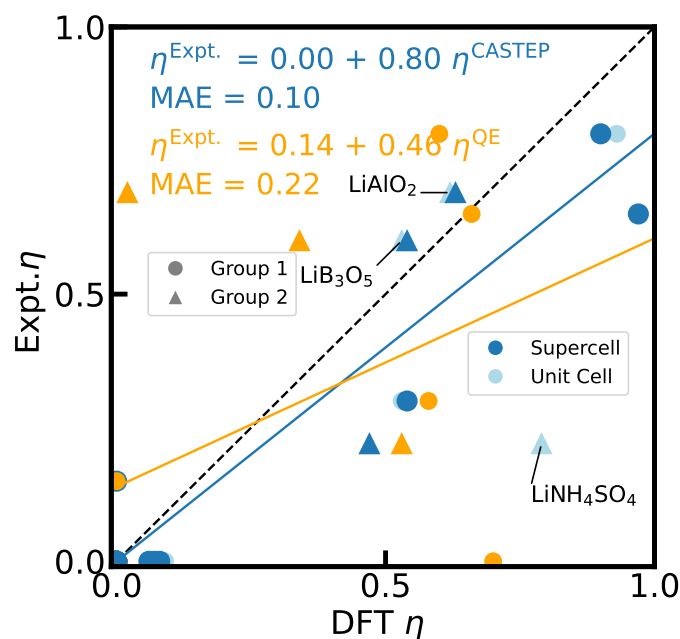


Fig. 5 Reference scale for ${}^7\text{Li}$ η . The ${}^7\text{Li}$ η values for 23 Li-containing compounds are calculated with PBE, fixed cell geometries, using CASTEP for unit cells (light blue), $2\times 2\times 2$ supercells (blue), and Quantum Espresso (orange) with the default PP in each case. For 15 of those compounds, the experimental values from literature can be found in Supplementary Information Tab. S4. The dashed diagonal line indicates the limit of ideal correlation. Outliers including LiH_4NSO_4 are labelled and described further in the text.

calculated η is off by more than factor 3 for the unit cell and gets even worse for the supercell (data not shown). Closer inspection of the crystal structure reveals rather different N-H bond lengths in the NH_4^+ units, which do not correspond to the structure visualized in ⁴². Neither the **fixed cell** nor the **opt.** structures improve the accuracy notably with respect to the experimental reference of η . Only a DFT **fixed cell** relaxation with a relaxed symmetry tolerance allows the N-H bonds to equilibrate, yielding a considerably better agreement with experiment and in particular an improvement by the supercell effect (c.f. Fig. 5).

Other striking outliers in the C_Q correlation (Fig. 4) can be identified as the hexagonal, layered Li pnictide Li_3P and its homologous Li_3Sb ⁹⁰ (hex- Li_3Pn). The calculated C_Q values of the different crystallographic sites are qualitatively correct, matching the Li in the Li-pnictogen layer (P, Sb) with the larger C_Q value and the Li in the pure Li interlayer with the smaller C_Q constant. However, the overestimation by DFT simulations amounts to factor 3 to 5. Both Li_3P and Li_3Sb are well-known Li ion conductors, facilitating fast ionic mobility through the pure Li layer, which is known to result in a smaller experimentally observable quadrupolar coupling constant reduced by partial motional averaging^{15,111}. Li_3N is also known as a good Li ion conductor, but shows excellent agreement for C_Q simulated with CASTEP. Here we study the cubic, layered Li_3N phase, rather than one homologous to the hexagonal Li_3P and Li_3Sb , where Li ion mobility up to 300 K takes place predominantly within

the Li-pnictogen layer¹¹². Including the temperature-dependent influence of ionic mobility on the quadrupolar observables either via the vibrational modes¹¹³, via chemical exchange models¹⁵, or via molecular dynamics^{12,13,114,115} is beyond the scope of this study.

Even when neglecting the outliers, the correlation of the calculated C_Q and η with experimental values (Fig. 4 and 5 in light blue) exhibits a major, systematic overestimation of C_Q and distinct discrepancies of η by up to several orders of magnitude for unit cell simulations. CASTEP calculations with $2\times 2\times 2$ supercells confirm a significant supercell effect, especially for materials with small C_Q and small unit cells. The supercell effect converges rapidly with cell size as test calculations with $3\times 3\times 3$ supercells corroborate, showing convergence is already achieved for $2\times 2\times 2$. The effect might result from approximations in the charge augmentation of CASTEP that exceed their physical limit¹¹⁶ or from long range interactions not correctly captured by the approximations utilized in the PBC implementation. The supercell effect is not observable in Quantum ESPRESSO.

Despite the correction for the supercell effect by using $2\times 2\times 2$ cells, the CASTEP DFT calculations still feature a significant overestimation of C_Q by about 20% (12% without hex- Li_3Pn) with respect to experimental values. In principle, an inaccurate nuclear electric quadrupole moment Q for deriving C_Q from the DFT calculated EFG tensor could explain the discrepancy. However, this overestimation has been observed before²¹ for ${}^7\text{Li}$ as well as other light nuclei, and is usually attributed to a hypothesis formulated in the 1950s by Sternheimer^{117–119}, proposing that the polarization of the electronic K-shell induces a secondary quadrupolar moment that *shields* the nuclear electric quadrupole moment Q . This effect cannot be correctly reproduced within the PP approach. Therefore, the PP-GIPAW calculations tend to overestimate C_Q .

In contrast to ${}^{27}\text{Al}$, ${}^7\text{Li}$ is a second period element with only three electrons in total. The distinction between core and valence electrons becomes ambiguous for such small elements. The default PP of CASTEP (C19) and the one utilized for Quantum ESPRESSO in this work describe all three electrons explicitly as valence electrons. Nevertheless, there is still a core region defined by the core radius which is *pseudized*. The larger the core radius, the *softer* the PP and hence the less computationally demanding are the DFT calculations of the electronic structure, since they converge faster with respect to the number of plane waves. On the other hand, a smaller core radius makes the PP harder, potentially improves the description of the electron density in the vicinity of the core, and presumably is better able to capture the polarization near the nucleus. The impact of the core radius was tested for four Li salts by generating a set of modified pseudopotentials with different core radii¹²⁰. The comparison in Fig. 6 shows that reducing the size of the core region can trigger important changes in the predicted EFGs, lowering the calculated C_Q with only minor impact on η (c.f. Supplementary Information Fig. S2). Although these results can be interpreted as a reduction in the overestimation of C_Q , their reliability requires a more detailed investigation in the Discussion.



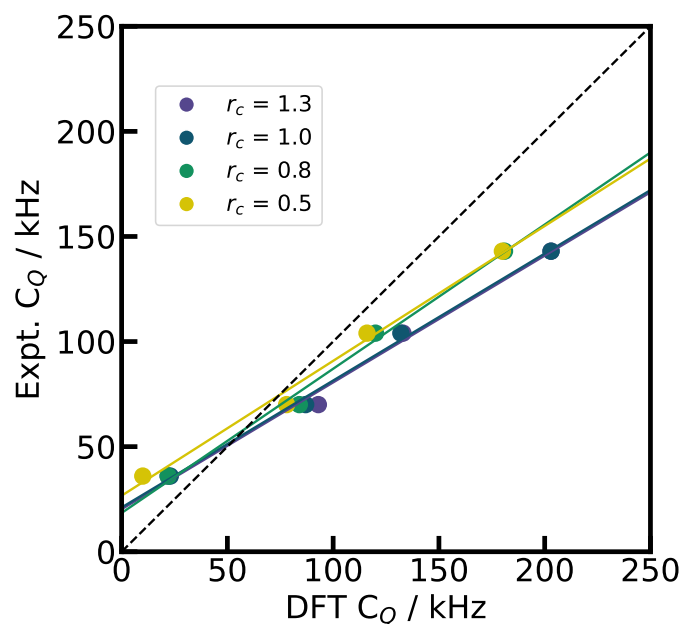


Fig. 6 Test with harder CASTEP PP. By changing the core radius r_c for the Li PP in CASTEP (default $r_c = 1.0$), we demonstrate the effect of a smaller Li pseudized core region on the simulated C_Q for four Li compounds (LiIO_3 ⁹⁶, Li_2CO_3 ²¹, $\text{Li}_2\text{B}_4\text{O}_7$ ⁸⁷, LiB_3O_5 ⁴¹), with PBE, fixed cell geometries, and supercells. The dashed diagonal line indicates the limit of ideal correlation.

For ^7Li , we could also find experimentally determined eigenvalues of the EFG tensors for $\text{Li}_2\text{B}_4\text{O}_7$, LiNbO_3 , $\text{LiCsB}_6\text{O}_{10}$ (**Group 1**) and LiB_3O_5 (**Group 2**)⁴¹ (c.f. Supplementary Information Tab. S5). Together with the principal components V_{ii} derived from the experimental C_Q and η , the correlation plot Fig. S4 (Supplementary Information) shows, that CASTEP is able to predict these quantities quite reliably. However, the systematic overestimation observed for C_Q is naturally reproduced by the notable overestimation of V_{zz} . But also V_{xx} and V_{yy} are overestimated, supporting the hypothesis of a shielded nuclear electric quadrupole moment, which does not become apparent in the η correlation in Fig. 5.

For LiB_3O_5 , LiNH_4SO_4 , and $\gamma\text{-LiAlO}_2$, the full experimental EFG tensors are available in literature^{41,42,97,109} (**Group 2**). Fig. 3 (blue and greens) shows the comparison of the series of tensors. The DFT simulations can reproduce the experimental values with a MAE of 15% of the experimental values, hence predicting the orientation of the EFG tensor with reasonable accuracy. Nevertheless, also for LiB_3O_5 , LiNH_4SO_4 , and $\gamma\text{-LiAlO}_2$, we observe the systematic overestimation of the magnitude C_Q as described before.

In contrast to ^{27}Al , the quadrupolar coupling of ^7Li proves to be more challenging to simulate reliably with CASTEP. Geometry relaxation and xc-functional once again do not show any significant impact as such, whereas the case of LiNH_4SO_4 demonstrates clearly the crucial importance of the correct representation of local atomistic structure and symmetry in particular on η . However, the CASTEP implementation of PBC does not prove to be robust to supercell effects, providing inaccurate results for

primitive unit cell simulations in particular for small C_Q values. Furthermore, the PP approximation appears to reach its limits for ^7Li , which presumably results in the systematic overestimation of C_Q for ^7Li . Nevertheless, considering the linear correlation between experiment and DFT calculated η values, the choice of approximations and computational schemes implemented in CASTEP performs quite well and predicts η with a MAE of 0.10 and a scaling factor of 0.80.

Quantum ESPRESSO and CASTEP are both PP-GIPAW, plane wave DFT codes, describing the electronic structure within the same basis based on the same physical picture and approximations. Our Quantum ESPRESSO simulations follow the workflow described for CASTEP as closely as possible. The xc-functional and the crystal geometries are identical, while the computational settings and convergence parameters are chosen to reflect the CASTEP ones as accurately as possible. While the results for ^{27}Al C_Q are almost identical between CASTEP and Quantum ESPRESSO (Fig. 1) and follow a comparable trend for ^{27}Al η (Fig. 2), ^7Li reveals major discrepancies.

The default GIPAW-PPs of CASTEP and Quantum ESPRESSO for Li and Al are based on the same assignment of core and valence electrons for each element. Nevertheless, other PP key values such as core radius, number and angular momentum of projectors, local and non-local channels as well as the parameterization are not comparable. For ^{27}Al , transferability between the codes does not suffer despite the different default PP. The smaller ^7Li on the other hand is more sensitive to modifications in the PP. Moreover, the sizable supercell effect demonstrated for ^7Li in CASTEP, which is not detectable in Quantum ESPRESSO, proves that the implementations though based on the same physical descriptions are distinctly different. In order to get comparable accuracy and reliability for ^7Li EFG calculations in Quantum ESPRESSO, a similar, detailed testing and workflow optimization as described above for CASTEP is necessary but beyond the scope of this work. It is just important to stress that simulation strategies and workflows cannot necessarily be transferred between codes, even if they are based on the same physical principles.

4 Discussion

In recent decades, the PP-GIPAW method has established itself as the standard method for calculating NMR properties for crystalline solid state materials ranging from CSA, indirect spin-spin coupling to quadrupolar coupling^{121–123}. At first glance, the PP approximation of the electron density in the core region by an effective core potential appears counterintuitive for simulating interactions of nuclear spin with its environment. However, the reconstruction of the all-electron electron density from the converged, pseudized electron density with the GIPAW method has proven to be an efficient and reliable approach to predict nuclear interactions with robust accuracy for a wide range of materials^{124,125}.

Our results for ^{27}Al C_Q quadrupolar observables and their excellent agreement with experimental references confirm the PP-GIPAW method as a powerful tool for EFG predictions, supporting NMR crystallography as has been shown before¹²⁶. While



^{27}Al is one of the most commonly studied quadrupolar nuclei in SS-NMR and well described in the PP picture, our literature survey confirms, that ^7Li is not as widely studied and challenges the PP approximation. On the one hand, previous benchmarking has shown accurate predictions of ^7Li chemical shifts with PP-GIPAW methods¹⁵. On the other hand, the EFG tensor is highly sensitive to small changes and aspherical asymmetries of the electron density near the nucleus¹, since it depends with r^{-3} on the charge distribution and its symmetry¹⁷. Furthermore, it is known that the polarization of the K-shell electrons in a magnetic field induces a local quadrupolar moment, which counteracts the nuclear electric quadrupole moment Q and yields a reduced effective quadrupole moment^{117–119}. The K-shell polarization is most pronounced for first and second period elements. In addition, elements on the left side of the periodic table have been reported to struggle with a precise representation of shallow core states in the plane wave basis, where electrons of the shell below the valence shell ($n - 1$) have semi-core character and need to be described as quasi-valence electrons¹.

Several examples show that PP-GIPAW predictions of C_Q for ^7Li and other light nuclei^{29,127} suffer from a systematic overestimation²¹. Our simulations exceed the experimental C_Q by about 20% (12% without hex-Li₃Pn) on average, which is well in line with reported overestimation factors for ^7Li of 1.20²¹, 1.15¹²⁷, and 1.11¹¹⁸.

Specific modifications of the Li PP and CASTEP test calculations with harder PPs support the hypothesis that the systematic overestimation for ^7Li C_Q might originate from the inadequate description of the K-shell polarization and/or the semi-core states in the default PP picture. However, harder PPs require much larger plane wave basis sets for convergence and hence increase the computational cost by orders of magnitude. Moreover, development of reliable, transferable, robust, and versatile PPs is an art in itself. Our test Li PPs have not been optimized or tested beyond their convergence with cut-off energy and they have not been benchmarked against other properties such as energies, forces, or band structure, not even against other NMR parameters, e.g. CSA. The harder Li PPs with smaller core regions have only been used to test the hypothesis that a better, i.e. explicit treatment of the electron density close to the nucleus improves the agreement of simulated C_Q with experimental values. Modifying PPs to improve agreement with experimental reference values is strongly discouraged, even if it can be physically justified. Instead, linear correlation relationships offer a viable and robust tool to translate between DFT simulated quadrupolar couplings and experimental observables, which is both computationally efficient and transferable to other systems within the limits of the applied methods, settings, and parameters.

The strong sensitivity of the EFG tensor to the local charge distribution is not only expressed in the significance of K-shell polarization and semi-core states, but also in any factor that potentially impacts the accuracy of DFT-derived electronic

densities. Several of these factors are computational parameters, which can be converged, such as basis set size, k-point grid, integration grid, convergence threshold etc, and are not discussed here. More general computational settings, which cannot be converged, include xc-functional, crystal geometry, and supercell effects. In order to establish a robust and reliable linear interpolation scheme, these factors need to be studied.

For ionic, diamagnetic ^{27}Al and ^7Li compounds, we could show, that the xc-functional and geometry relaxation have only minor significance and can be disregarded. However, this observation cannot be generalized. Compounds and elements with more covalent type binding character, hydrogen bonds, or π -orbital interactions might not be adequately represented by LDA or GGA but might benefit from hybrid xc-functionals. Naturally, crystal geometry and the local atomic environment has a major impact on the electron density throughout the material as well as close to nuclei. The observed, negligible impact of geometry relaxation arises from the very accurate, experimental crystal structures, where additional first-principles relaxations do not show any major change in atomic coordinates anyway. The most notable exceptions are materials containing hydrogen, such as LiNH_4SO_4 , since H does not scatter very well and its position cannot be determined reliably with XRD. Hence, **fixed cell** optimizations have been reported to improve prediction accuracy of DFT-derived NMR properties¹⁰⁵.

The supercell effect, which we have introduced above, is a collective term comprising any change in the computed property by simulating supercells or conventional instead of primitive unit cells. Supercell effects might arise from the implementation of integration grids, the treatment of crystal symmetry¹⁵, charge augmentations¹¹⁶, or any physical approximations applied in the PBC, which might be stretched beyond their limits of validity. Besides, supercell effects might only affect certain elements (e.g. light elements), certain crystal symmetries (e.g. hexagonal) or cells (e.g. small unit cells). Therefore, testing for supercell effects is expedient to rule out any obscure inconsistencies between simulation and experiment.

In general, the PP-GIPAW method is verified as a powerful tool for simulating EFG tensors and quadrupolar observables in periodic solids as demonstrated by the good accuracy of the predicted EFG tensor orientations with respect to the crystal lattice. Even for challenging nuclei such as ^7Li , the PP approach can be successfully applied, if certain measures are taken. With careful benchmarking of the nucleus and material class of interest, a transferable interpolation scheme has to be derived, which is only valid for the specified set of method (i.e. software), settings (i.e. xc, basis set and k-point grid convergence), and approximations (i.e. PP, PBC), but can then be utilized for production calculations of unknown, more complex materials.

5 Conclusion

The performance and accuracy of the plane wave PP-GIPAW DFT method for computing quadrupolar couplings has been bench-



marked before^{31,128}, even specifically for ²⁷Al^{1,107}. In this work, we focus on the less well-studied quadrupolar nucleus ⁷Li and compare it with the widely known ²⁷Al, including a comprehensive literature survey and summary of the available experimental data. To the best of our knowledge, we report the first EFG reference scale for ⁷Li.

We evaluate the performance of the plane wave PP-GIPAW DFT method, using CASTEP and Quantum ESPRESSO, and investigate not only the magnitude of the quadrupolar coupling C_Q , but also the shape of the EFG tensor η as well as its orientation given by the experimental direction cosines. Testing the impact of xc-functional, structure relaxation, PP, and supercell effects on the accuracy of the theoretical prediction, the simulations prove to be robust and reliable for ²⁷Al. ⁷Li however exceeds the limits of the PP approximation and shows considerable supercell effects in CASTEP. Based on benchmarking well-known reference substances, we propose practical guidelines for establishing a transferable linear correlation scheme for challenging nuclei such as ⁷Li, which can then be applied to translate between theoretical simulations and experimental results of unknown, complex materials. Using this in depth scrutinised and optimized linear correlation scheme, the simulated C_Q and η for both ⁷Li and ²⁷Al are in good agreement with experiment with an average error on the order of 10% to 20%, while the accuracy of the predicted tensor orientation is excellent.

The PP-GIPAW method competes with all-electron methods, which avoid the PP approximation but are technically more complex for periodic systems and computationally more expensive^{3,17}. More recently, solid state cluster embedding methods^{129–132} have been developed for NMR properties, which describe the immediate environment of the nucleus of interest at all-electron level and embed it in layered shells of classical molecular mechanics and point charges to mimic the long range interactions of a bulk material. While methodologically rather complex, the embedding method is very promising, especially for aperiodicities such as defects or disorder and for amorphous solid phases.

Author Contributions

Javier Valenzuela Reina: Investigation, Methodology, Writing - Original Draft, Data Curation

Federico Civaia: Writing - Original Draft, Writing - review and editing

Angela F. Harper: Supervision, Visualization

Christoph Scheurer: Conceptualization, Funding acquisition, Supervision

Simone S. Köcher: Conceptualization, Supervision, Writing - Original Draft, Writing - review and editing

Conflicts of Interest

There are no conflicts to declare.

Acknowledgements

All the authors would like to thank Prof. Chris Pickard, Prof. Jonathan Yates, Dr. Philipp Schleker, and Prof. Dr. Josef Granwehr for scientific exchange and valuable discussions. We

finally gratefully acknowledge the computational and data resources provided by the Max Planck Computing and Data Facility (MPCDF). AFH would like to acknowledge the support of the Alexander von Humboldt Foundation. JV acknowledges funding by the Bundesministerium für Bildung und Forschung (BMBF) within the Verbundprojekt AdamBatt (FKZ: 03XP0305D). FC and CS would like to acknowledge funding by the Deutsche Forschungsgemeinschaft (DFG, German Research Foundation) within the cluster of excellence EXC 2089: e-conversion.

References

- 1 P. Blaha, K. Schwarz, F. Tran, R. Laskowski, G. K. H. Madsen and L. D. Marks, *J. Chem. Phys.*, 2020, **152**, 074101.
- 2 M. Profeta, F. Mauri and C. J. Pickard, *J. Am. Chem. Soc.*, 2003, **125**, 541–548.
- 3 P. Blaha, K. Schwarz and P. Herzig, *Phys. Rev. Lett.*, 1985, **54**, 1192–1195.
- 4 A. R. Ferreira, K. Reuter and C. Scheurer, *RSC Adv.*, 2016, **6**, 41015–41024.
- 5 R. Böhmer, K. R. Jeffrey and M. Vogel, *Prog. Nucl. Magn. Res. Sp.*, 2007, **50**, 87–174.
- 6 B. Reif, S. E. Ashbrook, L. Emsley and M. Hong, *Nature Reviews Methods Primers*, 2021, **1**, 2.
- 7 L. A. O'Dell and C. I. Ratcliffe, in *NMR of Quadrupolar Nuclei in Solid Materials*, ed. R. E. Wasylshen, S. E. Ashbrook and S. Wimperis, Wiley, Hoboken, NJ, 1st edn., 2012, pp. 213–232.
- 8 S. E. Ashbrook and D. McKay, *Chem. Commun.*, 2016, **52**, 7186–7204.
- 9 R. K. Harris, P. Hodgkinson, C. J. Pickard, J. R. Yates and V. Zorin, *Magnetic Resonance in Chemistry*, 2007, **45**, S174–S186.
- 10 C. Bonhomme, C. Gervais, F. Babonneau, C. Coelho, F. Pourpoint, T. Azais, S. E. Ashbrook, J. M. Griffin, J. R. Yates, F. Mauri and C. J. Pickard, *Chem. Rev.*, 2012, **112**, 5733–5779.
- 11 M. C. Venetos, M. Wen and K. A. Persson, *J. Phys. Chem. A*, 2023, **127**, 2388–2398.
- 12 A. F. Harper, S. P. Emge, P. C. Magusin, C. P. Grey and A. J. Morris, *Chemical Science*, 2023, **14**, 1155–1167.
- 13 I. Chubak, L. Scaffi, A. Carof and B. Rotenberg, *Journal of Chemical Theory and Computation*, 2021, **17**, 6006–6017.
- 14 S. A. Southern and D. L. Bryce, *Annual Reports on NMR Spectroscopy*, 2021, **102**, 1–80.
- 15 S. Köcher, P. Schleker, M. Graf, R.-A. Eichel, K. Reuter, J. Granwehr and C. Scheurer, *J. Magn. Reson.*, 2018, **297**, 33–41.
- 16 C. P. Grey and N. Dupré, *Chem. Rev.*, 2004, **104**, 4493–4512.
- 17 J. W. Zwanziger, in *NMR of Quadrupolar Nuclei in Solid Materials*, ed. R. E. Wasylshen, S. E. Ashbrook and S. Wimperis, Wiley, Hoboken, NJ, 1st edn., 2012, pp. 199–209.
- 18 W. Kutzelnigg, *Calculation of NMR and EPR Parameters: Theory and Applications*, 2004, 43–82.
- 19 W. Kutzelnigg, *Isr. J. Chem.*, 1980, **19**, 193–200.



- 20 W. Kutzelnigg, U. Fleischer and M. Schindler, in *Deuterium and Shift Calculation*, Springer, Berlin, 1990, vol. 23 of NMR Basic Principles and Progress.
- 21 M. T. Dunstan, J. M. Griffin, F. Blanc, M. Leskes and C. P. Grey, *The Journal of Physical Chemistry C*, 2015, **119**, 24255–24264.
- 22 S. E. Ashbrook and S. Sneddon, *J. Am. Chem. Soc.*, 2014, **136**, 15440–15456.
- 23 J. R. Yates and C. J. Pickard, in *eMagRes*, John Wiley & Sons Ltd, 2007.
- 24 M. M. Islam and T. Bredow, *J. Phys. Chem. C*, 2016, **120**, 7061–7066.
- 25 F. A. Perras and D. L. Bryce, *The Journal of Physical Chemistry C*, 2012, **116**, 19472–19482.
- 26 F. A. Perras, I. Korobkov and D. L. Bryce, *CrystEngComm*, 2013, **15**, 8727–8738.
- 27 S. T. Holmes and R. W. Schurko, *The Journal of Physical Chemistry C*, 2018, **122**, 1809–1820.
- 28 S. T. Holmes, C. S. Vojvodin and R. W. Schurko, *The Journal of Physical Chemistry A*, 2020, **124**, 10312–10323.
- 29 J. M. Griffin, A. J. Miller, A. J. Berry, S. Wimperis and S. E. Ashbrook, *Phys. Chem. Chem. Phys.*, 2010, **12**, 2989–2998.
- 30 J. M. Griffin, L. Clark, V. R. Seymour, D. W. Aldous, D. M. Dawson, D. Iuga, R. E. Morris and S. E. Ashbrook, *Chem. Sci.*, 2012, **3**, 2293–2300.
- 31 S. E. Ashbrook, L. L. Pollès, C. J. Pickard, A. J. Berry, S. Wimperis and I. Farnan, *Phys. Chem. Chem. Phys.*, 2007, **9**, 1587–1598.
- 32 S. Stegmaier, R. Schierholz, I. Povstugar, J. Barthel, S. P. Rittmeyer, S. Yu, S. Wengert, S. Rostami, H. Kungl, K. Reuter *et al.*, *Advanced Energy Materials*, 2021, **11**, 2100707.
- 33 J. C. Bachman, S. Muy, A. Grimaud, H.-H. Chang, N. Pour, S. F. Lux, O. Paschos, F. Maglia, S. Lupart, P. Lamp, L. Giordano and Y. Shao-Horn, *Chemical Reviews*, 2016, **116**, 140–162.
- 34 F. Blanc, L. Spencer and G. R. Goward, in *NMR of Quadrupolar Nuclei in Solid Materials*, ed. R. E. Wasylshen, S. E. Ashbrook and S. Wimperis, Wiley, Hoboken, NJ, 1st edn., 2012.
- 35 J. Cuny, J. Yates, R. Gautier, E. Furet, E. Le Fur and L. Le Pollès, *Magnetic Resonance in Chemistry*, 2010, **48**, S171–S175.
- 36 P. P. Man, in *Encyclopedia of Nuclear Magnetic Resonance*, ed. D. M. Grant and R. K. Harris, J. Wiley, Chichester, 1996, pp. 3838–3848.
- 37 J. D. Memory, *Quantum theory of magnetic resonance parameters*, McGraw-Hill, New York, 1968.
- 38 P. Schwerdtfeger, M. Pernpointner and W. Nazarewicz, in *Calculation of NMR and EPR parameters*, ed. M. Kaupp, M. Bühl and V. G. Malkin, Wiley-VCH, Weinheim, 1st edn., 2004, pp. 279–289.
- 39 K. Schmidt-Rohr and H. W. Spiess, in *Multidimensional solid state NMR and polymers*, Acad. Press, London, 1st edn., 1994, pp. 18–21.
- 40 A. Abragam, *The Principles of Nuclear Magnetism*, Oxford University Press, Oxford, 1st edn., 1961.
- 41 A. R. Lim, J. W. Kim and C. S. Yoon, *Journal of Applied Physics*, 2003, **94**, 5095–5099.
- 42 A. Lim, S.-E. Park and S.-Y. Jeong, *Solid State Communications*, 2000, **113**, 389–394.
- 43 S. S. Hafner, M. Raymond and S. Ghose, *The Journal of Chemical Physics*, 1970, **52**, 6037–6041.
- 44 R. K. Harris, E. D. Becker, S. M. Cabral de Menezes, P. Granger, R. E. Hoffman and K. W. Zilm, *Pure Appl. Chem.*, 2008, **80**, 59–84.
- 45 M. H. Levitt, *Spin Dynamics*, John Wiley & Sons, 2008.
- 46 M. Karplus, *The Journal of Chemical Physics*, 1959, **30**, 11–15.
- 47 M. Karplus, *J. Am. Chem. Soc.*, 1963, **85**, 2870–2871.
- 48 D. M. Grant and E. G. Paul, *J. Am. Chem. Soc.*, 1964, **86**, 2984–2990.
- 49 L. P. Lindeman and J. Q. Adama, *Anal. Chem.*, 1971, **43**, 1245–1252.
- 50 W. Bremser, *Analytica Chimica Acta*, 1978, **103**, 355–365.
- 51 A. Ejchart, 1980, **13**, 368–371.
- 52 Y. A. Shahab and H. A. Al-Wahab, *J. Chem. Soc., Perkin Trans. 2*, 1988, 255–256.
- 53 M. Schindler and W. Kutzelnigg, *J. Chem. Phys.*, 1982, **76**, 1919–1933.
- 54 M. Schindler and W. Kutzelnigg, *J. Am. Chem. Soc.*, 1983, **105**, 1360–1370.
- 55 F. Bloch, *Z. Phys.*, 1929, **52**, 555–600.
- 56 L. Kleinman and D. M. Bylander, *Phys. Rev. Lett.*, 1982, **48**, 1425–1428.
- 57 D. Vanderbilt, *Phys. Rev. B*, 1990, **41**, 7892–7895.
- 58 P. E. Blöchl, *Phys. Rev. B*, 1994, **50**, 17953–17979.
- 59 T. Charpentier, *Solid State Nucl. Magn. Reson.*, 2011, **40**, 1–20.
- 60 F. Vasconcelos, S. Cristol, J.-F. Paul, L. Montagne, F. Mauri and L. Delevoye, *Magnetic Resonance in Chemistry*, 2010, **48**, S142–S150.
- 61 M. Body, C. Legein, J.-Y. Buzaré, G. Silly, P. Blaha, C. Martineau and F. Calvayrac, *J. Phys. Chem. A*, 2007, **111**, 11873–11884.
- 62 F. Tran and P. Blaha, *Phys. Rev. B*, 2011, **83**, 235118.
- 63 F. Tran, S. Ehsan and P. Blaha, *Phys. Rev. Mater.*, 2018, **2**, 023802.
- 64 R. Laskowski, P. Blaha and F. Tran, *Phys. Rev. B*, 2013, **87**, 195130.
- 65 W. Kohn and L. J. Sham, *Phys. Rev.*, 1965, **140**, A1133–A1138.
- 66 J. P. Perdew, K. Burke and M. Ernzerhof, *Phys. Rev. Lett.*, 1996, **77**, 3865–3868.
- 67 J. P. Perdew, A. Ruzsinszky, G. I. Csonka, O. A. Vydrov, G. E. Scuseria, L. A. Constantin, X. Zhou and K. Burke, *Phys. Rev. Lett.*, 2008, **100**, 136406.
- 68 J. P. Perdew, J. A. Chevary, S. H. Vosko, K. A. Jackson, M. R. Pederson, D. J. Singh and C. Fiolhais, *Phys. Rev. B*, 1992, **46**, 6671–6687.
- 69 A. P. Bartók and J. R. Yates, *The Journal of Chemical Physics*,



- 2019, **150**, 161101.
- 70 C. Leroy, P. M. Szell and D. L. Bryce, *Magnetic Resonance in Chemistry*, 2019, **57**, 265–267.
- 71 Y. Zhang, S. Mukherjee and E. Oldfield, *Journal of the American Chemical Society*, 2005, **127**, 2370–2371.
- 72 P. Pyykkö, *Molecular Physics*, 2008, **106**, 1965–1974.
- 73 P. Pyykkö, *Molecular Physics*, 2018, **116**, 1328–1338.
- 74 A. Jain, S. P. Ong, G. Hautier, W. Chen, W. D. Richards, S. Dacek, S. Cholia, D. Gunter, D. Skinner, G. Ceder and K. A. Persson, *APL Materials*, 2013, **1**,.
- 75 C. R. Groom, I. J. Bruno, M. P. Lightfoot and S. C. Ward, *Acta Crystallographica Section B Structural Science, Crystal Engineering and Materials*, 2016, **72**, 171–179.
- 76 T. Bräuniger, C. Chandran, U. Wedig and M. Jansen, *Zeitschrift für anorganische und allgemeine Chemie*, 2011, **637**, 530–535.
- 77 D. Müller, E. Jahn, G. Ladwig and U. Haubenreisser, *Chemical Physics Letters*, 1984, **109**, 332–336.
- 78 C. V. Chandran, C. E. A. Kirschhock, S. Radhakrishnan, F. Taulelle, J. A. Martens and E. Breynaert, *Chemical Society Reviews*, 2019, **48**, 134–156.
- 79 U. G. Nielsen, A. Boisen, M. Brorson, C. J. H. Jacobsen, H. J. Jakobsen and J. Skibsted, *Inorganic Chemistry*, 2002, **41**, 6432–6439.
- 80 J. Skibsted, E. Henderson and H. J. Jakobsen, *Inorganic Chemistry*, 1993, **32**, 1013–1027.
- 81 B. Ollivier, R. Retoux, P. Lacorre, D. Massiot and G. Férey, *Journal of Materials Chemistry*, 1997, **7**, 1049–1056.
- 82 R. C. L. Mooney, *Acta Crystallographica*, 1956, **9**, 728–734.
- 83 Y. Muraoka and K. Kihara, *Physics and Chemistry of Minerals*, 1997, **24**, 243–253.
- 84 C. Jacoboni, A. Leble and J. Rousseau, *Journal of Solid State Chemistry*, 1981, **36**, 297–304.
- 85 T. M. Gesing and W. Jeitschko, *Zeitschrift für Naturforschung B*, 1995, **50**, 196–200.
- 86 A. R. Lim, K. S. Hong, S. H. Choh and S.-Y. Jeong, *Solid State Communications*, 1997, **103**, 693–698.
- 87 A. R. Lim and I. G. Kim, *Solid State Nucl. Magn. Reson.*, 2015, **66-67**, 40–44.
- 88 M. Leskes, N. E. Drewett, L. J. Hardwick, P. G. Bruce, G. R. Goward and C. P. Grey, *Angewandte Chemie International Edition*, 2012, **51**, 8560–8563.
- 89 E. Witt, C. V. Chandran and P. Heitjans, *Solid State Ionics*, 2017, **304**, 60–64.
- 90 G. W. Ossman and A. A. Silvidi, *The Journal of Chemical Physics*, 1971, **54**, 979–982.
- 91 O. E. O. Zeman, I. L. Moudrakovski, C. Hartmann, S. Indris and T. Bräuniger, *Molecules*, 2020, **25**, 469.
- 92 H. Maekawa, S. Kato, K. Kawamura and T. Yokokawa, *American Mineralogist*, 1997, **82**, 1125–1132.
- 93 H. Eckert, Z. Zhang and J. H. Kennedy, *Chemistry of Materials*, 1990, **2**, 273–279.
- 94 T. K. Halstead, *The Journal of Chemical Physics*, 1970, **53**, 3427–3435.
- 95 A. R. Lim, J. W. Kim and C. S. Yoon, *Solid State Communications*, 2002, **123**, 505–510.
- 96 T. Minamisono, T. Ohtsubo, Y. Nakayama, S. Fukuda, T. Izumikawa, M. Tanigaki, M. Matsui, S. Takeda, N. Nakamura, M. Fukuda, K. Matsuta and Y. Nojiri, *Hyperfine Interactions*, 1993, **78**, 159–163.
- 97 S. Indris, P. Heitjans, R. Uecker and T. Bredow, *Physical Review B*, 2006, **74**, 245120.
- 98 L. O'Dell, S. Savin, A. Chadwick and M. Smith, *Solid State Nuclear Magnetic Resonance*, 2007, **31**, 169–173.
- 99 S. J. Clark, M. D. Segall, C. J. Pickard, P. J. Hasnip, M. I. J. Probert, K. Refson and M. C. Payne, *Zeitschrift für Kristallographie - Crystalline Materials*, 2005, **220**, 567–570.
- 100 S. Sturniolo, T. F. G. Green, R. M. Hanson, M. Zilka, K. Refson, P. Hodgkinson, S. P. Brown and J. R. Yates, *Solid State Nuclear Magnetic Resonance*, 2016, **78**, 64–70.
- 101 P. Giannozzi, O. Andreussi, T. Brumme, O. Bunau, M. B. Nardelli, M. Calandra, R. Car, C. Cavazzoni, D. Ceresoli, M. Cococcioni, N. Colonna, I. Carnimeo, A. D. Corso, S. de Gironcoli, P. Delugas, R. A. D. Jr, A. Ferretti, A. Floris, G. Fratesi, G. Fugallo, R. Gebauer, U. Gerstmann, F. Giustino, T. Gorni, J. Jia, M. Kawamura, H.-Y. Ko, A. Kokalj, E. Küçükbenli, M. Lazzeri, M. Marsili, N. Marzari, F. Mauri, N. L. Nguyen, H.-V. Nguyen, A. O. de-la Roza, L. Paulatto, S. Poncé, D. Rocca, R. Sabatini, B. Santra, M. Schlipf, A. P. Seitsonen, A. Smogunov, I. Timrov, T. Thonhauser, P. Umari, N. Vast, X. Wu and S. Baroni, *Journal of Physics: Condensed Matter*, 2017, **29**, 465901.
- 102 D. Freude and J. Haase, *Survey of NMR Parameters for Quadrupolar Nuclei in Powder Materials, in Particular for 27Al, 23Na and 17O*, 2019, <https://dieter-freude.de/quad-nmr/8.pdf>.
- 103 N. Wiberg, A. F. Holleman, E. Wiberg and G. Fischer, *Lehrbuch der Anorganischen Chemie*, De Gruyter, Berlin New York, 102nd edn., 2007.
- 104 P. Haas, F. Tran and P. Blaha, *Phys. Rev. B*, 2009, **79**, 085104.
- 105 R. K. Harris, E. D. Becker, S. M. C. De Menezes, P. Granger, R. E. Hoffman and K. W. Zilm, *Magnetic Resonance in Chemistry*, 2008, **46**, 582–598.
- 106 W. Ku, T. Berlijn and C.-C. Lee, *Physical Review Letters*, 2010, **104**,.
- 107 R. Lizárraga, E. Holmström, S. C. Parker and C. Arrouvel, *Phys. Rev. B*, 2011, **83**, 094201.
- 108 T. Vosegaard, *Progress in Nuclear Magnetic Resonance Spectroscopy*, 2021, **123**, 51–72.
- 109 T. Bräuniger, B. Groh, I. L. Moudrakovski and S. Indris, *The Journal of Physical Chemistry A*, 2016, **120**, 7839–7846.
- 110 X. Li, M. Tang, X. Feng, I. Hung, A. Rose, P.-H. Chien, Z. Gan and Y.-Y. Hu, *Chemistry of Materials*, 2017, **29**, 8282–8291.
- 111 M. F. Graf, H. Tempel, S. S. Köcher, R. Schierholz, C. Scheurer, H. Kungl, R.-A. Eichel and J. Granwehr, *RSC Adv.*, 2017, **7**, 25276–25284.
- 112 R. Messer, H. Birli and K. Differt, *Le Journal de Physique Colloques*, 1980, **41**, C6–28–C6–31.



- 113 B. Monserrat, R. J. Needs and C. J. Pickard, *The Journal of Chemical Physics*, 2014, **141**, 134113.
- 114 A. H. Mazurek, Ł. Szeleszczuk and D. M. Pisklak, *International Journal of Molecular Sciences*, 2021, **22**, 4378.
- 115 C. Lei, A. Erlebach, F. Brivio, L. Grajciar, Z. Tošner, C. J. Heard and P. Nachtigall, *Chemical Science*, 2023, **14**, 9101–9113.
- 116 J. Yates, personal communication, 2023.
- 117 R. Sternheimer, *Phys. Rev.*, 1950, **80**, 102–103.
- 118 R. Sternheimer, *Phys. Rev.*, 1951, **84**, 244–253.
- 119 T. P. Das, *Phys. Rev.*, 1956, **102**, 733–738.
- 120 C. Pickard, personal communication, 2023.
- 121 S. E. Ashbrook, L. Le Pollès, R. Gautier, C. J. Pickard and R. I. Walton, *Phys. Chem. Chem. Phys.*, 2006, **8**, 3423–3431.
- 122 S. Sen, *Molecular Simulation*, 2008, **34**, 1115–1120.
- 123 F. Pourpoint, C. Gervais, L. Bonhomme-Coury, F. Mauri, B. Alonso and C. Bonhomme, *Comptes Rendus. Chimie*, 2007, **11**, 398–406.
- 124 J. D. Hartman, A. Mathews and J. K. Harper, *Frontiers in Chemistry*, 2021, **9**.
- 125 D. V. Dudenko, J. R. Yates, K. D. M. Harris and S. P. Brown, *CrystEngComm*, 2013, **15**, 8797.
- 126 B. Karasulu, S. P. Emge, M. F. Groh, C. P. Grey and A. J. Morris, *Journal of the American Chemical Society*, 2020, **142**, 3132–3148.
- 127 G. S. Harbison, *Journal of Magnetic Resonance*, 2015, **257**, 24–31.
- 128 K. Choudhary, J. N. Ansari, I. I. Mazin and K. L. Sauer, *Sci Data*, 2020, **7**, 362.
- 129 A. Dittmer, G. L. Stoychev, D. Maganas, A. A. Auer and F. Neese, *J. Chem. Theory Comput.*, 2020, **16**, 6950–6967.
- 130 M. Kick and H. Oberhofer, *The Journal of Chemical Physics*, 2019, **151**, 184114.
- 131 D. Berger, H. Oberhofer and K. Reuter, *Phys. Rev. B*, 2015, **92**, 075308.
- 132 D. Berger, A. J. Logsdail, H. Oberhofer, M. R. Farrow, C. R. A. Catlow, P. Sherwood, A. A. Sokol, V. Blum and K. Reuter, *The Journal of Chemical Physics*, 2014, **141**, 024105.
- 133 D. Ceresoli, Davide Ceresoli - Pseudopotentials, 2024, <https://sites.google.com/site/dceresoli/pseudopotentials>.
- 134 D. Müller, W. Gessner, A. Samoson, E. Lippmaa and G. Scheler, *J. Chem. Soc., Dalton Trans.*, 1986, 1277–1281.
- 135 D. Müller, E. Jahn, G. Ladwig and U. Haubenreisser, *Chemical Physics Letters*, 1984, **109**, 332–336.
- 136 B. Zhou, B. L. Sherriff, J. S. Hartman and G. Wu, *American Mineralogist*, 2007, **92**, 34–43.
- 137 J. F. Hon and P. J. Bray, *Phys. Rev.*, 1958, **110**, 624–629.
- 138 G. E. Peterson, P. M. Bridenbaugh and P. Green, *The Journal of Chemical Physics*, 1967, **46**, 4009–4014.
- 139 M. A. Pimenta, P. Echegut, Y. Luspín, G. Hauret, F. Gervais and P. Abélard, *Physical Review B*, 1989, **39**, 3361–3368.
- 140 A. R. Lim, S. H. Choh and S. Y. Jeong, *Journal of Physics: Condensed Matter*, 1996, **8**, 4597–4602.
- 141 K. Arbi, J. Rojo and J. Sanz, *Journal of the European Ceramic Society*, 2007, **27**, 4215–4218.

