

Composition, structure, and stability of RuO₂(110) as a function of oxygen pressure

Karsten Reuter and Matthias Scheffler

Fritz-Haber-Institut der Max-Planck-Gesellschaft, Faradayweg 4-6, D-14195 Berlin-Dahlem, Germany

(Received 11 July 2001; published 19 December 2001)

Using density-functional theory we calculate the Gibbs free energy to determine the lowest-energy structure of a RuO₂(110) surface in thermodynamic equilibrium with an oxygen-rich environment. The traditionally assumed stoichiometric termination is only found to be favorable at low oxygen chemical potentials, i.e., low pressures and/or high temperatures. At a realistic O pressure, the surface is predicted to contain additional terminal O atoms. Although this O excess defines a so-called polar surface, we show that the prevalent ionic model, that dismisses such terminations on electrostatic grounds, is of little validity for RuO₂(110). Together with analogous results obtained previously at the (0001) surface of corundum-structured oxides, these findings on (110) rutile indicate that the stability of nonstoichiometric terminations is a more general phenomenon of transition metal oxide surfaces.

DOI: 10.1103/PhysRevB.65.035406

PACS number(s): 68.47.Gh, 05.70.Np, 71.15.Mb

I. INTRODUCTION

Density-functional theory (DFT) is often argued to be a zero-temperature, zero-pressure technique. As such, the results of static total-energy calculations at surfaces have to be transferred with considerable care to typical high-pressure applications such as catalysis—a situation which finds its correspondence in the experiment in form of the *ex situ* methods of ultrahigh-vacuum (UHV) surface science. Unfortunately, extrapolation of the low-pressure results to technical processes taking place at ambient atmosphere is often not possible, which has been coined with buzz words like *pressure* and *materials gap* (see, e.g., the discussion in Stampfl *et al.*¹ and references therein).

Trying to bridge these gaps, one needs to determine the equilibrium composition and geometry of a surface in contact with a given environment at finite temperature and pressure. Under these conditions the stable surface structure is a result of the statistical average of adsorption and desorption processes, and hence an analysis based on thermodynamics must be employed. When we aim to describe experiments that are conducted at constant pressure and temperature, the appropriate thermodynamic potential to consider is the Gibbs free energy $G(T,p)$. If DFT total energies enter in a suitable way into a calculation of $G(T,p)$ for a material surface, *ab initio thermodynamics* is the result, and the predictive power of the first-principles technique is extended to a more relevant temperature and pressure range.

This scheme has been successfully applied to, e.g., address the surface termination of corundum-type oxide structures,^{2,3} and we will use it here to determine the composition and lowest energy structure of RuO₂(110) in equilibrium with an oxygen atmosphere. In theoretical investigations of oxide surfaces, typically only stoichiometric terminations are considered,^{4,5} because they are believed to be more favorable than the other, so-called polar terminations⁶ for two reasons: First, they often involve a minimum of truncated bonds at the surface, and second, in a purely electrostatic model in which all oxide ions would be in their bulk formal oxidation state, polar surfaces would be charged and should thus exhibit an infinite surface energy.

In contrast to these arguments, our *ab initio thermodynamics* calculations show that on RuO₂(110) a polar surface termination with excess oxygen atoms is stabilized at higher O chemical potentials. Hence, depending on the experimental conditions, either the stoichiometric UHV or the hitherto unaccounted for high-pressure termination can be present. Both cases must be considered in the modeling of physical processes such as catalytic reactions occurring at this surface. We will also show that the rejection of polar surfaces on electrostatic grounds is not valid, as the strong dipole moment can be considerably reduced by surface relaxation and electron rearrangement. Rather than conceptualizing the surface as created simply by a given slice plane through the bulk stacking sequence (which is the basis of the electrostatic divergence argument), one should instead view the surface as a material in which the structural and electronic degrees of freedom of the top atomic layers allow a significant modification of the bulk properties of the atoms. These results for the rutile-structured RuO₂(110) are analogous to previous findings at the (0001) surface of corundum-type oxide structures,^{2,3} supporting the argument that polar terminations, particularly at realistic pressure, are a more general phenomenon of transition-metal-oxide surfaces.

II. THEORY

This section describes the thermodynamic formalism and how it is combined with DFT total-energy calculations. For the sake of clarity this discussion is referenced explicitly to the present application to RuO₂(110) in an oxygen atmosphere. However, the generalization to other compounds, M_xO_y , and even to an environment that contains multiple gas-phase species and not just oxygen, is obvious.

A. Surface free energy

We consider a surface in contact with an oxygen atmosphere described by an oxygen pressure p and temperature T . This means that the environment acts as a reservoir, because it can give (or take) any amount of oxygen to (or from) the sample without changing the temperature or pressure. The

appropriate thermodynamic potential required to describe such a system is the Gibbs free energy $G(T, p, N_{\text{Ru}}, N_{\text{O}})$, which also depends on the number of Ru, N_{Ru} , and O, N_{O} , atoms in the sample. The most stable surface composition and geometry is then the one that minimizes the surface free energy, $\gamma(T, p)$, defined as

$$\gamma(T, p) = \frac{1}{A} [G(T, p, N_{\text{Ru}}, N_{\text{O}}) - N_{\text{Ru}}\mu_{\text{Ru}}(T, p) - N_{\text{O}}\mu_{\text{O}}(T, p)]. \quad (1)$$

Here μ_{Ru} and μ_{O} are the chemical potentials of a Ru atom and an O atom, respectively, and $\gamma(T, p)$ is normalized to energy per unit area by dividing through the surface area A .

If the surface system is modeled by a slab with two equivalent surfaces, Eq. (1) gives

$$\gamma(T, p) = \frac{1}{2A} [G^{\text{slab}}(T, p, N_{\text{Ru}}, N_{\text{O}}) - N_{\text{Ru}}\mu_{\text{Ru}}(T, p) - N_{\text{O}}\mu_{\text{O}}(T, p)]. \quad (2)$$

Now A is the area of the surface unit cell and N_{Ru} and N_{O} are the numbers of Ru and O atoms in the three-dimensional supercell, respectively.

In Eq. (2) the chemical potentials of O and Ru enter in a symmetric way. However, if there is enough bulk material to act as a thermodynamic reservoir, the potentials are in fact no longer independent, but are related by the Gibbs free energy of the bulk oxide

$$\mu_{\text{Ru}}(T, p) + 2\mu_{\text{O}}(T, p) = g_{\text{RuO}_2}^{\text{bulk}}(T, p), \quad (3)$$

where lower case g is henceforth used to denote a Gibbs free energy per formula unit. Inserting this constraint into Eq. (2) leads to

$$\gamma(T, p) = \frac{1}{2A} [G^{\text{slab}}(T, p, N_{\text{Ru}}, N_{\text{O}}) - N_{\text{Ru}}g_{\text{RuO}_2}^{\text{bulk}}(T, p) + (2N_{\text{Ru}} - N_{\text{O}})\mu_{\text{O}}(T, p)], \quad (4)$$

which shows how the surface free energy depends now only on the oxygen chemical potential.

B. Range of allowed O chemical potentials

Since in experimental procedures it is normally the O_2 pressure and temperature which are varied, it is most useful to consider the dependence of the surface structure with respect to $\mu_{\text{O}}(T, p)$. It is important to note that experimentally (and assuming that thermodynamic equilibrium applies) μ_{O} cannot be varied without bounds. If μ_{O} becomes too low, all oxygen would leave the sample, i.e., the oxide would decompose into solid Ru and oxygen gas, which would start with the formation of Ru crystallites at the surface. Thus

$$\max[\mu_{\text{Ru}}(T, p)] = g_{\text{Ru}}^{\text{bulk}}(T, p), \quad (5)$$

where $g_{\text{Ru}}^{\text{bulk}}(T, p)$ is the Gibbs free energy of metallic ruthenium. Together with Eq. (3) and using $T=0$ K and the $p=0$ atm limit for the bulk energies, we will employ

$$\min[\mu_{\text{O}}(T, p)] = \frac{1}{2} [g_{\text{RuO}_2}^{\text{bulk}}(0, 0) - g_{\text{Ru}}^{\text{bulk}}(0, 0)] \quad (6)$$

to mark the ‘‘oxygen-poor limit’’ (or equivalently ‘‘Ru-rich’’ limit) in the graphs discussed below. This is a good estimate of the real physical limit and, most importantly, it is a theoretically well defined reference point on the μ_{O} axis.

On the other hand, the most oxygen-rich conditions can be defined as the point beyond which gas phase O would start to condense on the sample. However, in the temperature and pressure range we are interested in, a condensed O_2 -solid phase does not exist (the critical temperature of O_2 , i.e., above which gas and liquid phase are degenerate, is $T_c \approx 150$ K). Thus, similarly to Eq. (5), an appropriate and well-defined estimate of the upper limit of the oxygen chemical potential is

$$\max[\mu_{\text{O}}(T, p)] = 1/2 E_{\text{O}_2}^{\text{total}}, \quad (7)$$

where $E_{\text{O}_2}^{\text{total}}$ is the total energy of a free, isolated O_2 molecule at $T=0$ K.

Then, introducing the Gibbs free energy of formation, $\Delta G_f(T, p)$, of the oxide,

$$\Delta G_f(T, p) = g_{\text{RuO}_2}^{\text{bulk}}(T, p) - g_{\text{Ru}}^{\text{bulk}}(T, p) - g_{\text{O}_2}^{\text{gas}}(T, p), \quad (8)$$

where $g_{\text{O}_2}^{\text{gas}}(T, p)$ is the Gibbs free energy of an O_2 molecule, we see that the range of oxygen chemical potentials between our theoretical boundaries is

$$\frac{1}{2} \Delta G_f(0, 0) < \mu_{\text{O}}(T, p) - \frac{1}{2} E_{\text{O}_2}^{\text{total}} < 0. \quad (9)$$

We compute $\Delta G_f(0, 0) = -3.35$ eV per formula unit, which compares very well with the experimental Gibbs free energy of formation at standard pressure in the limit of low temperatures, $\Delta G_f^o(T \rightarrow 0, 1 \text{ atm}) = -3.19$ eV per formula unit.⁷

It is important to note that our delineated boundaries for the oxygen-rich and oxygen-poor conditions are theoretically well-defined limits, yet they only represent an estimate of the truly accessible range of the oxygen chemical potential. The range between our boundaries is $1/2 \Delta G_f(0, 0)$, but in reality the accessible range is $1/2 \Delta G_f(T, p)$, i.e., it is temperature and pressure dependent. At $T=1000$ K and $p=1$ atm, the Gibbs free energy of formation has increased by 0.63 eV compared to the aforementioned $T \rightarrow 0$ K value.⁷ Since the accessible range of chemical potential can thus vary by 0.3 eV, we will always show the resulting curves in our below discussed figures also some tenths of an eV outside the ‘‘oxygen-rich’’ and ‘‘oxygen-poor’’ boundaries.

C. Oxygen-poor limit as a safe reference

Total energies for extended systems are typically more accurately described by DFT calculations than those for atoms and molecules. It is therefore suitable to rewrite Eq. (9) as

$$\frac{1}{2} [g_{\text{RuO}_2}^{\text{bulk}}(0,0) - g_{\text{Ru}}^{\text{bulk}}(0,0)]$$

$$\langle \mu_{\text{O}}(T,p) \rangle < \frac{1}{2} [g_{\text{RuO}_2}^{\text{bulk}}(0,0) - g_{\text{Ru}}^{\text{bulk}}(0,0)] + \frac{1}{2} \Delta G_f(0,0). \quad (10)$$

If we then insert the oxygen-poor limit into Eq. (4), for the surface free energy we obtain

$$\gamma_{\text{O-poor}}(T,p) = \frac{1}{2A} \left[G^{\text{slab}}(T,p,N_{\text{Ru}},N_{\text{O}}) - N_{\text{Ru}} g_{\text{RuO}_2}^{\text{bulk}}(T,p) \right. \\ \left. - \left(N_{\text{Ru}} - \frac{N_{\text{O}}}{2} \right) [g_{\text{Ru}}^{\text{bulk}}(0,0) - g_{\text{RuO}_2}^{\text{bulk}}(0,0)] \right]. \quad (11)$$

Likewise, the oxygen-rich limit turns out to be

$$\gamma_{\text{O-rich}}(T,p) = \gamma_{\text{O-poor}}(T,p) - \frac{1}{2A} \left(N_{\text{Ru}} - \frac{N_{\text{O}}}{2} \right) \Delta G_f(0,0). \quad (12)$$

The result of this rewriting of Eq. (9) is that atomic or molecular quantities do not enter into the calculation of the oxygen-poor limit, i.e., Eq. (11), at all, which thus defines a safe reference involving only bulk or slab quantities.

On the other hand, $\Delta G_f(0,0)$ depends on the O_2 total energy, and $\Delta G_f(0,0)$ defines the slope of the lines representing the surface free energy as a function of μ_{O} : The slope is

$$\frac{1}{2A} \left(N_{\text{Ru}} - \frac{N_{\text{O}}}{2} \right) \Delta G_f(0,0) \quad (13)$$

[cf. Eq. (12)], and sometimes $\Delta G_f(0,0)$ may be affected by the error in $E_{\text{O}_2}^{\text{total}}$, in which case it might be preferable to use its experimental value. Yet, for the present case of RuO_2 , we note that our DFT result for the Gibbs free energy of formation is very close to the experimental value (see above). Thus here the error in $E_{\text{O}_2}^{\text{total}}$, which clearly exists, cancels out and the calculated slopes are very accurate. As a consequence, and in contrast to common belief, we note that the bulk total energy of RuO_2 must therefore have a similar error as $E_{\text{O}_2}^{\text{total}}$ —otherwise the apparent error cancelation in $\Delta G_f(0,0)$ would not occur.

We finally note in passing that Eqs. (11) and (12) nicely reflect the physics behind the dependence on the O chemical potential. While a stoichiometrically terminated surface structure ($N_{\text{Ru}}=N_{\text{O}}/2$) will exhibit a constant surface free energy as a function of $\mu_{\text{O}}(T,p)$, a termination with an O excess (deficiency) will become more favorable (unfavorable) with increasing $\mu_{\text{O}}(T,p)$, i.e., higher O pressure and/or lower temperature.

D. Gibbs free energies vs total energies

The formalism as described up to this point is entirely based on the Gibbs free energies of the system, whereas we

intend to provide as input total energies from DFT calculations. Therefore, we will now outline how both quantities are related, and under which approximations they might be equated to each other.

DFT total energies are evaluated for a certain volume V of the unit cell. The resulting $E^{\text{total}}(V,N_{\text{Ru}},N_{\text{O}})$ is related to a thermodynamical quantity only in a restricted way, corresponding to the Helmholtz free energy at zero temperature and neglecting zero-point vibrations. In general, the Helmholtz free energy can thus be written as

$$F(T,V,N_{\text{Ru}},N_{\text{O}}) = E^{\text{total}}(V,N_{\text{Ru}},N_{\text{O}}) + F^{\text{vib.}}(T,V,N_{\text{Ru}},N_{\text{O}}), \quad (14)$$

with

$$F^{\text{vib.}}(T,V,N_{\text{Ru}},N_{\text{O}}) \\ = E^{\text{vib.}}(T,V,N_{\text{Ru}},N_{\text{O}}) - TS^{\text{vib.}}(T,V,N_{\text{Ru}},N_{\text{O}}) \quad (15)$$

comprising all contributions, which depend on vibrational modes in the system. Here $E^{\text{vib.}}$ and $S^{\text{vib.}}$ are the vibrational energy (including the zero-point energy) and entropy, respectively. In turn, the Helmholtz free energy is associated with the Gibbs free energy via

$$G(T,p,N_{\text{Ru}},N_{\text{O}}) = F(T,p,N_{\text{Ru}},N_{\text{O}}) + pV(T,p,N_{\text{Ru}},N_{\text{O}}). \quad (16)$$

Checking first on the pV term, we find from a simple dimensional analysis that its contribution to the surface free energy (normalized to the surface area) will be $[pV/A] = \text{atm } \text{\AA}^3 / \text{\AA}^2 \sim 10^{-3} \text{ meV}/\text{\AA}^2$. As we are only interested in a pressure range that will not exceed about 100 atm, this contribution is negligible compared to the Helmholtz free energy, which is of the order of tenths of $\text{meV}/\text{\AA}^2$.

This leaves as the only additional contribution to $G(T,p,N_{\text{Ru}},N_{\text{O}})$ apart from the DFT total energy the vibrational term $F^{\text{vib.}}(T,V,N_{\text{Ru}},N_{\text{O}})$. Using the phonon density of states (DOS) $\sigma(\omega)$, this vibrational component of the free energy can be written as an integral over the modes ω ,

$$F^{\text{vib.}}(T,V,N_{\text{Ru}},N_{\text{O}}) = \int d\omega F^{\text{vib.}}(T,\omega) \sigma(\omega), \quad (17)$$

where an analytical expression for $F^{\text{vib.}}(T,\omega)$ is given in the Appendix.

Inserting this into Eq. (11), we obtain, for the vibrational contribution to the surface free energy of a stoichiometric termination ($N_{\text{Ru}}=N_{\text{O}}/2$) at the O-poor limit,

$$\gamma_{\text{O-poor}}^{\text{vib.}}(T,V) \\ = \frac{1}{2A} \int d\omega F^{\text{vib.}}(T,\omega) [\sigma^{\text{slab}}(\omega) - N_{\text{Ru}} \sigma_{\text{RuO}_2}^{\text{bulk}}(\omega)]. \quad (18)$$

To obtain an estimate of its value, we use the Einstein model and approximate the phonon DOS by just one characteristic frequency for each atom type. If we further consider that the vibrational mode of the topmost layer of Ru and O might be

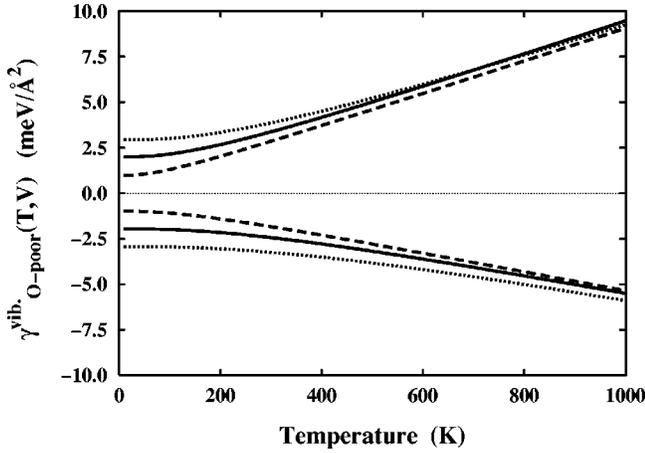


FIG. 1. Vibrational contribution to the surface free energy, of a stoichiometric termination [cf. Eq. (19)], in the temperature range of interest in the present study. The Ru and O modes are approximated in the Einstein model by characteristic frequencies, $\bar{\omega}_{\text{O}}^{\text{bulk}} = 80$ meV and $\bar{\omega}_{\text{Ru}}^{\text{bulk}} = 25$ meV. Shown is the contribution if the vibrational modes at the surface differs by $\pm 50\%$ from these bulk values (solid lines). To assess the dependence on the value chosen for the characteristic frequencies, the latter are varied by $\pm 50\%$ (dashed and dotted lines respectively). In all cases, the vibrational contribution stays below $10 \text{ meV}/\text{\AA}^2$ in the whole temperature range considered.

significantly changed at the surface, we thus have $\bar{\omega}_{\text{O}}^{\text{bulk}}$ and $\bar{\omega}_{\text{Ru}}^{\text{bulk}}$ as characteristic frequencies of O and Ru in RuO_2 bulk, as well as $\bar{\omega}_{\text{O}}^{\text{surf.}}$ and $\bar{\omega}_{\text{Ru}}^{\text{surf.}}$ as the respective modes at the surface. With this simplified phonon DOS, Eq. (18) reduces to

$$\gamma_{\text{O-poor}}^{\text{vib.}}(T, V) \approx \frac{3}{2A} \{ [F^{\text{vib.}}(T, \bar{\omega}_{\text{Ru}}^{\text{surf.}}) - F^{\text{vib.}}(T, \bar{\omega}_{\text{Ru}}^{\text{bulk}})] + [F^{\text{vib.}}(T, \bar{\omega}_{\text{O}}^{\text{surf.}}) - F^{\text{vib.}}(T, \bar{\omega}_{\text{O}}^{\text{bulk}})] \}. \quad (19)$$

Hence we see that in the O-poor limit $\gamma_{\text{O-poor}}^{\text{vib.}}(T, p)$ of a stoichiometric termination arises primarily out of the difference of the vibrational modes at the oxide surface with respect to their bulk value. To quantify this estimate, we use $\bar{\omega}_{\text{O}}^{\text{bulk}} = 80$ meV and $\bar{\omega}_{\text{Ru}}^{\text{bulk}} = 25$ meV,^{8,9} and allow a 50% variation of these values at the surface, to plot Eq. (19) in Fig. 1 in the temperature range of interest to our study. As these particular values for the characteristic frequencies are not well justified, but should only be considered as rough estimates, we also include the corresponding $\gamma_{\text{O-poor}}^{\text{vib.}}(T, p)$ in the graph, if these values changed by $\pm 50\%$. From Fig. 1 we see that the vibrational contribution to the surface free energy stays within $10 \text{ meV}/\text{\AA}^2$ in all of the considered cases, and that the uncertainty in the characteristic frequencies translates primarily to variations of $\gamma_{\text{O-poor}}^{\text{vib.}}(T, p)$ at low temperatures, where the value of the latter is very small in any case.

We have also computed the vibrational contribution to the surface free energy of nonstoichiometric terminations in an

analogous manner. There the expression becomes considerably more complex than in Eq. (11), and the vibrational contribution includes not only differences between bulk and surface vibrational modes, but also absolute $F^{\text{vib.}}(T, \omega)$ terms due to the excess or deficient atoms. However, even then, the vibrational contribution stays within $\pm 10 \text{ meV}/\text{\AA}^2$ similar to the above described stoichiometric case. In conclusion, we therefore take this value to represent a good upper bound for the vibrational influence on the surface free energy.

Such a $\pm 10\text{-meV}/\text{\AA}^2$ contribution is certainly not a completely negligible factor, yet as we will show below it is of the same order as the numerical uncertainty in our calculations. Furthermore, as will become apparent in the discussion of the results, this uncertainty does not affect any of the physical conclusions drawn in the present application. Hence we will henceforth neglect the complete vibrational contribution to the Gibbs free energy, leaving only the total energies $E^{\text{total}}(V, N_{\text{Ru}}, N_{\text{O}})$ as the predominant term. In turn, this allows us to rewrite Eq. (11) as

$$\gamma_{\text{O-poor}}(T, p) \approx \frac{1}{2A} \left[E^{\text{slab}}(V, N_{\text{Ru}}, N_{\text{O}}) - \frac{N_{\text{O}}}{2} E_{\text{RuO}_2}^{\text{bulk}}(V) - \left(N_{\text{Ru}} - \frac{N_{\text{O}}}{2} \right) E_{\text{Ru}}^{\text{bulk}}(V) \right], \quad (20)$$

which now contains exclusively terms directly obtainable from a DFT calculation. We stress that this approximation is well justified in the present case, but it is not a general result. There might well be applications where the inclusion of vibrational effects on the surface free energy can be crucial.

E. Pressure and temperature dependence of $\mu_{\text{O}}(T, p)$

Having completely described the recipe of how to obtain $\gamma(T, p)$ as a function of the O chemical potential, the remaining task is to relate the latter to a given temperature T and pressure p . As the surrounding O_2 atmosphere forms an ideal-gas-like reservoir, it can be shown that expression

$$\mu_{\text{O}}(T, p) = \mu_{\text{O}}(T, p^\circ) + 1/2 kT \ln \left(\frac{p}{p^\circ} \right), \quad (21)$$

applies, which already gives us the temperature and pressure dependence, if we only know the temperature dependence of $\mu_{\text{O}}(T, p^\circ)$ at one particular pressure, p° (see Appendix A 2).

We choose the zero reference state of $\mu_{\text{O}}(T, p)$ to be the total energy of oxygen in an isolated molecule, i.e., $\mu_{\text{O}}(0\text{K}, p) = 1/2 E_{\text{O}_2}^{\text{total}} = 0$. With respect to this zero, $\mu_{\text{O}}(T, p^\circ)$ is then given by

$$\begin{aligned} \mu_{\text{O}}(T, p^\circ) &= \mu_{\text{O}}^{\text{O-rich}}(0 \text{ K}, p^\circ) + 1/2 \Delta G(\Delta T, p^\circ, \text{O}_2) \\ &= 1/2 [H(T, p^\circ, \text{O}_2) - H(0 \text{ K}, p^\circ, \text{O}_2)] \\ &\quad - 1/2 T [S(T, p^\circ, \text{O}_2) - S(0 \text{ K}, p^\circ, \text{O}_2)], \end{aligned} \quad (22)$$

where we have used the relation $G = H - TS$ between the Gibbs free energy and the enthalpy H . This allows us to obtain the aspired temperature dependence simply from the

TABLE I. $\mu_{\text{O}}(T, p^\circ)$ in the temperature range of interest to our study. The entropy and enthalpy changes used to obtain $\mu_{\text{O}}(T, p^\circ)$ via Eq. (22) are taken from thermochemical tables at $p^\circ = 1$ atm.¹⁰

T	$\mu_{\text{O}}(T, p^\circ)$	T	$\mu_{\text{O}}(T, p^\circ)$
100 K	-0.08 eV	600 K	-0.61 eV
200 K	-0.17 eV	700 K	-0.73 eV
300 K	-0.27 eV	800 K	-0.85 eV
400 K	-0.38 eV	900 K	-0.98 eV
500 K	-0.50 eV	1000 K	-1.10 eV

differences in the enthalpy and entropy of an O_2 molecule with respect to the $T=0$ K limit. For standard pressure, $p^\circ = 1$ atm, these values are, e.g., tabulated in thermochemical tables.¹⁰ Inserting them into Eq. (22) leads finally to $\mu_{\text{O}}(T, p^\circ)$, which we list in Table I.

Together with Eq. (21) the O chemical potential can thus be obtained for any given (T, p) pair. Although we prefer to conveniently present the resulting surface energies as a one-dimensional function of $\mu_{\text{O}}(T, p)$, we will also often convert this dependence into a temperature (pressure) dependence at a fixed pressure (temperature) in a second x axis to elucidate the physical meaning behind the calculated curves.

F. DFT basis set and convergence

The DFT input to Eq. (20) has been obtained using the full-potential linear augmented plane wave method (FP-LAPW)^{11–13} within the generalized gradient approximation (GGA) of the exchange-correlation functional.¹⁴ For the $\text{RuO}_2(110)$ surface calculation we use a symmetric slab consisting of three rutile O-(RuO)-O trilayers, where all atomic positions within the outermost trilayer were fully relaxed. A vacuum region of ≈ 11 Å is employed to decouple the surfaces of consecutive slabs in the supercell approach. Test calculations with five and seven trilayered slabs, as well as with a vacuum region up to ≈ 28 Å, confirmed the good convergence of this chosen setup with variations of $\gamma(T, p)$ smaller than ± 3 meV/Å². Allowing a relaxation of deeper surface layers in the thicker slabs did not result in a significant variation of the respective atomic positions, nor did it influence the near-surface geometry obtained in the calculations with the standard three-trilayer slabs. To ensure maximum consistency, the corresponding RuO_2 bulk computations are done in exactly the same (110)-oriented unit cell as used for the slabs, in which the prior vacuum region is simply replaced by additional RuO_2 trilayers.

The FP-LAPW basis set is taken as follows: $R_{\text{MT}}^{\text{Ru}} = 1.8$ bohr, $R_{\text{MT}}^{\text{O}} = 1.3$ bohr, a wave function expansion inside the muffin tins up to $l_{\text{max}}^{\text{wf}} = 12$, and a potential expansion up to $l_{\text{max}}^{\text{pot}} = 4$. For the $\text{RuO}_2(110)$ slabs the Brillouin-zone integration was performed using a $(5 \times 10 \times 1)$ Monkhorst-Pack grid with 15 \mathbf{k} points in the irreducible part. The energy cutoff for the plane-wave representation in the interstitial region between the muffin tin spheres was 17 Ry for the wave functions and 169 Ry for the potential. Checking on the convergence, the surface free energies of the three possible (1×1) $\text{RuO}_2(110)$ truncations discussed below were found

unchanged to within 1 meV/Å² by increasing the k mesh to a $(7 \times 14 \times 1)$ Monkhorst-Pack grid with 28 \mathbf{k} points in the irreducible part. A larger interstitial cutoff of 24 Ry reduced the absolute values of the three $\gamma(T, p)$ by up to 10 meV/Å²; however, as all of them were reduced, their respective differences (which are the only relevant quantities entering the physical argument) stayed constant to within 5 meV/Å².

Overall we thus find the numerical accuracy of the calculated surface free energies with respect to the supercell approach and the finite basis set to be within 10 meV/Å², which will not affect any of the physical conclusions drawn. Note that the stated imprecision does not include possible errors introduced by more general deficiencies of the approach, namely, the use of the GGA as exchange-correlation functional, on upon which we will comment below.

III. RESULTS

A. $\text{RuO}_2(110)$ surface structure

RuO_2 crystallizes in the rutile structure, in which every metal atom is coordinated to six oxygens, and every oxygen to three metal neighbors.¹⁵ The oxygens that form an octahedron around each Ru atom are not all equivalent, but can be distinguished into four basal and two apical O atoms with calculated O-Ru bond lengths of 2.00 Å and 1.96 Å, respectively. We note that along the (110) direction this structure can then be viewed as a stacking sequence of O-(RuO)-O trilayers, in which each trilayer is simply composed of an alternating sequence of in-plane and perpendicularly oriented oxygen-ruthenium coordination octahedra [cf. Fig. 2(b)]. Cut along the (110) direction, the rutile structure can therefore exhibit three distinct terminations of (1×1) periodicity, depending at which plane the trilayer is truncated [cf. Figs. 2(a)–2(c)].

Traditionally, the stoichiometric $\text{RuO}_2(110)$ -O^{bridge} termination is believed to be the most stable one for all (110) surfaces of crystals with the rutile structure,^{4,5} because it leads to an uncharged surface in the ionic model and cuts the least number of bonds. While the Ru^{bridge,6f} atoms possess their ideal sixfold O coordination with two of their basal oxygens forming the terminal O^{bridge} atoms, only the Ru^{cus,5f} lack one apical on-top O, as shown in Fig. 2(a). Note that we will use a nomenclature for the surface Ru atoms, where, apart from a site-specific characterization (e.g., cus for the coordinatively unsaturated site in the stoichiometric termination), the number of direct O neighbors (e.g., 5f for fivefold coordination) is also stated. Conversely, we indicate the specific site to which the surface O atoms bind (e.g., O^{bridge} binds to the Ru^{bridge,6f} atoms).

Alternatively, in the second possible $\text{RuO}_2(110)$ -O^{cus} termination, shown in Fig. 2(b), terminal O^{cus} atoms occupy sites on top of the formerly undercoordinated Ru^{cus,6f} atoms, so that now all metal atoms in the surface possess their ideal sixfold coordination. This is, of course, compensated for by the presence of both the only twofold- and onefold-coordinated O^{bridge} and O^{cus} atoms, respectively. Finally, the

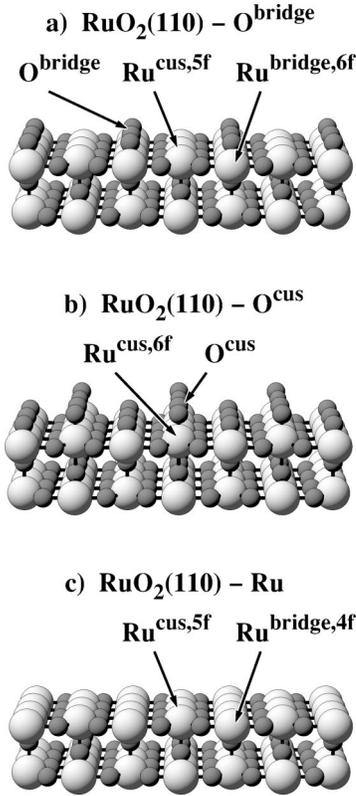


FIG. 2. Three possible terminating planes of the rutile (110) surface: (a) Stoichiometric $\text{RuO}_2(110) - \text{O}^{\text{bridge}}$ termination with fivefold, sixfold, and twofold-coordinated $\text{Ru}^{\text{cus},5f}$, $\text{Ru}^{\text{bridge},6f}$, and O^{bridge} atoms, respectively. (b) $\text{RuO}_2(110) - \text{O}^{\text{cus}}$ termination, where additional O^{cus} atoms sit atop the formerly undercoordinated $\text{Ru}^{\text{cus},6f}$ atoms. (c) $\text{RuO}_2(110) - \text{Ru}$ termination, which lacks the O^{bridge} atoms in comparison to the stoichiometric termination (Ru, large, light spheres; O, small, dark spheres).

third $\text{RuO}_2(110) - \text{Ru}$ termination exhibiting the mixed (RuO) plane at the surface is achieved by removing the O^{bridge} atoms from the stoichiometric termination [cf. Fig. 2(c)]. Here no undercoordinated oxygens are present any longer, but this occurs at the expense of the fourfold- and fivefold-bonded $\text{Ru}^{\text{bridge},4f}$ and $\text{Ru}^{\text{cus},5f}$ atoms.

B. Prediction of a high-pressure termination

The calculated surface free energies of the three possible terminations are shown in Fig. 3. As explained in connection with Eq. (12), the $\text{RuO}_2(110) - \text{O}^{\text{cus}}$ [$\text{RuO}_2(110) - \text{Ru}$] termination with an excess (deficiency) of O at the surface becomes more favorable (unfavorable) toward the O-rich limit, while the stoichiometric $\text{RuO}_2(110) - \text{O}^{\text{bridge}}$ termination exhibits a constant $\gamma(T,p)$. Indeed, we find the traditionally assumed stoichiometric $\text{RuO}_2(110) - \text{O}^{\text{bridge}}$ surface to be the most stable over quite a range of oxygen chemical potentials above the O-poor limit. To clarify the physical meaning of this range, we have used Eq. (21) to convert $\mu_{\text{O}}(T,p)$ into a pressure dependence at a fixed temperature, as can be seen at the top x axis of Fig. 3. The temperature of $T=600$ K corresponds to a typical annealing temperature employed experimentally for this system.^{9,16–19} From the resulting pres-

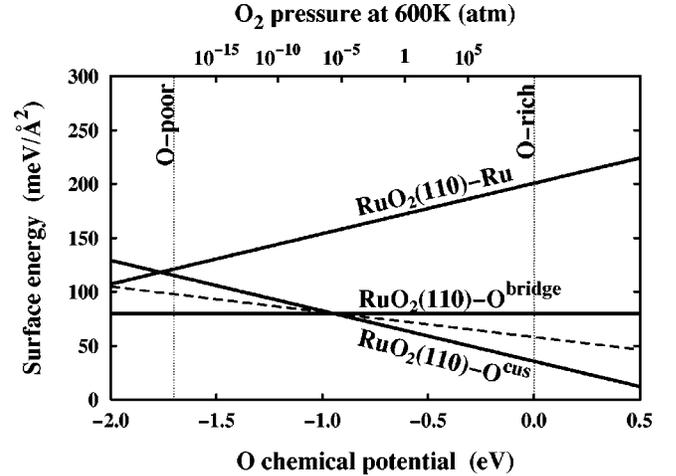


FIG. 3. Surface free energies $\gamma(T,p)$ of the three $\text{RuO}_2(110)$ terminations depicted in Fig. 2. Additionally shown by the dashed line is the surface free energy of a $\text{RuO}_2(110) - \text{O}^{\text{cus}}$ termination, in which only every second O^{cus} site along the trenches is occupied. The dotted vertical lines indicate the allowed range of the oxygen chemical potential, $\mu_{\text{O}}(T,p)$, using $1/2E_{\text{O}_2}^{\text{total}}$ as zero reference as explained in Sec. II B. In the top x axis, the dependence on $\mu_{\text{O}}(T,p)$ has been cast into a pressure scale at a fixed temperature of $T=600$ K.

sure scale we see that the stability of the stoichiometric termination therefore extends roughly around the pressure range corresponding to UHV conditions.

However, this is different at higher O pressures, where the $\text{RuO}_2(110) - \text{O}^{\text{cus}}$ termination becomes the most stable surface structure [cf. Fig. 3]. In the O-rich limit, it exhibits a $\gamma^{\text{O-rich}}(T,p)$, which is by $49 \text{ meV}/\text{\AA}^2$ lower than the one of the stoichiometric $\text{RuO}_2(110) - \text{O}^{\text{bridge}}$ surface, i.e., the deduced crossover between the two terminations is far beyond the estimated uncertainty of $\approx \pm 10 \text{ meV}/\text{\AA}^2$ due to the neglect of the vibrational contribution to the Gibbs free energies and due to the finite basis set. This estimate does, however, not comprise the more general error due to the use of the GGA as exchange-correlation functional. To this end, we have also calculated the surface free energies of the two competing terminations within the local density approximation (LDA).²⁰ Although the absolute values of both $\gamma^{\text{O-poor}}(T,p)$ turn out to be by $\approx 15 \text{ meV}/\text{\AA}^2$ higher, their respective difference is almost unchanged, which is eventually what determines the crossover point of the two lines in Fig. 3. The $\text{RuO}_2(110) - \text{O}^{\text{cus}}$ termination is therefore the lowest energy structure for $\mu_{\text{O}}(T,p) > -0.85 \text{ eV}$ in the LDA, which is almost the same as the $\mu_{\text{O}}(T,p) > -0.93 \text{ eV}$ found with the GGA, shown in Fig. 3. Consequently, while the choice of the exchange-correlation functional may affect the exact transition temperature or pressure, the transition *per se* is untouched. In turn, we may safely predict the stability of a polar surface termination on $\text{RuO}_2(110)$ at high O chemical potential, corresponding e.g. to the pressure range typical for catalytic applications.

Note, that Fig. 3 summarizes only the $\gamma(T,p)$ of the three (1×1) terminations, which arise by truncating the RuO_2 crystal at bulk-like planes in the (110) orientation. However,

it is *a priori* not clear that the terminal atoms at the surface must be in the sites corresponding to the bulk stacking sequence. To check this, we have additionally calculated the surface free energies of surface structures, where the O^{bridge} (O^{cus}) atoms occupy atop (bridge) sites over the $Ru^{\text{bridge},5f}$ ($Ru^{\text{cus},6f}$) atoms, instead of their normal bridging (atop) configuration. In both cases, we find the $\gamma(T,p)$ considerably higher, which excludes the possibility that these adatoms occupy non bulklike sites at the surface. Similarly, a $RuO_2(110)-O^{\text{cus}}$ termination, where the O^{bridge} atoms have been removed, can also safely be ruled out as alternative for a stoichiometrically terminated surface.

C. Lateral interaction between O^{cus} atoms and vacancy concentration

The reasoning of Sec. III B leaves only the $RuO_2(110)-O^{\text{bridge}}$ and $RuO_2(110)-O^{\text{cus}}$ termination as the relevant surface structures stabilized in UHV and under high O pressure respectively. Both differ from each other only by the presence of the additional O^{cus} atoms, which continue the bulk stacking sequence by filling the vacant sites on top of the formerly undercoordinated $Ru^{\text{cus},5f}$ atoms. The way the $RuO_2(110)-O^{\text{cus}}$ termination is formed at an increasing oxygen chemical potential will therefore depend significantly on the details of the lateral interaction among this adatom species.

The $RuO_2(110)-O^{\text{bridge}}$ surface has a trenchlike structure with a distance of 6.43 Å between the rows formed by the O^{bridge} atoms [cf. Fig. 2(a)]. This renders any lateral interaction between O^{cus} atoms adsorbed in neighboring trenches rather unlikely. On the other hand, the distance between two O^{cus} atoms occupying neighboring sites along one trench is only 3.12 Å. To check on the corresponding interaction we calculated the surface free energy of a $RuO_2(110)-O^{\text{cus}}$ termination in a (2×1) supercell, in which the O^{cus} atoms occupied only every other site along the trenches. The corresponding $\gamma(T,p)$ is drawn as a dashed line in Fig. 3. As now only half of the excess O^{cus} atoms are present, the slope of this curve has to be one half of the slope of the line representing the normal $RuO_2(110)-O^{\text{cus}}$ termination [cf. Eq. (12)].

Interestingly, both curves cross the stoichiometric $RuO_2(110)-O^{\text{bridge}}$ line at exactly the same point. This can only be understood by assuming a negligible lateral interaction between neighboring O^{cus} atoms: If there was an attractive (repulsive) interaction between them, then it would be favorable (unfavorable) to put O^{cus} atoms as close to each other as possible. In turn, the (2×1) overlayer of O^{cus} atoms, in which only every other site is occupied, would be less (more) stable than the normal $RuO_2(110)-O^{\text{cus}}$ termination, where all neighboring sites are full. Consequently, the stability with respect to the stoichiometric termination would be decreased (enhanced), leading to a later (earlier) crossover point in Fig. 3. That both calculated lines cross the $RuO_2(110)-O^{\text{bridge}}$ line at the same point is therefore a reflection of a negligible lateral interaction between the O^{cus} atoms.

Additionally, we compute a very high barrier of almost 1.5 eV for diffusion of O^{cus} atoms along the trenches, indicating that the latter species will be practically immobile in the temperature range where the oxide is stable. This, together with the small lateral interaction, indicates that at increasing O chemical potential the $RuO_2(110)-O^{\text{cus}}$ surface is formed from the stoichiometric termination by a random occupation of O^{cus} sites, until eventually the whole surface is covered. Even so, at finite temperatures there will still be a certain vacancy concentration even at O chemical potentials above the crossover point of the two terminations. As the undercoordinated $Ru^{\text{cus},5f}$ atoms exposed at such a vacant O^{cus} site [cf. Fig. 2], might be chemically active sites for surface reactions,¹⁸ it is interesting to estimate how many of these sites will be present under given (T,p) conditions.

Since we have shown that each O^{cus} site at the surface is filled independently from the others, we can estimate its occupation probability within a simple two-level system (site occupied or vacant) in contact with a heat bath. The vacancy concentration then follows from a canonic distribution, where the energy of the two levels is given by the $\gamma(T,p)$ of the two terminations at the chosen chemical potential. As an example, we first address room temperature, where the $RuO_2(110)-O^{\text{cus}}$ termination becomes stable at pressures higher than $p\sim 10^{-22}$ atm. A vacancy concentration of only 1% is in turn already reached at $p\sim 10^{-17}$ atm, so that at this temperature there will only be a negligible number of vacancies on the O^{cus} -terminated surface for any realistic pressure.

However, this situation becomes completely different at elevated temperatures. At $T=800$ K, the crossover to the $RuO_2(110)-O^{\text{cus}}$ termination occurs at $p\sim 10^{-1}$ atm, with a 10% vacancy concentration still present at 10^2 atm. In the range of atmospheric pressures the $RuO_2(110)$ surface will therefore exhibit a considerable number of vacancies, which could explain the high catalytic activity reported for this material.^{18,19,21-24} However, although we have deliberately chosen $T=800$ K as a typical catalytic temperature, where, e.g., a maximum conversion rate for the CO/CO₂ oxidation reaction over $RuO_2(110)$ was found,²² we immediately stress that our reasoning is at the moment only based on the O pressure alone, and is therefore not directly applicable to catalysis experiments, which may also depend on the partial pressure of other reactants in the gas phase.

D. On the stability of polar surfaces

As already mentioned in Sec. I, the predicted high-pressure $RuO_2(110)-O^{\text{cus}}$ termination is traditionally not expected as it forms a so-called polar surface, which should not be stable on electrostatic grounds.^{4,5} The corresponding argument is based on the ionic model of oxides, in which every atom in the solid is assumed to be in its bulk formal oxidation state. Along a particular direction z , the crystal may then be viewed as a stack of planes with charge q , each of which contribute with $V(z)\propto qz$ to the total electrostatic potential. As this contribution diverges at infinite distances, the crystal as a whole can in turn only be stable if constructed as a neutral block in which all infinite values due to the individual planes cancel. For $RuO_2(110)$, which is a type-2 sur-

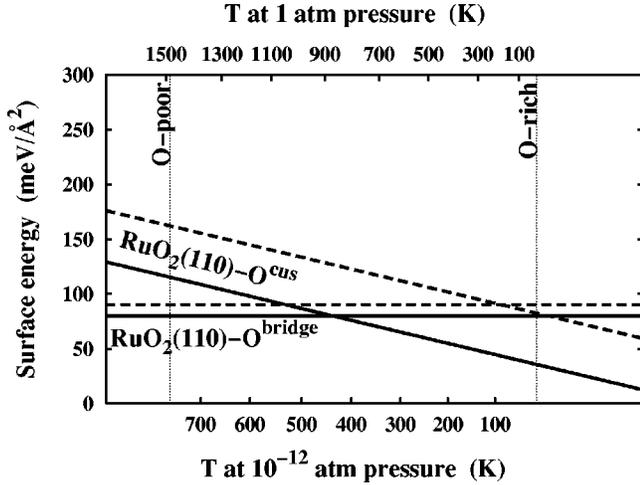


FIG. 4. Surface free energies $\gamma(T,p)$ of the stoichiometric $\text{RuO}_2(110)\text{-O}^{\text{bridge}}$ and polar $\text{RuO}_2(110)\text{-O}^{\text{cus}}$ terminations. Shown is the effect of relaxation at the surface, with solid lines indicating fully relaxed surface structures, and dashed lines the corresponding bulk-truncated geometries. The dependence on the oxygen chemical potential has been translated into a temperature scale at 10^{-12} atm (bottom x axis) and 1 atm (top x axis) pressure.

face in Tasker's widely used classification scheme,²⁵ the only neutral repeat unit is a symmetric O-(RuO)-O trilayer with a $(-2)\text{-}(+4)\text{-}(-2)$ charge sequence. Correspondingly, the stoichiometric $\text{RuO}_2(110)\text{-O}^{\text{bridge}}$ termination would be the only surface termination without net dipole moment in this ionic model.

On the other hand, the $\text{RuO}_2(110)\text{-O}^{\text{cus}}$ termination with its extra unmatched (-2) charge plane formed by the O^{cus} atoms would lead to a diverging potential and should thus not be stable. That we indeed find this surface stabilized at higher O chemical potentials points to the most obvious shortcoming of the electrostatic model, namely, the assumption that all atoms in the solid are identical, i.e., that also all surface atoms are in bulklike states both structurally as well as electronically. The extent to which the additional structural degrees of freedom at the surface already influence the stability is exemplified in Fig. 4, where the surface free energies of the two relevant terminations are compared in either a bulk-truncated or fully relaxed geometry. While the small relaxation of the $\text{RuO}_2(110)\text{-O}^{\text{bridge}}$ termination hardly affects the $\gamma(T,p)$, the bulk-truncated $\text{RuO}_2(110)\text{-O}^{\text{cus}}$ surface structure turns out to be considerably less stable compared to its relaxed counterpart. This bulk-truncated $\text{RuO}_2(110)\text{-O}^{\text{cus}}$ surface exhibits a work function $+2.5$ eV higher than the stoichiometric termination, which indicates that the addition of the O^{cus} atoms indeed induces a considerable dipole moment, as suggested by the ionic model. However, the relaxation alone lowers this work function by 1 eV, reflecting that the dipole moment can already be considerably reduced via a significantly shortened $\text{O}^{\text{cus}}\text{-Ru}^{\text{cus}}$ bond length of 1.70 Å (compared to the bulk value of 1.96 Å), thereby considerably stabilizing the surface.

Not only do the topmost layers in the $\text{RuO}_2(110)\text{-O}^{\text{cus}}$ surface differ structurally to an appreciable extent from their respective bulk counterparts, but there are also significant

electronic differences as well. This is illustrated in Fig. 5, where we show the (x,y) -averaged potential along the (110) direction perpendicular to the surface, z . In the bulk-truncated, stoichiometric $\text{RuO}_2(110)\text{-O}^{\text{bridge}}$ termination in Fig. 5(a), the electrostatic potential at the topmost O-(RuO)-O trilayer is still almost identical to the corresponding one in the deeper trilayers, thus enabling a description in this case of this surface in terms of bulklike planes as assumed in the ionic model. Conversely, we find a significant deviation of the potential in the outermost layers of the $\text{RuO}_2(110)\text{-O}^{\text{cus}}$ termination [cf. Fig. 5(b)], even for a bulk-truncated geometry. This difference is further enhanced by the structural relaxation, shown in Fig. 5(c), so that the topmost (RuO)-O-O planes of this termination are certainly not well characterized by bulk properties, thus invalidating the electrostatic argument raised against this polar surface.

We argue instead that the surface fringe composed by the topmost layers should be viewed as a new material, which properties might differ considerably from the bulk stacking sequence due to the additional structural and electronic degrees of freedom present at the surface. A similar conclusion was previously reached by Wang and co-workers,^{2,3} who discussed the stability of oxygen-terminated polar (0001) surfaces of corundum-structured $\alpha\text{-Fe}_2\text{O}_3$ and $\alpha\text{-Al}_2\text{O}_3$. This indicates that the traditionally dismissed polar terminations⁶ might indeed be a more general phenomenon, the existence of which could be a crucial ingredient to understand the function of oxide surfaces under realistic environmental conditions. As particularly polar terminations with excess oxygen can be stabilized at increased O_2 partial pressure in the gas phase, the different properties of the latter should be taken into consideration when modeling high-pressure applications such as catalysis.

E. Importance of experimental preparation conditions

This influence of the O_2 partial pressure on the surface morphology and function has recently become apparent in a number of studies addressing the reported high CO oxidation rates over Ru catalysts. While it was believed for a long time that the active species is the Ru metal itself,²⁶⁻²⁹ the decisive role played by oxide patches formed under catalytic conditions was only recently realized.^{17-19,21,22} This was primarily due to the problem of preparing a fully oxidized surface in a controlled manner under UHV conditions. By means of more oxidizing carrier gases or higher O partial pressures, however, it is now possible to circumvent this *materials gap*,³⁰ enabling a detailed characterization of $\text{RuO}_2(110)$ domains formed on the model $\text{Ru}(0001)$ surface with the techniques of surface science.^{9,17-19,21-24}

The results of the present study, however, show that the surface termination of these domains changes with the O_2 pressure as well. Unaware of this dependence on the O_2 pressure, previous researchers proposed a reaction mechanism for the CO oxidation based solely on the stoichiometric $\text{RuO}_2(110)\text{-O}^{\text{bridge}}$ termination that was characterized in the respective low-energy electron-diffraction (LEED) study under UHV conditions.^{18,19} While it is presently not clear to what extent the O^{cus} atoms additionally present at atmo-

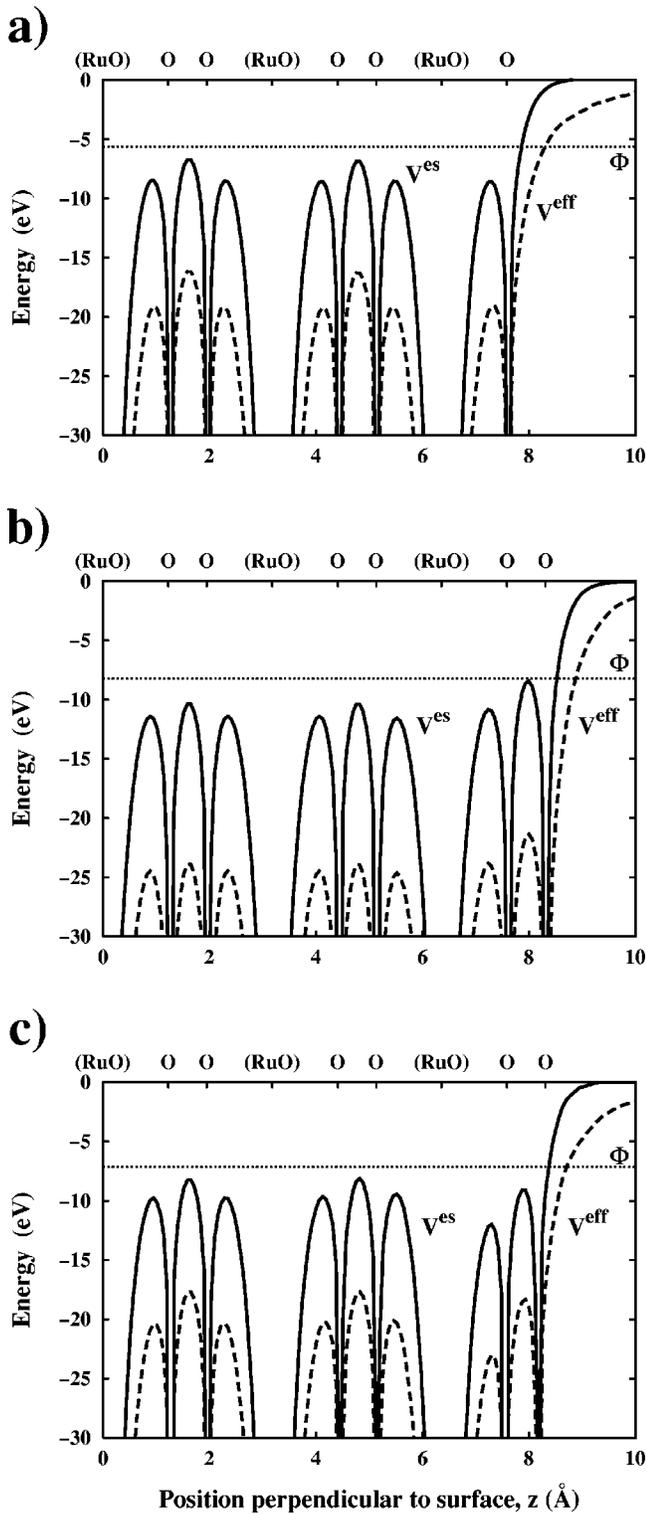


FIG. 5. (x,y) -averaged Kohn-Sham effective, potential $V^{\text{eff}}(z)$ (dashed line) and electrostatic potential $V^{\text{es}}(z)$ (solid line), along the (110) direction perpendicular to the surface z . Also shown is the work function Φ , by the dotted line. (a) Bulk-truncated $\text{RuO}_2(110)\text{-O}^{\text{bridge}}$ termination ($\Phi = 5.7$ eV). (b) Bulk-truncated $\text{RuO}_2(110)\text{-O}^{\text{cus}}$ termination ($\Phi = 8.2$ eV). (c) Fully relaxed $\text{RuO}_2(110)\text{-O}^{\text{cus}}$ termination ($\Phi = 7.2$ eV). The top x axis marks the position of O-(RuO)-O layers in the crystal.

spheric pressures are involved in the reaction,^{23,24} we note that their binding energy of 1 eV with respect to molecular oxygen renders them a catalytically rather interesting species. Consideration of high-pressure O^{cus} atoms might therefore be of crucial importance to understand the reactivity of $\text{RuO}_2(110)$, highlighting the delicacy with which the results of UHV spectroscopies and post-exposure experiments have to be applied to effectively model catalysis and steady-state conditions.

Only very recently has UHV equipment been able to stabilize the high-pressure $\text{RuO}_2(110)\text{-O}^{\text{cus}}$ termination intentionally by postdosing O_2 at low temperatures.^{9,17,23,24} Temperature desorption spectroscopy (TDS) experiments found the corresponding excess O^{cus} atoms to be stable up to about 300–550 K in UHV.¹⁷ This agrees nicely with the calculated transition temperature of 450 ± 50 K at the crossover point between the two terminations for a pressure of $10^{-12 \pm 2}$ atm, presumably present during a typical TDS experiment,³¹ cf. the bottom x axis of Fig. 4. However, the actual desorption temperature is of course significantly higher for the orders of magnitude higher O_2 partial pressures present in catalytic applications. This is exemplified by the temperature scale on the top x axis of Fig. 4 at a pressure of $p = 1$ atm, representative of the early high-pressure experiments addressing the high CO/CO_2 conversion rates of Ru catalysts.^{27,28} The corresponding elevated transition temperature of 900 K shows that O^{cus} atoms were most probably present on oxidized $\text{RuO}_2(110)$ domains in all of these experiments.

The presence of the hitherto unaccounted for high-pressure termination of $\text{RuO}_2(110)$ might therefore be a key to understanding the data obtained from grown $\text{RuO}_2(110)$ films or oxidized $\text{Ru}(0001)$ surfaces, which are unanimously prepared under highly O-rich conditions. An example of this can be seen in a preceding publication,³² in which it was suggested that the controversially discussed, largely shifted satellite peak in Ru $3d$ x-ray photoemission spectroscopy data from such surfaces,^{16,33} might receive some signal from the $\text{Ru}^{\text{cus},6f}$ atoms in the $\text{RuO}_2(110)\text{-O}^{\text{cus}}$ termination, which experience a significantly different environment due to the aforementioned very short bonds to the O^{cus} atoms.

Whether or not the high-pressure termination created during the preparation of the crystal survives during the transfer to UHV depends then on the details of the transfer itself, e.g., on whether or not the temperature is kept constant while the pressure goes down to its base value after exposure. A dependence of the TDS data of an oxygen-rich $\text{Ru}(0001)$ surface on these parameters has already been reported and considered by Böttcher and Niehus.¹⁷ On the other hand, the final annealing step to 600 K after transfer to UHV employed in the LEED work identifying $\text{RuO}_2(110)$ domains on oxidized $\text{Ru}(0001)$ ^{18,19} explains why there only the stoichiometric $\text{RuO}_2(110)\text{-O}^{\text{bridge}}$ termination could be characterized (cf. Fig. 3).

Such dependences on the experimental preparation have hitherto often been neglected, entailing a low comparability of data sets obtained in different groups. Instead, the present results demonstrate that systematic investigations in the whole (T,p) range are required to fully identify the surface structure and composition of oxide surfaces at realistic con-

ditions, which in turn is a prerequisite before tackling the long-term goal of understanding the function of the latter in the wealth of everyday applications.

IV. SUMMARY

In conclusion we have combined density-functional theory (DFT) and classical thermodynamics to determine the lowest energy structure of an oxide surface in equilibrium with an O environment. The formalism is applied to RuO₂(110) showing that apart from the expected stoichiometric surface, a so-called polar termination with an excess of oxygen (O^{cus}) is stabilized at high O chemical potentials. Depending on the details of the experimental preparation conditions, either of the two terminations can therefore be present, and their different properties have to be taken into account when trying to understand the experimental data or aiming to extrapolate the results of UHV *ex situ* techniques to high-pressure applications like oxidation catalysis.

A polar termination is traditionally not considered to be stable within the framework of electrostatic arguments based on the ionic model of oxides. We show that this reasoning is of little validity, as it assumes all atoms to be in the same bulk-like state. On the contrary, the additional structural and electronic degrees of freedom at an oxide surface allow substantial deviations from these bulk properties and may thus stabilize even nonstoichiometric surface terminations. A similar conclusion was previously also reached for the O-rich (0001) termination of corundum-structured α -Fe₂O₃ indicating that polar surfaces might indeed be a more general feature of transition-metal oxides. The concentration of oxygen vacancies found for the polar termination of RuO₂(110) at atmospheric pressures and elevated temperatures could finally offer a possible explanation of the high catalytic activity reported for this surface.

ACKNOWLEDGMENTS

We thank Anne Chaka for a careful reading of this paper. This work was partially supported by the Deutsche Forschungsgemeinschaft (Schwerpunkt ‘‘Katalyse’’).

APPENDIX

1. Vibrational contribution to the Gibbs free energy

The vibrational contribution to the Gibbs free energy comprises vibrational energy and entropy [cf. Eq. (15)]. Both can be calculated from the partition function of an N -atomic system³⁴

$$Z = \sum_{i=1}^{3N} \int \frac{d\mathbf{k}}{(2\pi)^3} \sum_{n=0}^{\infty} e^{-[n+(1/2)]\beta\hbar\omega_i(\mathbf{k})}, \quad (\text{A1})$$

where $\beta = 1/kT$ and the $\omega_i(\mathbf{k})$ are the $3N$ vibrational modes. The vibrational energy is then given by

$$E^{\text{vib.}}(T, V, N) = -\frac{\partial}{\partial\beta} \ln Z, \quad (\text{A2})$$

and the entropy is defined as

$$S^{\text{vib.}}(T, V, N) = k(\ln Z + \beta E^{\text{vib.}}). \quad (\text{A3})$$

Writing $F^{\text{vib.}}(T, V, N)$ as a frequency integral including the phononic density of states, $\sigma(\omega)$, and using the relation $F^{\text{vib.}} = E^{\text{vib.}} - TS^{\text{vib.}}$, one arrives at

$$F^{\text{vib.}}(T, \omega) = \hbar\omega \left(\frac{1}{2} + \frac{1}{e^{\beta\hbar\omega} - 1} \right) - kT \left[\frac{\beta\hbar\omega}{e^{\beta\hbar\omega} - 1} - \ln(1 - e^{-\beta\hbar\omega}) \right]. \quad (\text{A4})$$

2. Ideal gas expression for $\mu_{\text{O}_2}(T, p)$

For an ideal gas of N particles at constant pressure p and temperature T , the chemical potential is simply given by the Gibbs free energy per atom:

$$\mu = \left(\frac{\partial G}{\partial N} \right)_{T, p, N} = \frac{G}{N}. \quad (\text{A5})$$

As the Gibbs free energy is a potential function depending on pressure and temperature, its total derivative can be written as

$$dG = \left(\frac{\partial G}{\partial T} \right)_p dT + \left(\frac{\partial G}{\partial p} \right)_T dp = -SdT + Vdp, \quad (\text{A6})$$

where we have inserted the Maxwell relations for the entropy, S and volume V . Using the ideal gas equation of state, $pV = NkT$, the partial derivative of $G(T, p)$ with respect to pressure at constant temperature is consequently

$$\left(\frac{\partial G}{\partial p} \right)_T = V = \frac{NkT}{p}. \quad (\text{A7})$$

In turn, a finite pressure change from p to p° results in

$$G(T, p) - G(T, p^\circ) = \int_{p^\circ}^p \left(\frac{\partial G}{\partial p} \right)_T dp = NkT \ln(p/p^\circ). \quad (\text{A8})$$

Combining Eqs. (A5) and (A8), for the chemical potential of O we can finally write

$$\mu_{\text{O}}(T, p) = 1/2 \mu_{\text{O}_2}(T, p) = \mu_{\text{O}}(T, p^\circ) + 1/2 kT \ln(p/p^\circ), \quad (\text{A9})$$

which is the expression used in Sec. II E.

- ¹C. Stampfl, M. V. Ganduglia-Pirovano, K. Reuter, and M. Scheffler, *Surf. Sci.* **500** (in press); preprint download under <http://www.fhi-berlin.mpg.de/th/pub01.html>.
- ²X.-G. Wang, W. Weiss, Sh.K. Shaikhutdinov, M. Ritter, M. Petersen, F. Wagner, R. Schlögl, and M. Scheffler, *Phys. Rev. Lett.* **81**, 1038 (1998).
- ³X.-G. Wang, A. Chaka, and M. Scheffler, *Phys. Rev. Lett.* **84**, 3650 (2000).
- ⁴V.E. Henrich and P.A. Cox, *The Surface Science of Metal Oxides* (Cambridge University Press, Cambridge, 1994).
- ⁵C. Noguera, *Physics and Chemistry at Oxide Surfaces* (Cambridge University Press, Cambridge, 1996).
- ⁶C. Noguera, *J. Phys.: Condens. Matter* **12**, R367 (2000).
- ⁷*CRC Handbook of Chemistry and Physics*, 76th ed. (CRC Press, Boca Raton FL, 1995).
- ⁸R. Heid, L. Pintschovius, W. Reichardt, and K.-P. Bohnen, *Phys. Rev. B* **61**, 12 059 (2000).
- ⁹Y.D. Kim, A.P. Seitsonen, S. Wendt, J. Wang, C. Fan, K. Jacobi, H. Over, and G. Ertl, *J. Phys. Chem.* **105**, 3752 (2001).
- ¹⁰D.R. Stull and H. Prophet, *JANAF Thermochemical Tables*, 2nd ed. (U.S. National Bureau of Standards, Washington, DC, 1971).
- ¹¹P. Blaha, K. Schwarz and J. Luitz, WIEN97, *A Full Potential Linearized Augmented Plane Wave Package for Calculating Crystal Properties* (Karlheinz Schwarz, Technical Universität Wien, Austria, 1999. ISBN 3-9501031-0-4).
- ¹²B. Kohler, S. Wilke, M. Scheffler, R. Kouba, and C. Ambrosch-Draxl, *Comput. Phys. Commun.* **94**, 31 (1996).
- ¹³M. Petersen, F. Wagner, L. Hufnagel, M. Scheffler, P. Blaha, and K. Schwarz, *Comput. Phys. Commun.* **126**, 294 (2000).
- ¹⁴J. P. Perdew, K. Burke, and M. Ernzerhof, *Phys. Rev. Lett.* **77**, 3865 (1996).
- ¹⁵P. I. Sorantin and K. H. Schwarz, *Inorg. Chem.* **31**, 567 (1992).
- ¹⁶Lj. Atanasoska, W. E. O'Grady, R. T. Atanasoski, and F. H. Polak, *Surf. Sci.* **202**, 142 (1988).
- ¹⁷A. Böttcher and H. Niehus, *Phys. Rev. B* **60**, 14 396 (1999).
- ¹⁸H. Over, Y. D. Kim, A. P. Seitsonen, S. Wendt, E. Lundgren, M. Schmid, P. Varga, A. Morgante, and G. Ertl, *Science* **287**, 1474 (2000).
- ¹⁹Y. D. Kim, H. Over, G. Krabbes, and G. Ertl, *Top. Catal.* **14**, 95 (2001).
- ²⁰J. P. Perdew and Y. Wang, *Phys. Rev. B* **45**, 13 244 (1992).
- ²¹A. Böttcher, H. Niehus, S. Schwegmann, H. Over, and G. Ertl, *J. Phys. Chem. B* **101**, 11 185 (1997).
- ²²A. Böttcher, H. Conrad, and H. Niehus, *Surf. Sci.* **452**, 125 (2000).
- ²³C. Y. Fan, J. Wang, K. Jacobi, and G. Ertl, *J. Chem. Phys.* **114**, 10 058 (2001).
- ²⁴J. Wang, C. Y. Fan, K. Jacobi, and G. Ertl, *Surf. Sci.* **481**, 113 (2001).
- ²⁵P. W. Tasker, *J. Phys. C* **12**, 4977 (1979).
- ²⁶T. E. Madey, H. A. Engelhardt, and D. Menzel, *Surf. Sci.* **48**, 304 (1975).
- ²⁷N. W. Cant, P. C. Hicks, and B. S. Lennon, *J. Catal.* **54**, 372 (1978).
- ²⁸C. H. F. Peden and D. W. Goodman, *J. Phys. Chem.* **90**, 1360 (1986).
- ²⁹C. Stampfl, S. Schwegmann, H. Over, M. Scheffler, and G. Ertl, *Phys. Rev. Lett.* **77**, 3371 (1996).
- ³⁰A. Böttcher and H. Niehus, *J. Chem. Phys.* **110**, 3186 (1999).
- ³¹A TDS experiment with a low heating rate of 6 K/s is considered to refer to a situation where the system is always close to equilibrium. Indeed, the agreement of the experimental results of Böttcher and Niehus (Ref. 30) with our calculations confirms this assumption.
- ³²K. Reuter and M. Scheffler, *Surf. Sci.* **490**, 20 (2001).
- ³³Y. J. Kim, Y. Gao, and S. A. Chambers, *Appl. Surf. Sci.* **120**, 250 (1997), and references therein.
- ³⁴N. W. Ashcroft and N. D. Mermin, *Solid State Physics* (CBS Publishing, Tokyo 1981).