

This document is confidential and is proprietary to the American Chemical Society and its authors. Do not copy or disclose without written permission. If you have received this item in error, notify the sender and delete all copies.

Towards Cove-Edged Low Band Gap Graphene Nanoribbons

Journal:	<i>Journal of the American Chemical Society</i>
Manuscript ID:	ja-2015-030178.R1
Manuscript Type:	Article
Date Submitted by the Author:	18-Apr-2015
Complete List of Authors:	Liu, Junzhi; max-planck institute for polymer research, Li, Bo-Wei; Xiamen University, Tan, Yuanzhi; Xiamen University, chemistry Giannakopoulos, Angelos; University of Mons, Sanchez-Sanchez, Carlos ; Nanotech@surfaces Laboratory, Empa, Swiss Federal Laboratories for Materials Science and Technology, Beljonne, David; Université de Mons - UMONS / Materia Nova, Chimie des Matériaux Nouveaux & Centre d'Innovation et de Recherche en Matériaux Polymères Ruffieux, Pascal; EMPA, nanotech@surfaces Laboratory Fasel, Roman; EMPA - Swiss Fed. Lab. for Materials Testing and Research, Nanotech@Surfaces Laboratory Feng, Xinliang; Dresden University of Technology, Molecular Functional Materials Müllen, Klaus; Max-Planck-Institute for Polymer Research,

SCHOLARONE™
Manuscripts

Towards cove-edged low band-gap graphene nanoribbons

Junzhi Liu,[†] Bo-Wei Li,[‡] Yuan-Zhi Tan,[‡] Angelos Giannakopoulos,[‡] Carlos Sanchez-Sanchez,[§] David Beljonne,[‡] Pascal Ruffieux,[§] Roman Fasel,^{§#} Xinliang Feng^{*#} and Klaus Müllen^{*†}

[†]Max-Planck Institut für Polymerforschung, Ackermannweg 10, 55128, Mainz, Germany

[‡]State Key Laboratory of Physical Chemistry of Solid Surfaces and Department of Chemistry, College of Chemistry and Chemical Engineering, Xiamen University, Xiamen, 361005, China.

[‡]Laboratory for Chemistry of Novel Materials, University of Mons, Place du Parc 20, B-7000 Mons, Belgium

[§]Nanotech@surfaces Laboratory, Empa, Swiss Federal Laboratories for Materials Science and Technology, 8600 Dübendorf, Switzerland

[#]Department of Chemistry and Biochemistry, University of Bern, Freiestrasse 3, 3012 Bern, Switzerland

^{*}Center for Advancing Electronics Dresden (cfaed) & Department of Chemistry and Food Chemistry, Technische Universität Dresden, 01062 Dresden, Germany


KEYWORDS. nanographene, ribbons, low band gap, cove edge structure.

ABSTRACT: Graphene nanoribbons (GNRs), defined as nanometer-wide strips of graphene, have attracted increasing attention as promising candidates for next-generation semiconductors. Here, we demonstrate a bottom-up strategy toward novel low band gap GNRs ($E_g=1.70$ eV) with a well-defined cove-type periphery both in solution and on a solid substrate surface with chrysene as the key monomer. Corresponding cyclized chrysene-based oligomers consisting of the dimer and tetramer are obtained via an Ullmann coupling followed by oxidative intramolecular cyclodehydrogenation in solution, and much higher GNR homologues via on-surface synthesis. These oligomers adopt non-planar structures due to the steric repulsion between the two C-H bonds at the inner cove position. Characterizations by single crystal X-ray analysis, UV-vis absorption spectroscopy, NMR spectroscopy, and scanning tunneling microscopy (STM) are described. The interpretation is assisted by density functional theory (DFT) calculations.

INTRODUCTION

Graphene nanoribbons (GNRs) have been proven to be unique conjugated polymers.^[1-5] In contrast to graphene, which is semimetallic with zero-band gap, GNRs are tunable band gap semiconductors and thus attractive materials for nanoscale electronic devices, such as field effect transistors.^[6-9] The width and edge structure of GNRs essentially determine their electronic features such as the band gap and spintronic properties.^[10-15] One can envisage two different classes of GNRs depending on their periphery structure of the edges (Scheme 1), zigzag-GNRs (ZGNRs) and armchair-GNRs (AGNRs), and these have been extensively investigated both theoretically and experimentally. Two main strategies have been recently established to prepare GNRs, namely “top-down” and “bottom-up” approaches. The “top-down” approach, such as the cutting of graphene, sonochemical extraction from expanded graphite and unzipping of carbon nanotubes, has produced GNRs with sub-10 nm widths,^[16-22] revealing their semiconducting nature and excellent charge transport properties. However, “top-down” methods generally suffer from low yields and non-uniform widths, as

well as ill-defined edge structures. Moreover, to achieve sufficient band gap control, GNRs should be narrowed to sub-5 nm, at which width scale current lithography methods meet limitations. Thereby, it is highly desirable to produce GNRs with a precise periphery structure and controllable width.

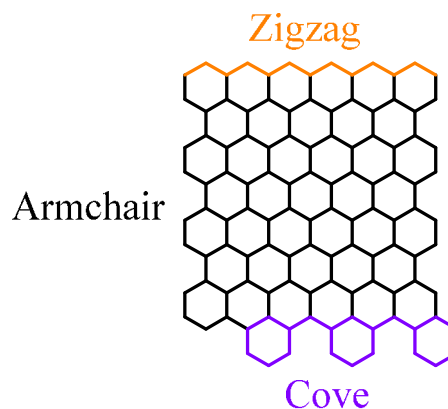

Scheme 1. The edge structure of graphene.


In contrast, “bottom-up” chemical synthesis provides structurally well-defined GNRs with uniform structures.^{15, 23-34} The synthesis is based on solution-mediated or surface-assisted cyclodehydrogenation and “planarization” of three-dimensional polyphenylene precursors. The polyphenylene precursors are designed and synthesized from small organic molecules, providing access to GNRs with different widths and edge structures. Up to now, “bottom-up” synthesis has mainly focused on AGNRs, whereas GNRs with zigzag or cove-type edges (Scheme 1) have remained elusive.^[35-39]

In this study, we demonstrate a novel type of GNR containing a unique cove-type periphery based on 11,11'-dibromo-5,5'-bischrysene (**5**) as the key monomer (Scheme 2). As model subunits of the infinite **cove-edged GNRs**, fused chrysene-based oligomers or polycyclic aromatic hydrocarbons (PAHs), namely the dimer **1** (two units of chrysene) and tetramer **2** (four units of chrysene), can be synthesized via the Ullmann coupling reaction of 11,11'-dibromo-5,5'-bischrysene (**5b**) followed by intramolecularly oxidative cyclodehydrogenation in solution. The structure of the tetramer **2** is unambiguously proven by X-ray single crystal analysis. In comparison with GNRs with armchair or zigzag edges, the cove-edged analogues manifest characteristic non-planar alternative “up-down” conformations. These PAHs are characterized by UV-vis, matrix-assisted laser desorption/ionization time-of-flight (MALDI-TOF) mass spectrometry (MS) and cyclic voltammetry (CV). The optical band-gap of the tetramer is 1.9


eV from the onset of the UV-vis absorption spectrum. We further demonstrate the surface-mediated synthesis of **cove-edged GNRs** based on monomer **5a**, thereby achieving much longer GNRs with lengths up to 20 nm and a width of 0.9 nm. From spectroscopic data and DFT calculations, **cove-edged GNRs** are shown to possess smaller band-gaps than AGNRs of similar width.^[29]

RESULTS AND DISCUSSION

Oligomer Synthesis in solution. First, the key building block 11,11'-dibromo-5,5'-bischrysene (**5**) was synthesized as depicted in Scheme 3. Compound **5** was obtained in five steps from 1-bromo-2-iodobenzene (**6**). 1-bromo-2-(trimethylsilylethynyl)benzene (**7**) was prepared by a selective Sonogashira reaction of **6** with trimethylsilylacetylene in excellent yield. Afterwards, the bromo group in compound **7** was transformed into the iodo analogue by treatment with 1,2-diiodoethane, affording 1-iodo-2-(trimethylsilylethynyl)benzene **8** in yields of 88-90%. Then, Glaser self-coupling of **8** with CuCl as a catalyst under an ambient atmosphere provided 1,4-bis(2-iodophenyl)-diacetylene (**9**) in 78-83% yield. Subsequently, the key precursor 1,4-bis(2-(3-bromonaphthalen-2-yl)phenyl)buta-1,3-diyne (**11**) was furnished through the Suzuki coupling of **9** and 2-bromo-3-naphthaleneboronic acid (**10**) in 50-56% yield. A final cyclization of compound **11** with PtCl₂ as a catalyst under an argon atmosphere at 85 °C for 24 hours afforded the desired compound **5** in 70-78% yield.

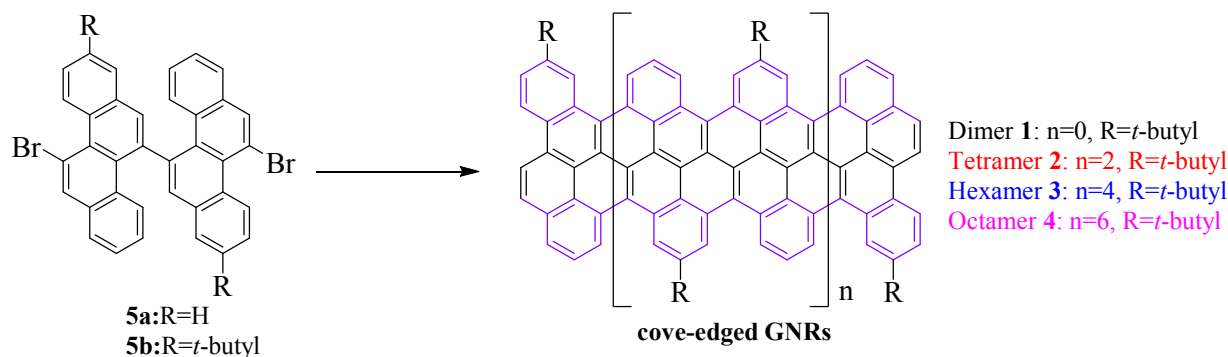


Scheme 2. The structure of targeted cove-edged GNRs.

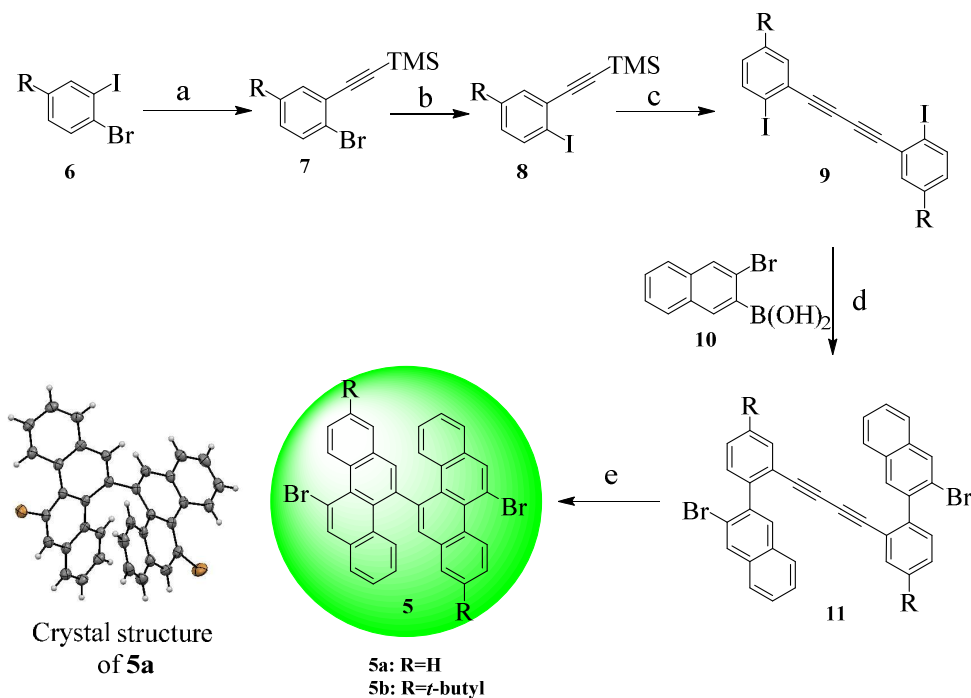

24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

^aReagents and conditions: a) PdCl₂(PPh₃)₂, CuI, Et₃N, THF, r.t., 24h, **7a**: 82 %, **7b**: 85 %. b) *n*-BuLi, THF, ICH₂CH₂I, -78 °C to r.m, **8a**: 88 %, **8b**: 90 %. c) CuCl, DMF, Air, 80 °C, 6h, **9a**: 78 %, **9b**: 83 %. d) Pd(PPh₃)₄/Na₂CO₃, THF/H₂O/EtOH, 60 °C, 24h, **11a**: 50 %, **11b**: 56 %. e) PtCl₂, Toluene, 85 °C, 24h, **5a**: 70 %, **5b**: 78 %.

Scheme 3. The synthetic route toward the key building block 11,11'-dibromo-5,5'-bischrysene 5.

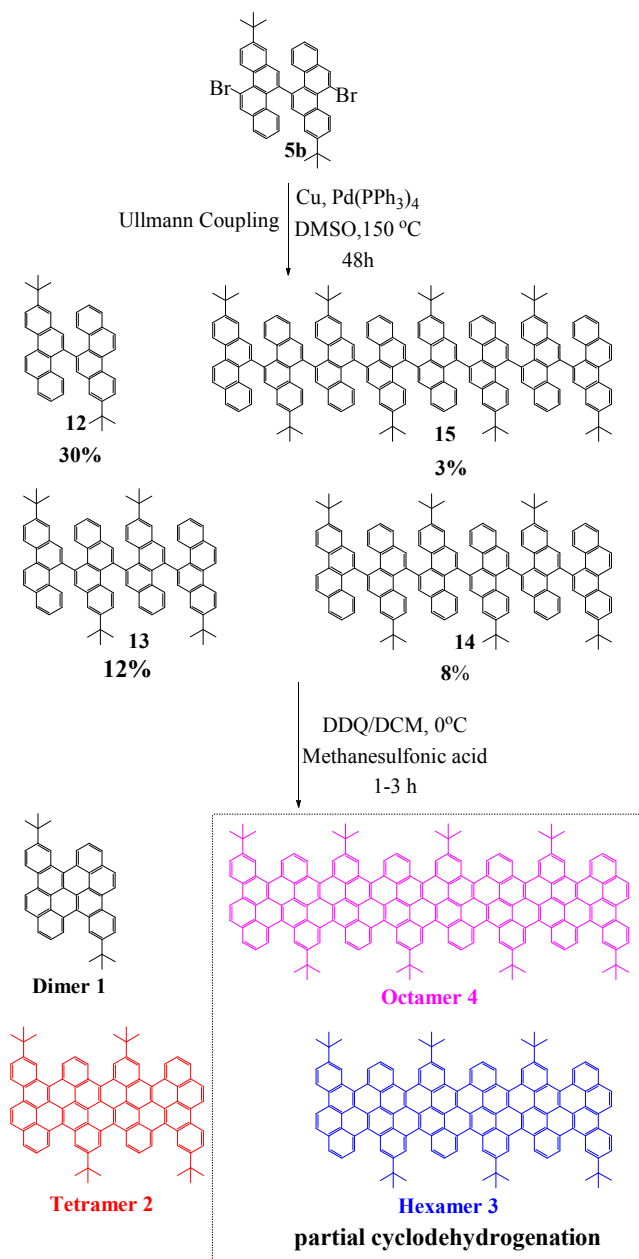

Scheme 4. The synthetic route toward the oligomers and fused dimer **1** and tetramer **2**.

Next, the corresponding chrysene oligomers were achieved by Ullmann coupling at 150 °C in dimethyl sulfoxide (DMSO) based on the core building block **5b**, as depicted in Scheme 4. Initially, a Yamamoto coupling of compound **5b** was attempted at 80 °C and 100 °C in toluene and dimethylformamide (DMF) solutions, respectively. The reaction failed even under microwave-assistance, most likely due to the high steric repulsion between the two C-H bonds at the bay-positions of chrysene. Therefore, we turned our attention to the Ullmann coupling at high temperature. Ullmann coupling, when tried at higher temperatures, did not yield the corresponding polymers. Nevertheless, the crude oligomeric mixtures were first separated by silica gel column chromatography, and the pure homologues **12**, **13**, **14** and **15** were obtained by

recycling GPC. Afterwards, their cyclodehydrogenation was carried out by using iron(III) chloride (FeCl₃) or 2,3-dichloro-5,6-dicyano-1,4-benzoquinone (DDQ)/ trifluoromethanesulfonic acid (CF₃SO₃H) as the Lewis oxidant/acid. The former conditions produced mainly chlorinated products, as confirmed by MALDI-TOF MS (Figure S6). In contrast, cyclodehydrogenation with DDQ and CF₃SO₃H afforded the desired fused dimer (**1**) and tetramer (**2**) successfully. Compounds **1** and **2** were unambiguously characterized by MALDI-TOF MS, as depicted in Figure 1. There is only one dominant peak in the respective mass spectra of **1** and **2**, revealing its defined molecular composition; the isotopic distribution pattern of the mass peak is in good agreement with the calculated patterns. Unfortunately, although we could isolate the precursors of hexamer **14** and octamer **15** from the Ullmann-reaction mixtures, only partially fused derivatives of hexamer (**3**) and octamer (**4**) were obtained after cyclodehydrogenation, which prevented further purification and separation (Figures S7-S11).

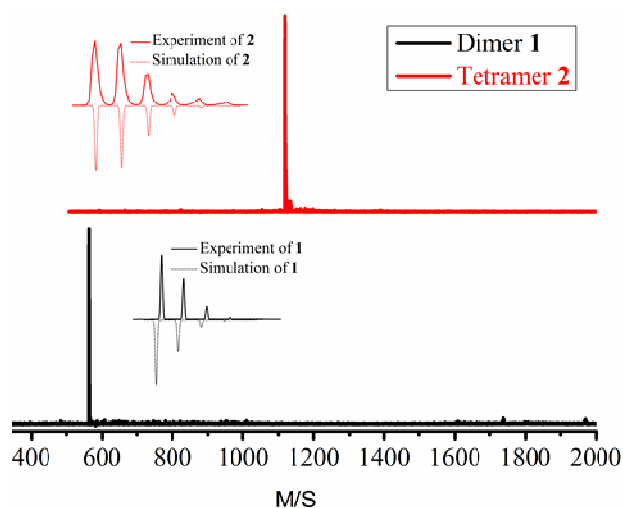


Figure 1. MALDI-TOF MS of **1** and **2**.

Structure analysis of 2. Single crystals of **2** were grown by slow evaporation from a carbon disulfide solution. Compound **2** is a ribbon-shaped molecule with a length and width of 1.8 and 0.9 nm, respectively (Figure 2), and thus serves as a molecular model of its corresponding **cove-edged GNRs**. Different from the reported graphene molecules with zigzag or armchair peripheries that mostly have planar structures, the outstanding feature of **2** is its non-planar π -conjugated carbon skeleton, which results from the steric hindrance of its cove periphery. Notably, the benzenoid rings in the cove region in **2** adopt an alternating “up-down” conformation with a mean torsional angle of 38.2°, which suggests that the **cove-edged GNRs** could also adopt a similar alternating “up-down” conformation at the periphery.

The distorted carbon framework makes **2** chiral, as shown in Figure 2a. Remarkably, one enantiomer forms a dimer by intermolecular π - π interactions with an interlayer distance as short as 3.22 Å (Figure 2b), whereas such a

dimer assembles with its corresponding enantiomeric isomer by face-to-edge CH- π interactions (Figure 2c). Further attempts to separate the enantiomer pair of **2** in solution by chiral HPLC were unfortunately not successful. This is most likely due to the low activation barrier of racemization, as suggested by DFT calculations (vide infra).

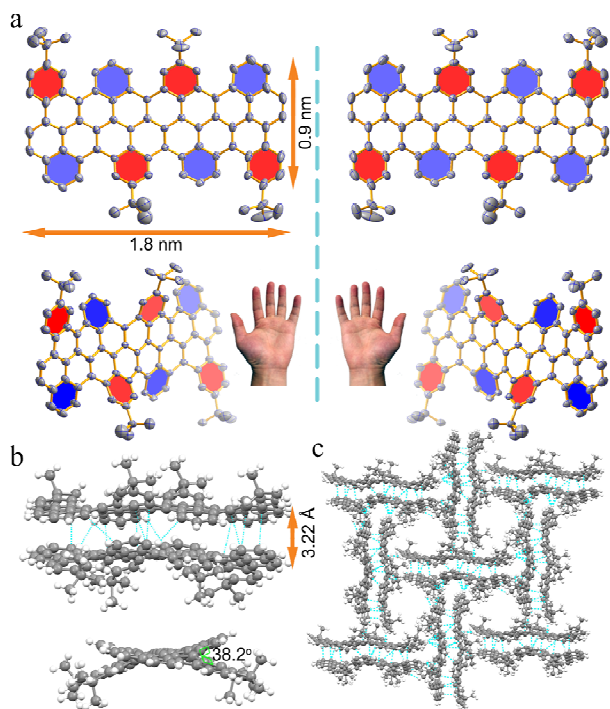


Figure 2. Crystal structure of **2**. (a) Top view of enantiomer pair of **2**. (b) Crystal packing of dimer from side view. (c) Crystal packing of face-to-face (δ - δ) and face-to-edge (CH- δ).


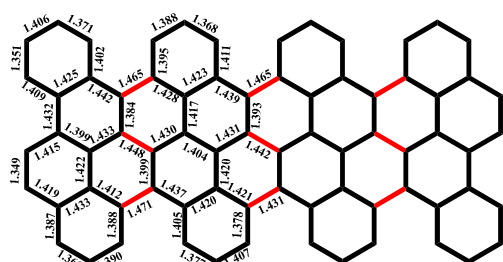


Figure 3. Bond lengths of **2**.

The X-ray diffraction data also disclose the detailed bond parameters of **2** (Figure 3). The C-C bonds at the cove region are obviously longer (1.46 Å), most likely due to the repulsive forces of congested hydrogen atoms. In **2**, the chrysene units connect with each other by a single C-C bond, and the distribution of the bond lengths in the chrysene unit is consistent with the resonance structure shown in Scheme 5. The short bond lengths of C(1)-C(2) and C(3)-C(4) support resonance structure **2**, whereas the short bond lengths of C(5)-C(6) and C(7)-C(8) imply

structure **2-1**. Compound **2** thus adopts a π -bond localized resonance structure in the solid state, which is different from that prevailing in fully benzenoid PAHs. Moreover, the bonding-antibonding pattern calculated at the DFT level for the HOMO (HOCO) of the oligomers (ribbons) strongly supports **2-1** as the dominant Clar formula (Figure S12).

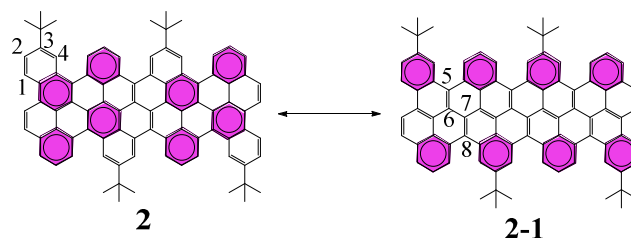

Scheme 5. Resonance structure of **2**: Clar formula is represented by two resonance structures comprising eight aromatic sextets.

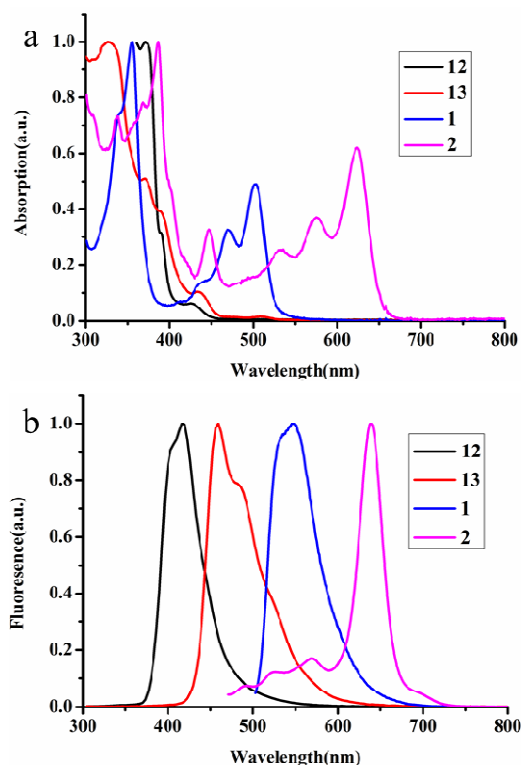


Figure 4. (a) UV-vis absorption spectra and (b) Fluorescence spectra of precursor **12**, **13** and fused **1**, **2** (for all spectra: 10^{-5} M in THF).

Optical and electrochemical properties. The UV-vis absorption spectra of precursors **12** and **13**, as well as the cyclodehydrogenation compounds **1** and **2** in THF solution, are compared in Figure 4a. This is possible for the fused **1** and **2** because they have sufficient solubility in common organic solvents such as THF, toluene and trichlorobenzene as a result of the non-planar cove structure at the periphery and the presence of *t*-butyl substituents. The main absorption bands of **1** and **2** are signifi-

compd	λ_{\max} (nm)	λ_{em} (nm)	λ_{edge} (nm)	HOMO (eV) ^a	LUMO (eV) ^a	HOMO (eV) ^b	LUMO (eV) ^c	$E_g(\text{opt})$ (eV) ^d	$E_g(\text{cal})$ (eV) ^a
1	503	546	526	-4.67	-2.06	-5.12	-2.76	2.36	2.61
2	623	638	652	-4.38	-2.37	-4.98	-3.08	1.90	2.01
GNRs	---	---	---	-4.22	-2.52	---	---	---	1.70

Table 1. Optical and electrochemical property for the **1**, **2** and its corresponding **cove-edged GNRs**. (a) Calculations were performed at the B₃LYP/6-31G (d,p) level; (b) HOMO levels were calculated from the measured first oxidation potential of CV; (c) LUMO levels were calculated from the optical band gap $E_g(\text{opt})$ and the respective HOMO levels; (d) Optical band gaps were estimated from the wavelength of the absorption peak.

cantly red shifted compared to those of precursors **12** and **13**. Notably, compounds **1** and **2** exhibit similarly shaped UV-vis absorption patterns, including one major band between 300-400 nm and another major band peaking at 502 nm with two shoulder peaks at 469 and 439 nm for **1**. Compound **2** shows a significant absorption maximum bathochromically shifted by 121 nm relative to that of **1**, with an absorption maximum at 623 nm and two other shoulder peaks at 574 and 532 nm, respectively. The optical band gaps of **1** and **2** are determined from the onsets of their UV-vis absorption spectra, which are 2.36 and 1.90 eV, respectively. This result suggests that the energy gap drastically decreases upon increasing the conjugation length of this type of cove ribbon-shaped molecule. Interestingly, cove-edged tetramer **2** features a similarly low band gap (1.90 eV) compared to our previous bottom-up synthesized AGNRs (approximately 1.88 eV) of comparable width but greatly extended length (>100 nm).^[29] The emission spectra of precursors **12**, **13** and fused **1**, **2** are shown in Figure 4b. These compounds show fluorescence in THF solution with maxima at 416 and 459 nm for **12** and **13** and 546 and 638 nm for **1** and **2**, respectively. The electrochemical properties of **1** and **2** were investigated by means of cyclic voltammetry (CV) in THF solution (Figure S4). According to the CV analysis, compounds **1** and **2** show two reversible oxidation and one irreversible reduction. The HOMO energy levels are estimated from the onsets of the reversible oxidation peaks to be -5.12 and -4.98 eV for **1** and **2**, respectively. Thus, the LUMO energy levels are estimated from the optical gaps determined from the onsets of the absorption spectra, and the extracted values are listed in Table 1. These results are fully consistent with the DFT calculations (see below).

Surface synthesis. As the solution approach suffers from steric hindrance when trying to achieve high molecular weight precursor polymers of chrysene, we turned our attention to the surface-assisted synthesis employing **5a**. The on-surface approach is based on the same two steps as used in solution. Precursor monomers are deposited on

a supporting media (in this case the solid Au (111) surface) where they are thermally driven to first form polyphenylene oligomers via dehalogenation and subsequent radical combination and then form GNRs by surface-assisted cyclodehydrogenation. The resulting **cove-edge GNRs** grown under ultra-high vacuum conditions are shown in the STM^[40] images in Figure 5, in which the lengths of the GNRs are up to 20 nm. Deposition of monomer **5a** on a clean Au (111) surface held at 160°C and post-annealing of the system at 360°C yields GNRs with lengths ranging from tetramers to hexadecamers (sixteen chrysene repeating units). There is, however, a clear tendency for interribbon cross-coupling. This can be rationalized in terms of on-surface diffusion and reaction during the cyclodehydrogenation step. The barriers to cyclodehydrogenation and to dehydrogenation at the edge are close. Edge radicals will thus be formed, which attack the C-H from neighboring ribbons and cross-couple, thus partially hindering the formation of longer ribbons (Figure 5a). When on a surface, oligomers adopt a flat geometry due to the tendency of aromatic structures to maximize van der Waals interactions with the surface, in contrast to the non-planarity obtained in bulk. The apparent height of the GNRs is approximately 1.7 Å, in good agreement with the values observed for other planar aromatic species on metallic surfaces. Despite their tendency to cross-couple, it is possible to find isolated oligomers such as the ones shown in Figure 5b and c. In both cases, the cove-edged structure is discerned, in good agreement with the superimposed schematic model of the ribbon. The formation of longer GNRs under UHV conditions on metallic surfaces compared to those obtained in solution can be rationalized in terms of monomer confinement. Monomers deposited on a surface are confined to two dimensions, in contrast to in solution-based methods, which increasing the probability of monomers finding each other and reacting to form longer oligomers. Additionally, metallic surfaces are known to act as catalyst, thus increasing the oligomerization yield over that of solution-based methods on Au (111).

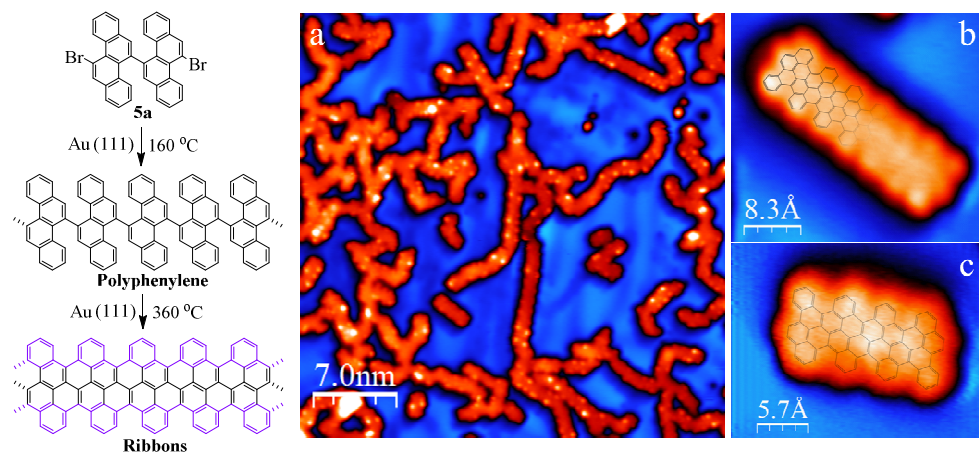


Figure 5. Set of STM images showing **cove-edged GNRs** grown via on-surface bottom-up reaction of monomer **5a** under ultra-high vacuum conditions. (a) Long range STM image of the oligomers after cyclodehydrogenation. $I=100\text{pA}$ $V=-1.20\text{V}$. (b) and (c) High resolution STM images of two isolated short GNRs with schematic models superimposed. (b) $I=400\text{pA}$ $V=-0.90\text{V}$. (c) $I=200\text{pA}$ $V=-0.70\text{V}$.

DFT Calculations. First principle calculations were carried out to obtain further insight into the electronic structure of the oligomers and their corresponding cove-edged GNRs. Geometry optimization was performed at the B3LYP level with the 6-31G (d,p) basis set using the Gaussian09 simulation package. The fused chrysene oligomers adopt a non-planar conformation, in line with the crystal structural data. Interestingly, multiple conformers that differ by their relative torsion angles along the ribbon (alternating ‘top-down’ or ‘helical’) and slightly different optical properties are predicted to coexist (Figures S15 and S22). The HOMO and the LUMO orbitals of the most stable conformers are shown in Figure 6, together with their corresponding energies. From these calculations, the band-gaps of **1** and **2** are 2.62 and 2.01 eV, respectively. The computed one-electron bandgap is reduced upon increasing the ribbon length and is in excellent agreement with experimental results (Table 1). This translates into a red-shifted optical absorption with extended ribbon length, as predicted from TD-DFT calculations (Figure S14), in line with the observed trends upon going from **1** to **2**. The electronic band structure of the corresponding infinite **cove-edged GNRs** (that features the ‘up-down’ twisted conformation) is presented in Figure S30. The wave functions for the frontier crystal orbitals are reminiscent of those obtained for the oligomers and are fully delocalized across the ribbon width, in contrast to zigzag GNRs (with localized states at the ribbon edges).^[41] The bonding-antibonding pattern in the highest occupied crystalline orbital (HOCO) is consistent with formula **2-1** in Scheme 5 being the predominant Clar formula. The electronic band-gap of cove-edged GNR infinite ribbon amounts to 1.70 eV. Mobility calculations were also carried out using the Boltzmann transport equation coupled with the deformation potential theory (Table S1), as implemented in the BoltzTrapP software. The mobility is found to be $1.0 \times 10^3 \text{ cm}^2/\text{Vs}$ for holes and $2.1 \times 10^3 \text{ cm}^2/\text{Vs}$ for electrons. These results are in line with previous charge

transport modeling calculations^[42] performed at the same level of theory for comparable GNRs, which indicate mobilities on the order $10^3\text{-}10^4 \text{ cm}^2/\text{Vs}$ and decreasing as the width of the nanoribbons is reduced.

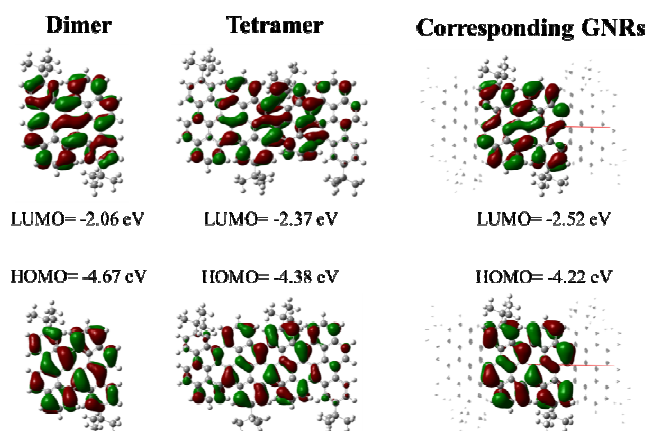


Figure 6. HOMO-LUMO for **1**, **2** and the corresponding GNRs.

CONCLUSION

In summary, we have demonstrated a bottom-up synthetic approach toward unprecedented low band gap GNRs featuring a cove-type periphery. Although the corresponding cyclized chrysene-based oligomers consisting of a dimer and tetramer have been successfully synthesized in solution, the surface-assisted synthesis on an Au (111) yields corresponding GNRs with lengths of up to 20 nm. The unambiguous crystallographic characterization of tetramer **2** reveals that the cove-edge structure causes it to deviate from planarity due to steric repulsion and that it possesses an alternative ‘up-down’ geometry. DFT calculations further demonstrate that the ‘up-down’ geometry of the tetramer has lower energy than the ‘mix’

and “helix” conformers. One would safely conclude that the corresponding infinite GNRs also adopt the alternating “up-down” rolling hill. The DFT calculations predict that such cove-edged GNRs possess low band-gaps ($E_g=1.70$ eV) and high charge carrier mobility for both holes and electrons. Moreover, the electronic properties of the GNRs are expected to be tuned through controlling the width with such cove-type periphery via the bottom-up synthesis. Thereby, the unique optoelectronics properties of such cove-edged GNRs are expected to open a new door toward GNR-based nanoelectronic devices.

ASSOCIATED CONTENT

Supporting Information.

Experimental details, crystallographic data for 5a, dimer and tetramer, NMR, MALDI-TOF MS, UV-vis spectra, cyclic voltammograms, and computational details as well as STM information. This material is available free of charge via the Internet at <http://pubs.acs.org>.

AUTHOR INFORMATION

Corresponding Author

xinliang.feng@tu-dresden.de
muellen@mpip-mainz.mpg

Notes

The authors declare no competing financial interest.

ACKNOWLEDGMENT

This work was financially supported by ERCF grants on NANOGRAPH and 2DMATER, DFG Priority Program SPP 1459, EU Project GENIUS, MOLESOL, the EC under Graphene Flagship (No. CNECT-ICT-604391), the Swiss National Science Foundation, and the Office of Naval Research BRC Program. D.B. is a FNRS Research Director.

REFERENCES

- (1) Son, Y. W.; Cohen, M. L.; Louie, S. G. *Nature* **2006**, *444*, 347-349.
- (2) Li, X.; Wang, X.; Zhang, L.; Lee, S.; Dai, H. *Science* **2008**, *319*, 1229-1232.
- (3) Jiao, L.; Zhang, L.; Wang, X.; Diankov, G.; Dai, H. *Nature* **2009**, *458*, 877-880.
- (4) Kosynkin, D.; Higginbotham, A.; Sinitskii, A.; Lomeda, J.; Dimiev, A.; Price, K.; Tour, J. *Nature* **2009**, *458*, 872-876.
- (5) Cai, J.; Ruffieux, P.; Jaafar, R.; Bieri, M.; Braun, T.; Blankenburg, S.; Muoth, M.; Seitsonen, A. P.; Saleh, M.; Feng, X.; Müllen, K.; Fasel, R. *Nature* **2010**, *466*, 470-473.
- (6) Neto, A. H. C.; Guinea, F.; Peres, N. M. R.; Novoselov, K. S.; Geim, A. K. *Rev. Mod. Phys.* **2009**, *81*, 109-162.
- (7) Gemayel, M. E.; Narita, A.; Dössel, L. F.; Sundaram, R. S.; Kiersnowski, A.; Pisula, W.; Hansen, M. R.; Ferrari, A. C.; Orgiu, E.; Feng, X.; Müllen, K.; Samori, P. *Nanoscale* **2014**, *6*, 6301-6314.
- (8) Bennett, P.B.; Pedramrazi, Z.; Madani, A.; Chen, Y. C.; Oteyza, D. G.; Chen C.; Fischer, F. R.; Crommie, M. F.; Bokor, J. *Appl. Phys. Lett.* **2013**, *103*, 253114.
- (9) Wang, X.; Ouyang, Y.; Li, X.; Wang, H.; Guo, J.; Dai, H. *Phys. Rev. Lett.* **2008**, *100*, 206803.
- (10) Ritter, K. A.; Lyding, J. W. *Nat. Mater.* **2009**, *8*, 235-242.
- (11) Han, M.; Özyilmaz, B.; Zhang, Y.; Kim, P. *Phys. Rev. Lett.* **2007**, *98*, 206805.
- (12) Chen, Y. C.; Oteyza, D. G.; Pedramrazi, Z.; Chen C.; Fischer, F. R.; Crommie, M. F. *ACS Nano* **2013**, *7*, 6123-6128.
- (13) Zhang, X.; Yazyev, O. V.; Feng, J.; Xie, L.; Tao, C.; Chen, Y. C.; Jiao, L.; Pedramrazi, Z.; Zettl, A.; Louie, S. G.; Dai, H.; Crommie, M. F. *ACS Nano* **2013**, *7*, 198-202.
- (14) Tao, C.; Jiao, L.; Yazyev, O. V.; Chen, Y. C.; Feng, J.; Zhang, X.; Capaz, R. B.; Tour, J. M.; Zettl, A.; Louie, S. G.; Dai, H.; Crommie, M. F. *Nat. Phys.* **2011**, *7*, 616-620.
- (15) Yazyev, O. V. *Acc. Chem. Res.* **2013**, *46*, 2319-2328.
- (16) Datta, S. S.; Strachan, D. R.; Khamis, S. M.; Johnson, A. T. C. *Nano Lett.* **2008**, *8*, 1912-1915.
- (17) Campos-Delgado, J.; Romo-Herrera, J.; Jia, X.; Cullen, D.; Muramatsu, H.; Kim, Y.; Hayashi, T.; Ren, Z.; Smith, D.; Okuno, Y.; Ohba, T.; Kanoh, H.; Kaneko, K.; Endo, M.; Terrones, H.; Dresselhaus, M.; Terrones, M. *Nano Lett.* **2008**, *8*, 2773-2778.
- (18) Chen, Z. H.; Lin, Y. M.; Rooks, M. J.; Avouris, P. *Physica E* **2007**, *40*, 228-232.
- (19) Elías A.; Botello-Méndez, A.; Meneses-Rodríguez, D.; González, V.; Ramírez-González, D.; Ci, L.; Muñoz-Sandoval, E.; Ajayan, M.; Terrones, H.; Terrones, M. *Nano Lett.* **2010**, *10*, 366-372.
- (20) Jiao, L.; Wang, X.; Diankov, G.; Wang, H.; Dai, H. *Nat. Nano.* **2010**, *5*, 321-325.
- (21) Sakaguchi, H.; Kawagoe, Y.; Hirano, Y.; Iruka, T.; Yano, M.; Nakae, T. *Adv. Mater.*, **2014**, *26*, 4134-4138.
- (22) Pan, Z.; Liu, N.; Fu, L.; Liu, Z. *J. Am. Chem. Soc.* **2011**, *133*, 17578-17581.
- (23) Wu, J.; Gherghel, L.; Watson, M.; Li, J.; Wang, Z.; Simpson, C.; Kolb, U.; Müllen, K. *Macromolecules* **2003**, *36*, 7082-7089.
- (24) Yang, X.; Dou, X.; Rouhanipour, A.; Zhi, L.; Räder, H.; Müllen, K. *J. Am. Chem. Soc.* **2008**, *130*, 4216-4217.
- (25) Fogel, Y.; Zhi, L.; Rouhanipour, A.; Andrienko, D.; Räder, H.; Müllen, K. *Macromolecules* **2009**, *42*, 6878-6884.
- (26) Schwab, M. G.; Narita, N.; Hernandez, Y.; Balandina, Y.; Mali, K. S.; Feyter, S. D.; Feng, X.; Müllen, K. *J. Am. Chem. Soc.* **2012**, *134*, 18169-18172.
- (27) Dössel, L.; Gherghel, L.; Feng, X.; Müllen, K. *Angew. Chem. Int. Ed.* **2011**, *50*, 2540-2543.
- (28) Chen, L.; Hernandez, Y.; Feng, X.; Müllen, K. *Angew. Chem. Int. Ed.* **2012**, *51*, 7640-7654.
- (29) Narita, A.; Feng, X.; Hernandez, Y.; Jensen, S. A.; Bonn, M.; Yang, H.; Verzhbitskiy, I. A.; Casiraghi, C.; Hansen, M.R.; Koch, A. H. R.; Fytas, G.; Ivasenko, O.; Li, B.; Mali, K. S.; Tatyana, B.; Mahesh, S.; Feyter, S. D.; Müllen, K. *Nat. Chem.* **2014**, *6*, 126-132.
- (30) Cai, J.; Pignedoli, C. A.; Talirz, L.; Ruffieux, P.; Söde, H.; Liang, L.; Meunier, V.; Berger, R.; Li, R.; Feng, X.; Müllen, K.; Fasel, R. *Nat. Nano.* **2014**, *9*, 896-900.
- (31) Narita, A.; Verzhbitskiy, I. A.; Frederickx, W.; Mali, K. S.; Jensen, S. N.; Hansen, M. R.; Bonn, M.; Feyter, S. D.; Casiraghi, C.; Feng, X.; and Müllen, K. *ACS Nano* **2014**, *8*, 11622-11630.
- (32) Plasser, F.; Pašalić, H.; Gerzabek, M. H.; Libisch, F.; Reiter, R.; Burgdörfer, J.; Müller, T.; Shepard, R.; Lischka, H. *Angew. Chem. Int. Ed.* **2013**, *52*, 2581-2584.
- (33) Vo, T. H.; Shekhirev, M.; Kunkel, D. A.; Morton, M. D.; Berglund, E.; Kong, L.; Wilson, P. M.; Dowben, P. A.; Enders, A.; Sinitskii, A. *Nat. Commun.* **2014**, *5*, 3189.

- (34) Chen, Y. C.; Cao, T.; Chen, C.; Pedramrazi, Z.; Haberer, Z.; Oteyza, D. G.; Fischer, F. R.; Louie, S. G.; Crommie, M. F. *Nat. Nano.* **2015**, 10, 156-160.
- (35) Konishi, A.; Hirao, Y.; Matsumoto, K.; Kurata, H.; Kishi, R.; Shigeta, Y.; Nakano, M.; Tokunaga, K.; Kamada, K.; Kubo T. *J. Am. Chem. Soc.* **2013**, 135, 1430-1437.
- (36) Konishi, A.; Hirao, Y.; Nakano, M.; Shimizu, A.; Botek, E.; Champagne, B.; Shiomi, D.; Sato, K.; Takui, T.; Matsumoto, K.; Kurata, H.; Kubo T. *J. Am. Chem. Soc.* **2010**, 132, 11021-11023.
- (37) Zhong, Y.; Kumar, B.; Oh, S.; Trinh, M. T.; Wu, Y.; Elbert, K.; Li, P.; Zhu, X.; Xiao, S.; Ng, F.; Steigerwald, M. L.; Nuckolls, C. *J. Am. Chem. Soc.* **2014**, 136, 8122-8130.

- (38) Ball, M.; Zhong, Y.; Wu, Y.; Schenck, C.; Ng F.; Steigerwald, M.; Xiao, S.; Nuckolls, C. *Acc. Chem. Res.* **2015**, 48, 267-276.
- (39) Konishi, A.; Hirao, Y.; Kurata, H.; Kubo, T. *Solid State Commun.* **2013**, 175-176, 62-70.
- (40) Horcas, I.; Fernández, R.; Gómez-Rodríguez, J. M.; Colchero, J.; Gómez-Herrero, J.; Baro, A. M. *Rev. Sci. Instrum.* **2007**, 78, 013705.
- (41) Magda, G. Z.; Jin, X.; Hagymási, I.; Vancsó, P.; Osváth, Z.; Nemes-Incze, P.; Hwang, C.; Biró L. P.; Tapasztó, L. *Nature* **2014**, 514, 608-611.
- (42) Chen, L.; Wang, L.; Beljonne, D. *Carbon* **2014**, 77, 868-879.

